

Magnetic Functionalities in MOFs: from the Framework to the Pore

Guillermo Mínguez Espallargas* and Eugenio Coronado*

Instituto de Ciencia Molecular (ICMol), Universidad de Valencia, c/ Catedrático José Beltrán, 2, 46980 Paterna, Spain.

0. Abstract

In this review, we show the different approaches so far developed to prepare Metal-Organic Frameworks (MOFs) presenting electronic functionalities, with particular attention to magnetic properties. We will cover the chemical design of the framework necessary for the incorporation of different magnetic phenomena, as well as the encapsulation of functional species in the pores leading to hybrid multifunctional MOFs combining an extended lattice with a molecular lattice.

1. Introduction

Metal-organic frameworks (MOFs), also known as porous coordination polymers (PCPs), have emerged in the last 30 years as revolutionary materials with applications in societal and industrially relevant domains such as storage of fuels (hydrogen and methane), capture of gases (e.g. greenhouse gases), separation, drug delivery and catalysis, among others.¹ Recent advances in this area in the past decade has resulted in an explosive growth in their preparation, characterization, and study, with over 5000 publications on this topic in 2016 and more than 80.000 MOFs reported.² The common property for all these open crystalline frameworks is their permanent porosity constructed from the assembly of inorganic sub-units (metal centres, clusters, chains...) and organic linkers (carboxylates, phosphonates, azolates, etc.). In a similar way as zeolites, they present large cavities in their structures. However, unlike zeolites and mesoporous silica, the adaptable nature of the organic ligands and their variety of coordination modes, together with the geometry of the constitutive metal ions, provide an assortment of topologies and different architectures that can be intended by chemical design. In addition to this structural property, these crystalline solids may also exhibit other properties arising from the diverse manners in which different functionalities can be incorporated into these materials.

In particular, electronic properties, i.e. magnetic, electric or optical properties, can also be introduced in the MOF by adequately choosing the functional nodes, the organic linkers and the way in which they are connected in the solid, or by including functional molecules in the pores. These possibilities, which largely span the applications of these materials, have started to be exploited only very recently. Thus, the introduction of electrical conductivity in a MOF remains an

almost unexplored topic since for the most part these materials are insulators.³ A recent review that covers this topic has recently been published.⁴ As far as the luminescent MOFs are concerned, this area has also been extensively reviewed recently for their use in chemical sensing and explosive detection,⁵ light-harvesting sensitizers,⁶ and light emitting applications.⁷

In the present review, we will focus on the molecular design of magnetic MOFs. In these materials and depending on the magnetic dimensionality within and between the two constituent sublattices (the extended framework and the molecular units), one can distinguish between MOFs exhibiting cooperative properties (e.g., magnetic ordering or cooperative spin crossover), or MOFs exhibiting molecular properties (e.g., single-molecule magnetism). We do not intend to provide a comprehensive collection of the literature, but to illustrate with selected examples the current state-of-the-art of the different approaches that have been employed to incorporate this functionality into MOFs.

In the field of molecular magnetism, coordination polymers have been extensively used to generate magnetic materials exhibiting cooperative properties. In this area, a major focus of interest during the last 30 years has been to design high- T_c magnets, i.e., molecule-based magnetic materials exhibiting spontaneous magnetization above room temperature.⁸ These materials are highly desired in magnetism since they can compete with the traditional inorganic magnets, showing at the same time superior properties from the point of view of their chemical versatility (they are prepared using coordination chemistry at low temperatures) and their structural and electronic versatilities (they are transparent and can often incorporate more functional properties). Taking advantage of this last feature, a current challenge in this field has been the incorporation of two or more properties in the same material, i.e. the preparation of a multifunctional magnetic materials in which magnetism is co-existing and/or coupled with a second property of interest, like conductivity, superconductivity, luminescence, bistability, porosity, etc.⁹ Thus, playing with a molecular approach, it has been possible to incorporate in the same material two properties that are difficult, or even impossible, to achieve in a conventional solid-state material. Depending on the way in which the two components are integrated in the coordination material, one can differentiate between “two-network materials”, composed of two independent networks each of them providing a physical property, and “one-network material”, in which the two properties are strongly coupled thus often leading to stimuli-responsive materials. Examples of the first approach have given rise to the combination of magnetism with conductivity, or even superconductivity, in the same crystal,^{10,11} whereas examples of the second approach can be found in the so-called spin-crossover complexes with LIESST effect,¹² or in Prussian Blue Analogues (PBAs) with photomagnetism,¹³ or piezomagnetism.¹⁴ In this case,

the magnetism is coupled with light or pressure in such a way that by applying the corresponding external stimulus (light irradiation or pressure) the spin state can be tuned.

There are several reasons that justify the extension of this approach to the field of MOFs. On the one hand, the possibility of adding porosity to these magnetic coordination polymers offers an attractive way to generate multifunctional materials in which the magnetism can be tuned by the presence of molecules in the pores. Thus, these systems provide an ideal scenario to unravel the role played by the guest-framework intermolecular interactions, the chemical pressure generated by the guest molecules, or the modifications of the electronic properties in the MOF (i.e. isostructural MOFs with different ligands) on the magnetic behaviour. These features may be of interest for sensing the molecular species trapped in the pores through their magnetic response. On the other hand, the presence of magnetic centres either in the nodes or in the pores of a crystalline MOF opens the possibility of creating organized nanostructures of these magnetic centres, while keeping them well separated in the space. Such a feature may be of potential interest in quantum technologies, as they require a controlled disposition of magnetic moieties in the space. All these possibilities will be illustrated in the present review, which is organized as follows:

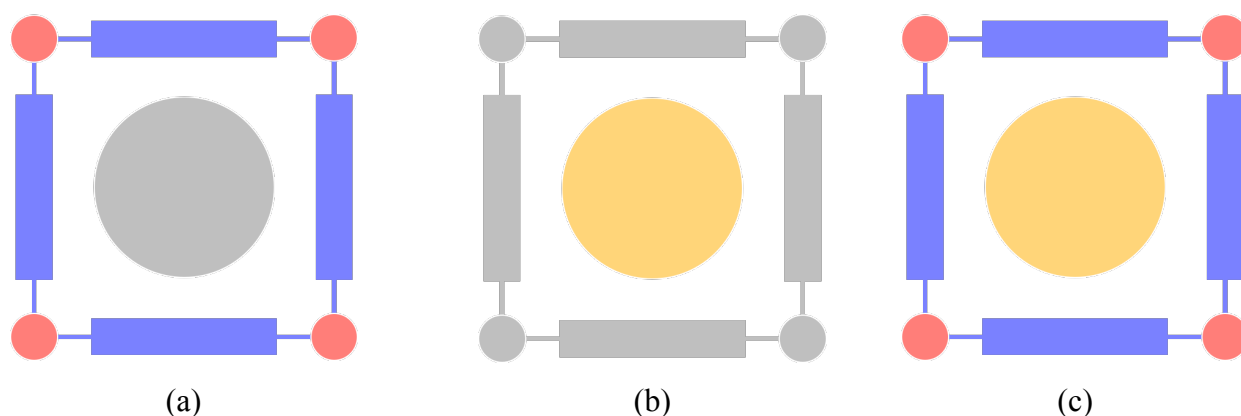



Figure 1. Schematic representation of (a) a magnetic MOF with a non-functional guest, (b) a non-magnetic MOF with a functional guest, and (c) a magnetic-MOF with a functional guest.

The first part is dedicated to MOFs in which the coordination framework is magnetic (Figure 1a). In these materials, a rational chemical design has been crucial for the appearance of new properties and for controlling the effects of different stimuli on the magnetic properties. This part covers both MOF showing solid-state properties, such as long-range magnetic order (presenting magnetic cooperativity) or spin-crossover (presenting elastic cooperativity), and MOFs showing molecular properties as a result of the incorporation of functional molecules at the nodes of the framework. In this last case, the functional molecules –single-molecule magnets, in particular– are

isolated by the organic spacers (i.e., no cooperative properties are expected). Still, the crystallinity of these porous materials will give rise to long-range arrangements of these functional molecules, providing a useful way to obtain organized nanostructures of these magnetic molecules. The second part presents the inclusion of functional molecules (magnetic in particular) in the channels of the framework to give rise to hybrid functional MOFs combining an extended lattice with a molecular lattice. In this case, one can distinguish between the system formed by a non-magnetic MOF and a functional guest (Figure 1b), or a magnetic MOF combined with a functional guest (Figure 1c). In the latter, a judicious choice of the molecule is the key for the appearance of different functionalities. The examples here presented will show that these porous solids provide an ideal platform to create new multifunctional materials covering from the simple co-existence of different electronic properties, provided by the framework and the functional guest, to a synergy between these functionalities as a result of the coupling between the two components.

2. MOFs based on magnetic frameworks

The preparation of MOFs based on magnetic frameworks is an example of a one network multifunctional material where the magnetic property coexists with the presence of porosity. These porous materials offer the possibility of inserting additional molecules in the pores (either gas molecules or other guests), acting as external chemical stimuli that can serve to tune the magnetism of the framework.¹⁵ Depending on the origin of the magnetic phenomena, four types of MOFs based on magnetic framework can be differentiated (Figure 2): a) magnetic MOFs, where magnetic cooperativity results through magnetic exchange via the ligands; b) spin-crossover MOFs, where the nodes have suitable coordination environments for this phenomena to exist; c) MOFs with magnetic relaxation, where the nodes are clusters possessing an anisotropic spin ground state; with single-molecule magnet behaviour; d) MOFs with magnetocaloric effect, where the nodes are clusters possessing an isotropic spin ground state.

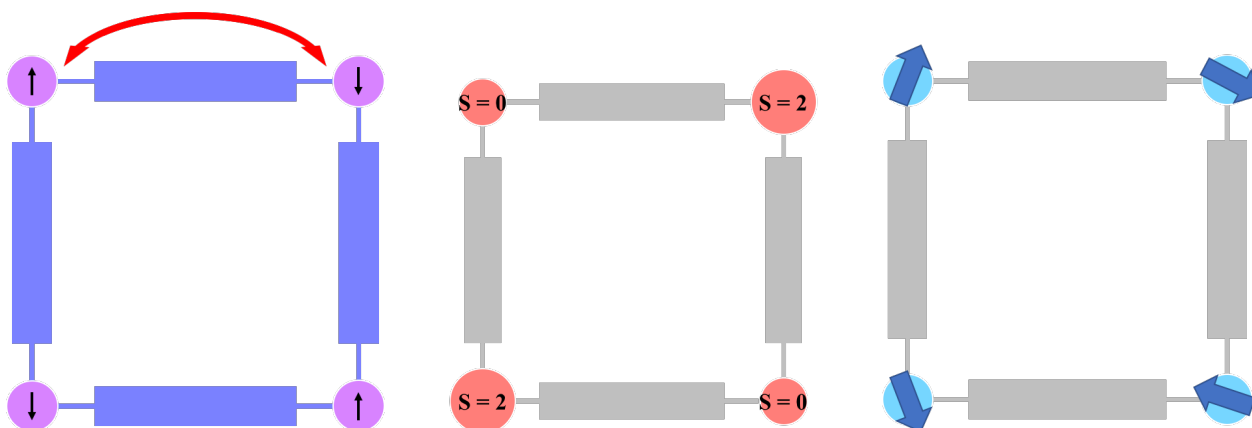

(a) (b) (c)

Figure 2. Schematic representation of the different strategies to incorporate magnetic functionalities in MOFs: (a) magnetic exchange via the ligands; (b) spin-crossover at the nodes; (c) MOFs with magnetic clusters in the nodes (anisotropic spin for SMM, isotropic spin for magnetocaloric).

2.1. Magnetic MOFs

The coexistence of magnetism and porosity is a challenging aspect from the point of view of the chemical design, as these two properties are inimical to one another: whereas magnetic exchange interactions require short distances between the metal centres, which are most commonly the spin carriers, porosity is typically favoured with the use of long linkers, which are often too long for magnetic ordering to exist at temperatures much above absolute zero. However, different synthetic routes can be envisaged towards the formation of porous magnetic materials, which will be presented below (Figure 3). First, the use of short linkers will be described in the preparation of magnetic MOFs (Figure 3a), with selected examples using formate, cyanide, azolates, diazines, and lactate, and then moving to their combination with longer linkers that can provide large pore apertures. Secondly, a different synthetic route to achieve the preparation of magnetic MOFs will be explained, which consists on using preformed complexes, i.e. a metallo-ligand approach (Figure 3b). Finally, we will finish this section by showing that exchange coupling and porosity can also be combined through the use of radical ligands (Figure 3c), and different examples of the use of varied radicals will be described.

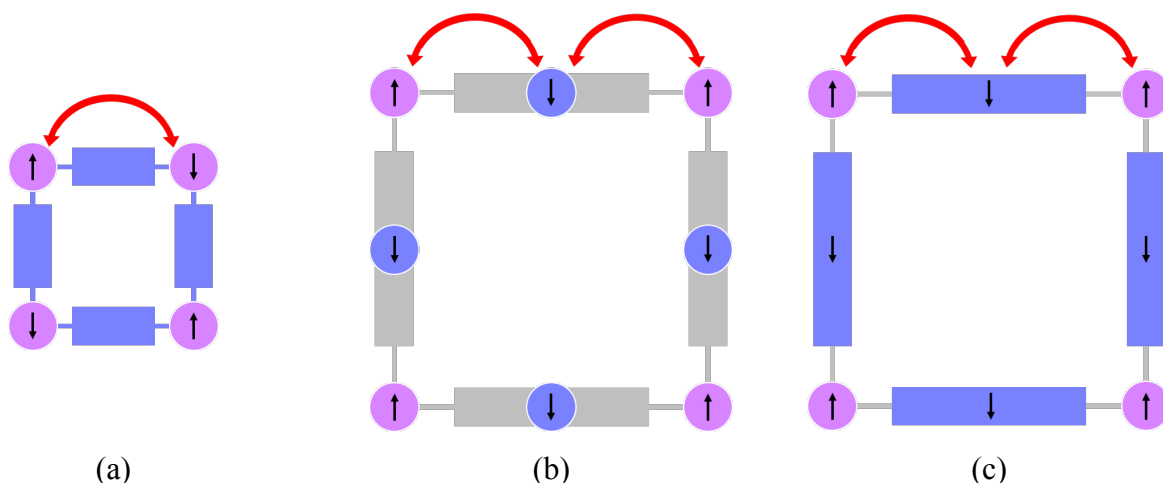


Figure 3. Schematic representation of the different synthetic routes available for the preparation of magnetic MOFs: (a) use of short linkers; (b) metallo-ligand approach; (c) use of radicals as ligands.

a) Use of short linkers. MOF synthesis is dominated by the use of relatively long ligands that can provide open frameworks, but this approach typically prevents the existence of magnetic interaction between the metal centres. Among the denser structures with shorter linkers, long-range magnetic order can emerge, although sorption of gases in this situation is rather atypical. This problem has nevertheless been circumvented by our group in a dense Cu coordination polymer capable of incorporating gas molecules into the framework thus alleviating the necessity for pores in the structure for gas sorption to occur.¹⁶ In this paper it was found that chemisorption of gaseous HCl molecules instigates drastic modifications in the magnetic properties of the material, which switch from strong antiferromagnetic exchange interactions between the Cu(II) ions to ferromagnetic ones upon gas sorption. These magnetic conversions result from profound structural changes, as the gas molecules are directly incorporated into the framework rather than located in pores, and despite involving cleavage and formation of covalent bonds there is no disruption of crystallinity, which provide direct structural evidence of the modification of the magnetic pathways. However, in the above example these exchange interactions were not sufficient to trigger the appearance of a long range magnetic order, at least at the temperatures at which the magnetic behaviour was studied (above 2K). The main reason of this result was the low magnetic dimensionality of these coordination compounds (formed by exchange-coupled dimers and chains).

Using this approach, more pronounced cooperative effects were observed in higher dimensional systems and, in particular, in 3D frameworks based on short organic linkers. An example of this kind is provided by ammonium metal formate frameworks. These compounds have shown the coexistence of magnetic and electric orderings in a family of multiferroic three-dimensional frameworks of formula $[(\text{CH}_3)_2\text{NH}_2][\text{M}(\text{HCOO})_3]$ and $[\text{NH}_4][\text{M}(\text{HCOO})_3]$ (M= Mn, Fe, Co, and Ni), as demonstrated by the groups of Cheetham¹⁷ and Gao¹⁸. Specifically, these compounds display paraelectric to ferroelectric phase transitions between 160 and 254 K, which is combined with spin-canted antiferromagnetic ordering (in the range 8 to 36 K), as shown in Figure 4. The origin of the ferroelectricity is caused by disorder-order transitions of the ammonium cations and their displacement within the channels of the framework, as demonstrated by single crystal diffraction, whereas the magnetic ordering is caused by the use of the short formate linkers. This type of solids has been extensively investigated in the recent years,¹⁹ but due to the presence of the cations in the pores no gas sorption has been observed.

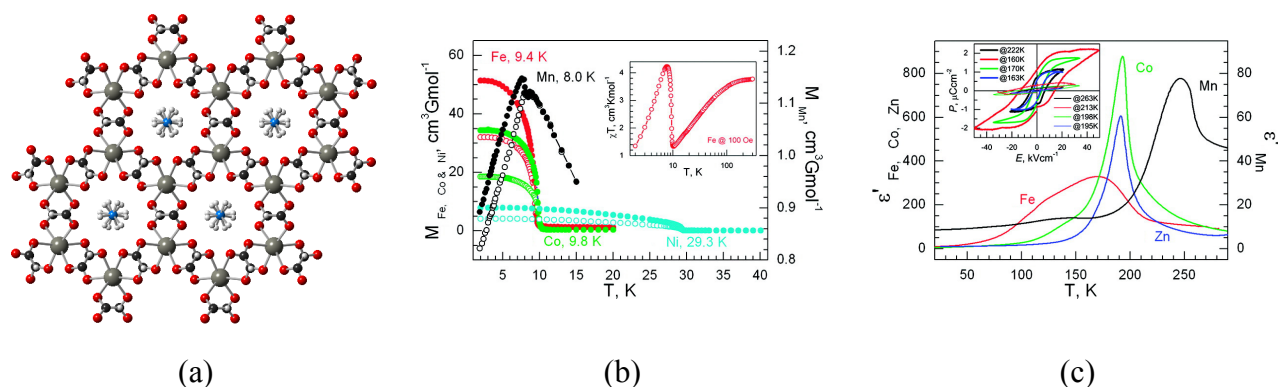


Figure 4. a) Crystal structure of [NH₄][M(HCOO)₃]; b) Zero-field-cooled (open symbols) and field-cooled (filled symbols) magnetization plots of the Mn, Fe, Co, and Ni derivatives under 5 or 10 Oe fields. Inset: temperature dependence of the magnetic susceptibility of the Fe derivative under 100 Oe field; c) Temperature-dependent traces of the real part of the dielectric permittivities, ϵ' , for the Mn, Fe, Co, and Zn derivatives, with $E//c$ at 10 kHz. Inset: electric hysteresis loops for the four materials at temperatures below and above the transition points, with $E//c$. Reprinted with permission from reference 18, Copyright 2011 American Chemical Society.

An approach that has been developed to introduce porosity in the above family consists of using bulky amines instead of ammonium. This yields a related family of three-dimensional isostructural porous formates of formula $M_3(\text{HCOO})_6$ ($M = \text{Mn, Fe, Co, Ni}$), in which the bulky amine acts as a structure directing agent and is not incorporated into the solids. This family of porous magnets, discovered independently by three groups, consists of a diamond net combining octahedral and tetrahedral nodes with the pores occupied by a great variety of solvent molecules, which can be removed upon heating (Figure 5).^{20,21,22,23,24,25,26} The magnetic behaviour of these magnetic MOFs depends on the type of metal ion: the iron, and manganese formates are ferromagnets, with critical temperatures T_C of 16.1 and 8.0, whereas the cobalt compound is a spin-canted antiferromagnet below 1.8 K and the nickel derivative displays 3D long-range ferromagnetic ordering at 2.7 K (see Figure 5b). The permanent porosity of these MOFs has been proven by gas adsorption, revealing a BET surface of 360 m²/g. Furthermore, the available space has been confirmed by successfully inserting over 40 different guests into the pores, which also modulate T_C possibly due to subtle changes in the M–O–M angles and/or host-guest hydrogen-bond interactions.

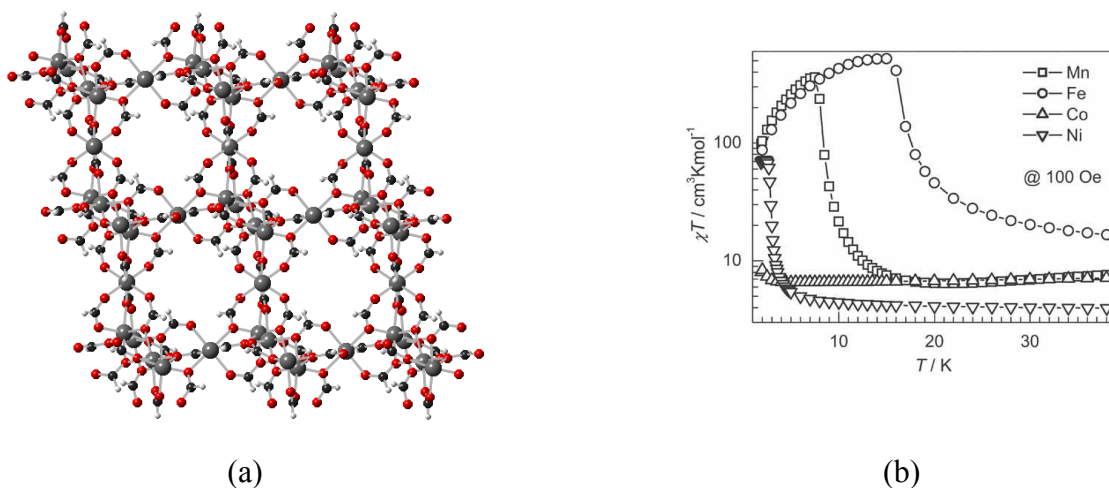


Figure 5. Crystal structure of $M_3(\text{HCOO})_6$; b) Temperature dependence of susceptibility for $[M_3(\text{HCOO})_6]$ of $M=\text{Mn, Fe, Co, and Ni}$ between 2–40 K. Note that the χT scale is logarithmic for easy representation of the large difference in χT values for different compounds. Adapted from reference 26, with permission from Wiley.

The smallest bridging ligand that has been used to design magnetic coordination polymers is cyanide. An extensive family of three-dimensional (3D) bimetallic frameworks based on this linker, referred to as Prussian blue analogues,²⁷ has been reported. In these coordination polymers the small size of the cyanide, which provides suitable pathways for magnetic superexchange, together with the 3D character of the magnetic lattice, leads to magnets ordering at relatively high temperatures. Many laboratories have been very active on this type of materials since the pioneering works of Verdager and Hashimoto, including nowadays the groups of Ohkoshi, Sieklucka, Dunbar, Girolami, Sato, Oshio, Coronado, Clerac, Long, Mallah, Larionova and Miller.²⁸ One compound of this family, $\text{Co}_3[\text{Co}(\text{CN})_5]_2$, was the first material in which long-range magnetic ordering and microporosity was rigorously demonstrated to coexist.²⁹ Thus, despite the use of such a short linker, Long and co-workers reported a magnetic ordering at 38 K with BET surface area of 480 m^2/g , determined by N_2 adsorption. Some years later, it was demonstrated on two related compounds of formula $\text{CsNi}[\text{Cr}(\text{CN})_6]$ and $\text{Cr}_3[\text{Cr}(\text{CN})_6]_2 \cdot 6\text{H}_2\text{O}$ (Figure 6) that sorption of paramagnetic O_2 molecules causes an increase in the ordering temperature, explained by the authors as a result of ferromagnetic coupling between the gas and the $[\text{Cr}(\text{CN})_6]^{3-}$ units of the frameworks, as diamagnetic N_2 does not cause any shift that could be originated from a structural transition.³⁰ More specifically, $\text{CsNi}[\text{Cr}(\text{CN})_6]$ is a ferromagnet with ordering temperature of 75 K, and upon O_2 sorption the $[\text{Cr}(\text{CN})_6]^{3-}$ units couple ferromagnetically with the spin of the adsorbed O_2 molecules. Differently, $\text{Cr}_3[\text{Cr}(\text{CN})_6]_2 \cdot 6\text{H}_2\text{O}$ orders at 219 K, and the sorption of O_2 molecules causes a

decrease in the magnetic moment of the system, as well as a reduction in the coercivity from 110 to 10 Oe and the remnant magnetization from 1200 to 440 emu·G/mol.

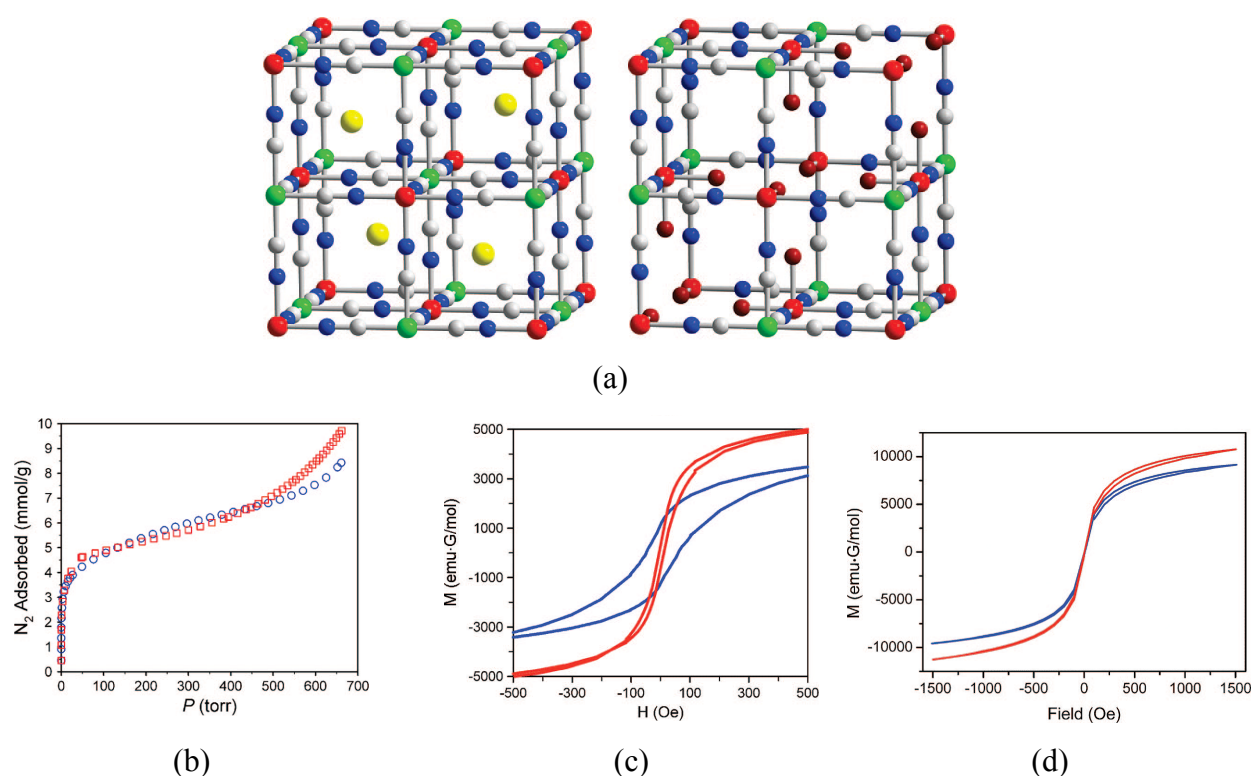


Figure 6. a) Crystal structure of $\text{CsNi}[\text{Cr}(\text{CN})_6]$ (left) and $\text{Cr}_3[\text{Cr}(\text{CN})_6]_2 \cdot 6\text{H}_2\text{O}$ (right); b) Nitrogen adsorption isotherms for $\text{CsNi}[\text{Cr}(\text{CN})_6]$ (red squares) and $\text{Cr}_3[\text{Cr}(\text{CN})_6]_2 \cdot 6\text{H}_2\text{O}$ (blue circles), as measured at 77 K; c) Magnetic hysteresis loops, measured at 5 K, of $\text{Cr}_3[\text{Cr}(\text{CN})_6]_2 \cdot 6\text{H}_2\text{O}$ (blue) and $\text{Cr}_3[\text{Cr}(\text{CN})_6]_2 \cdot 6\text{H}_2\text{O}$ sealed in a quartz tube containing 2.9 molecules of O_2 per formula unit (red); d) Magnetic hysteresis loops, measured at 2 K of $\text{CsNi}[\text{Cr}(\text{CN})_6]$ (blue) and $\text{CsNi}[\text{Cr}(\text{CN})_6]$ sealed in a quartz tube containing 1.8 molecules of O_2 per formula unit (red). Reproduced from reference 30, Copyright 2008 American Chemical Society. Further permissions related to this material should be directed to the ACS.

Another family of short organic ligands that have also been employed for the preparation of MOFs is that provided by azolates, which can form strong and directional coordination bonds serving as bridges between metal ions,^{31,32} and therefore are appealing candidates for the preparation of magnetic MOFs. For example, zeolitic imidazolate frameworks (ZIFs) are a subfamily of MOFs consisting of tetrahedral metal centers (Zn^{II} and Co^{II} primarily) connected by bent imidazolate-derived organic ligands, with geometrical features analogous to those of zeolites.³³ Thus, despite the use of a short linker such as imidazolate, highly porous solids of different

topologies can be obtained, akin to zeolites, which in the case of Co^{II} are also magnetic. The term ZIF was coined in 2006,³⁴ but some years earlier Gao and You reported the structures and magnetic properties of seven polymorphs of $\text{Co}(\text{imidazolate})_2$, indicating structural features similar to that of silica, although no studies on gas sorption were performed at that moment (Figure 7).^{35,36,37} The robustness of the porous framework was nevertheless proven in one of these polymorphs by exchanging the included template with EtOH and removing it later by vacuum treatment.²⁶ Although imidazolates transmit the antiferromagnetic coupling between the Co^{II} ions in these structures, the uncompensated antiferromagnetic couplings arising from the non-centrosymmetric structures have often lead to the appearance of weak ferromagnets (also known as canted-antiferromagnets) as a consequence of the spin-canting.

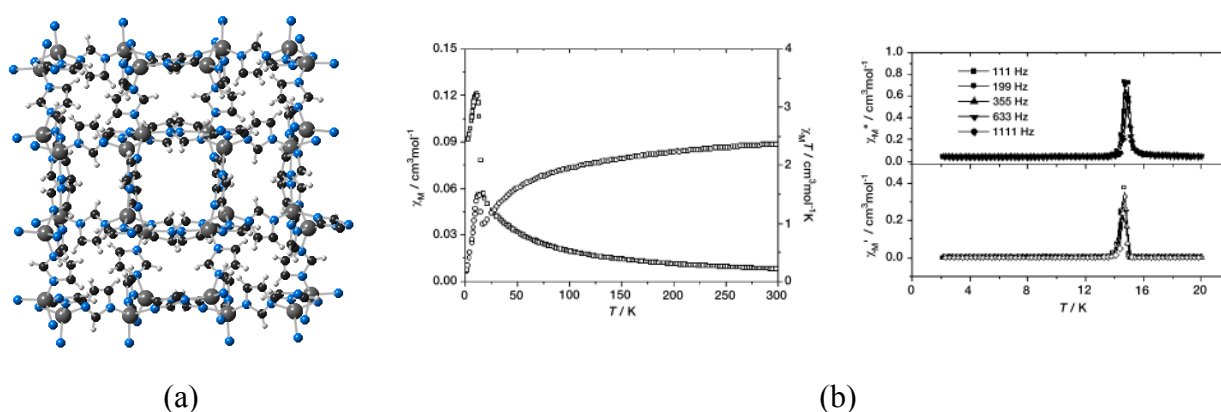


Figure 7. a) Crystal structure of $\text{Co}(\text{imidazolate})_2$; b) Plots of temperature dependence of χ_M and χ_{MT} for $\text{Co}(\text{imidazolate})_2$ measured at 10 kOe field (left) and temperature dependence of AC susceptibility χ' (top) and χ'' (bottom) obtained at 20 Oe field. Adapted from reference 36, with permission from Wiley.

Functionalized imidazolates with additional coordination groups have also been used for the formation of magnetic MOFs. For example, Figure 8 shows the crystal structure of a $\text{Co}(\text{II})$ –imidazolate-4-amide-5-imidate based MOF, which possesses 1D hexagonal channels and a BET surface area of $649 \text{ m}^2/\text{g}$.³⁸ The cobalt centres are penta-coordinated by the imidazolate–amide–imidate linkers to form a distorted trigonal–bipyramidal geometry, with antiferromagnetic coupling between the metal centres.



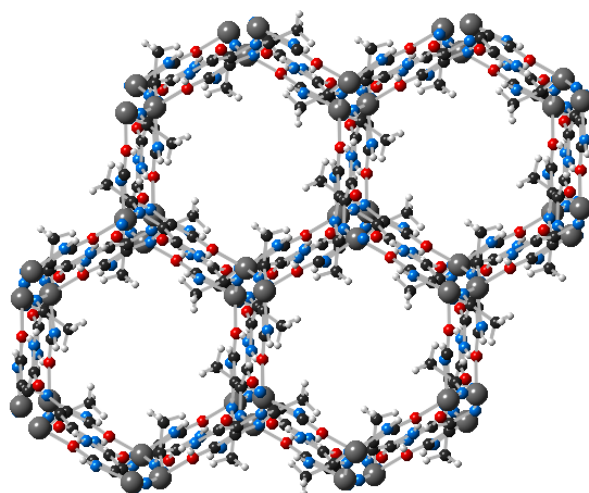


Figure 8. Crystal structure of Co(imidazolate-4-amide-5-imidate)·0.5DMF. Adapted from reference 38, with permission from The Royal Society of Chemistry.

Another interesting example of the use of a functionalized azolate, is provided by a magnetic MOF that undergoes multiple changes in the magnetic properties upon desolvation/resolvation, as shown in Figure 9.³⁹ The parent compound, $[\text{Cu}(\text{tzc})(\text{dpp})] \cdot 2\text{H}_2\text{O}$, can lose one equivalent of water to form the monohydrate phase $[\text{Cu}(\text{tzc})(\text{dpp})] \cdot \text{H}_2\text{O}$, or can also transform into an anhydrous phase $[\text{Cu}(\text{tzc})(\text{dpp})]$, which can exist in three different polymorphs. The dihydrate phase shows antiferromagnetic exchange interactions, whereas ferromagnetic properties are observed for the trimorphic anhydrate system.

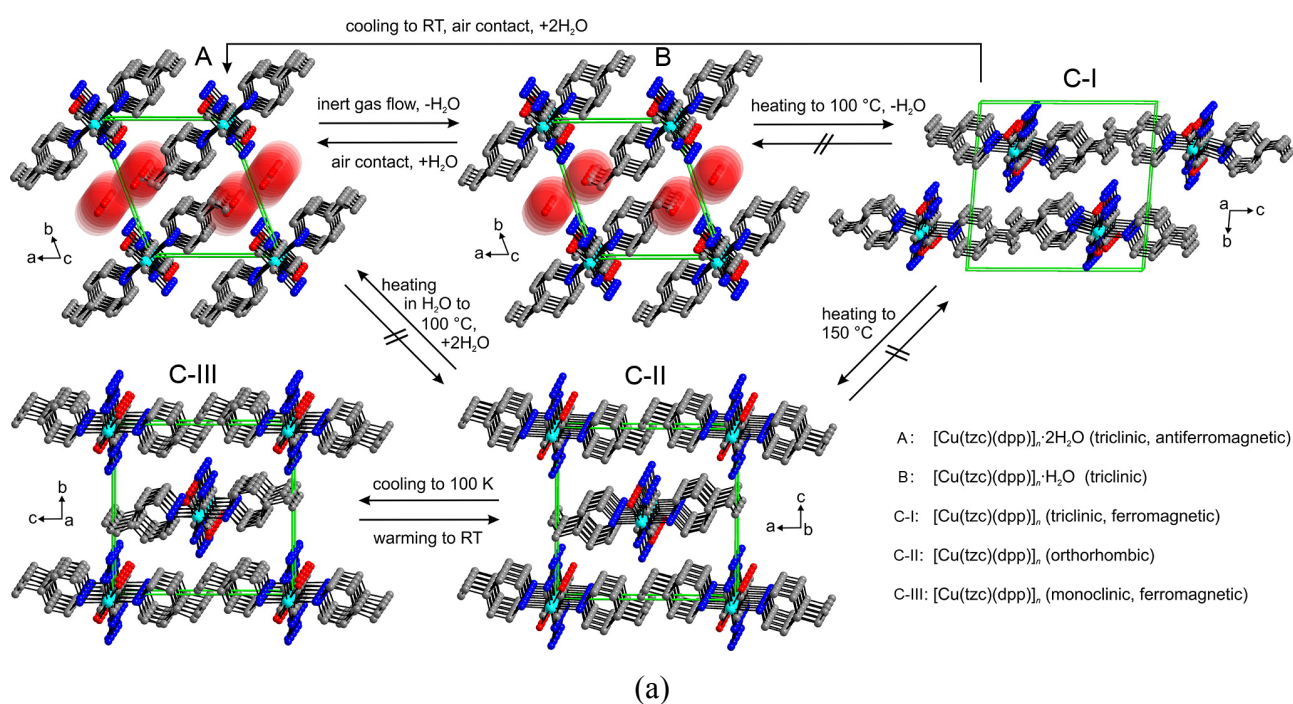

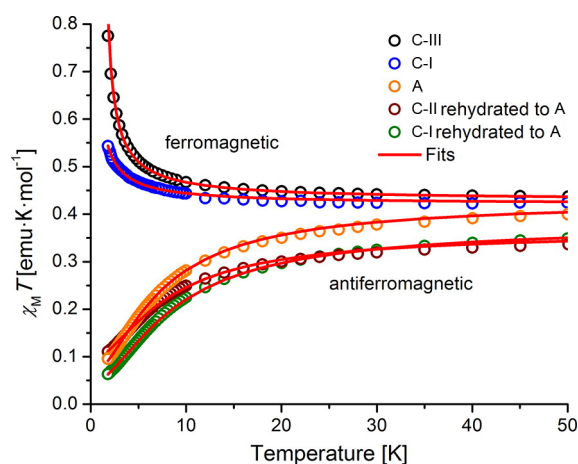

(b)

Figure 9. Crystal structures of the hydrates $[\text{Cu}(\text{tzc})(\text{dpp})] \cdot 2\text{H}_2\text{O}$ (4, A), $[\text{Cu}(\text{tzc})(\text{dpp})] \cdot \text{H}_2\text{O}$ (5, B) and its polymorphic anhydrous modifications $[\text{Cu}(\text{tzc})(\text{dpp})]$ (6I, C; 6II, D; 6III, E) viewed as stacked chains in a single unit cell. Arrows and labels indicate the directions and conditions, respectively, for phase transitions occurring between these phases. Reprinted with permission from reference 39, Copyright 2013 American Chemical Society.

A related family of heterocyclic ligands that can also promote magnetic exchange is provided by diazines, which have given rise to the first example of a gas-responsive magnetic material. The Cu-based MOF of formula $[\text{Cu}(\text{F-pymo})_2(\text{H}_2\text{O})_{1.25}]_n$ (F-pymo = 5-fluoropyrimidin-2-olate), shown in Figure 10, has helical channels of ca. 2.9 Å diameter which are filled with water molecules that can be removed upon heating.⁴⁰ The as-synthesized solid shows antiferromagnetic interactions, mediated by the pyrimidine ligands, and it orders as a canted antiferromagnet below $T_N = 24$ K (22 K upon activation). Different gas molecules can be incorporated into the empty channels, like CO_2 , whose presence in the pores causes an increase in the Neel temperature from 22 to 29 K. The authors attribute this increase to a structural perturbation exerted by the CO_2 guests which affect the exchange interaction pathways through the ligands, albeit it cannot be confirmed due to lack of structural information after gas sorption.



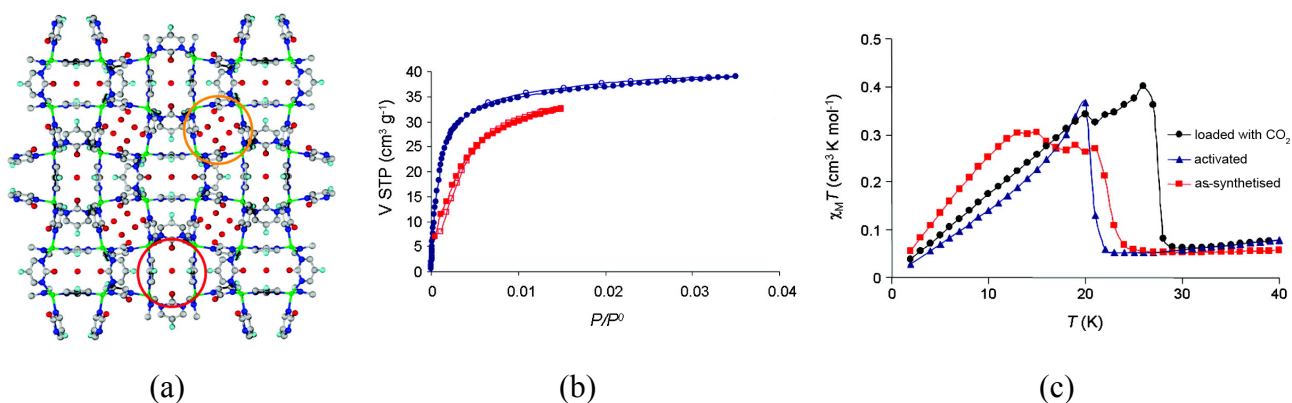


Figure 10. a) Crystal structure of $[\text{Cu}(\text{F-pymo})_2(\text{H}_2\text{O})_{1.25}]_n$; b) CO_2 adsorption isotherm of activated sample of $[\text{Cu}(\text{F-pymo})_2]_n$ at 273 K (circles) and 298 K (squares), with the open symbols denoting desorption; c) Effect of the CO_2 sorption in the magnetic behavior of $[\text{Cu}(\text{F-pymo})_2]_n$ at an external magnetic field of 100 Oe. Reprinted with permission from reference 40, Copyright 2008 American Chemical Society.


An unusual ligand recently employed by Zeng and co-workers for the formation of a porous magnet is lactate. $[\text{Co}^{\text{II}}_3(\text{lac})_2(\text{pybz})_2] \cdot 3\text{DMF}$ is the magnetic analogue of the double-walled framework $[\text{Zn}^{\text{II}}_3(\text{lac})_2(\text{pybz})_2] \cdot 3\text{DMF}$. It is formed by square rod of Co-lactate and the double wall connection between them (Figure 11).⁴¹ The structure contains M–O–M connectivity within the well-separated square chains, which provides a short pathway for magnetic exchange. Interestingly, the solvent molecules that fill the pores can be exchanged with several guests without affecting the integrity of the structure, including gases (N_2 , H_2 and CH_4) and volatile guests (methanol, ethanol, propanol, benzene). However, upon exposure to water molecules or iodine, a structural transformation takes place with the coordination of a water molecule or the oxidation of a Co^{II} centre, yielding respectively to a hydrated and a partially oxidized MOF. The nature of different solvents in the channels modifies the magnetic properties, with a complex magnetic phenomenology observed in this MOF, with four different ground states: canted antiferromagnets for $[\text{Co}^{\text{II}}_3(\text{pybz})_2(\text{lac})_2] \cdot x\text{Solvent}$ and iodine-loaded samples due to the antiferromagnetic interchain coupling ($J' < 0$) via the solvent or iodine molecules, single-chain magnet for the desolvated $[\text{Co}^{\text{II}}_3(\text{pybz})_2(\text{lac})_2]$ as $J' \approx 0$, ferrimagnet for $[\text{Co}^{\text{II}}_3(\text{pybz})_2(\text{lac})_2(\text{H}_2\text{O})_2] \cdot 7\text{H}_2\text{O}$ as $J' > 0$, and ferromagnet for the partially oxidized $[\text{Co}^{\text{III}}\text{Co}^{\text{II}}_2(\text{pybz})_2(\text{lac})_2(\text{H}_2\text{O})_2] \cdot 2\text{H}_2\text{O} \cdot 1.5\text{DMSO}$ as $J' > 0$.

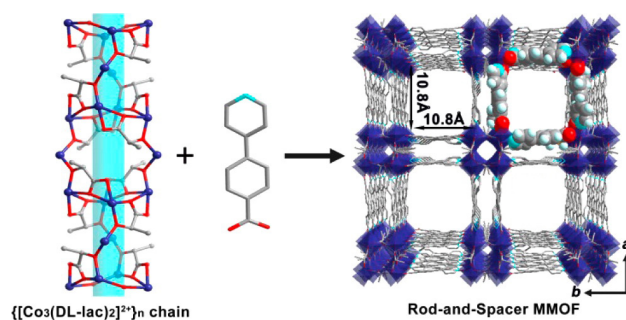

(a)

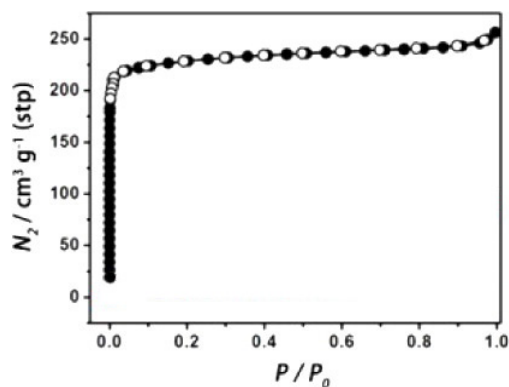

(b)

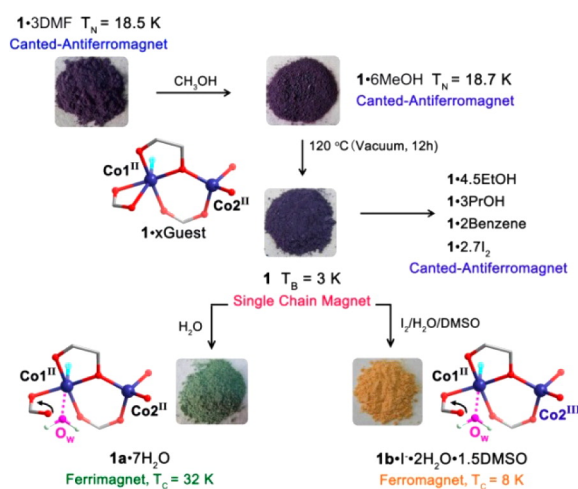

(c)

Figure 11. a) Crystal structure of $[\text{Co}^{\text{II}}_3(\text{pybz})_2(\text{lac})_2(\text{H}_2\text{O})_2]$; b) N_2 sorption isotherm of $[\text{Co}^{\text{II}}_3(\text{pybz})_2(\text{lac})_2(\text{H}_2\text{O})_2]$ at 77 K; c) Post-synthetic modifications and resulting magnetic ground states and changes in coordination and valence of cobalt ions. Reprinted with permission from reference 41, Copyright 2014 American Chemical Society.

All the above examples have been based on the use of short linkers to create a dense metallic packing, while keeping some porosity. A different approach to improve the porosity in these magnetic solids consists on the combination of a short ligand with a considerably longer one.

In this case the short ligand may organize the metal centres in infinite chains (or layers), while the long organic links are orthogonal to those chains (or layers) providing large pore apertures. With this approach, a strong magnetic interaction between the metal centers can be envisaged, although with the limitation of occurring in one (or two) dimensions, which also limits the occurrence of magnetic ordering to low temperatures. A successful example of this methodology is illustrated by the group of MOFs known as MOF-74 or CPO-27, which display Brunauer-Emmett-Teller surface areas over 1000 m²/g and have been identified as among the most promising MOFs for CO₂ capture. These materials, of formula M₂(dhtp)(H₂O)₂ (dhtp = 2,5-dihydroxyterephthalate), have been prepared from several transition metals including Mg^{II}, Zn^{II} and the magnetic Mn^{II}, Fe^{II}, Co^{II}, Ni^{II}, Cu^{II}. The crystal structure is formed by helical chains of *cis*-edge connected metal oxygen octahedral which are each linked by the organic ligand with three adjacent chains, resulting in a honeycomb distribution of one-dimensional channels 11 Å wide (Figure 12). The coordinated water molecule can be removed, leaving an open coordination site accessible to incoming adsorbate molecules. The first magnetic member of this family to be reported was the Co^{II} derivative,⁴² whose magnetic study revealed a metamagnetic-like behaviour, with an antiferromagnetic ordering below 8 K and a field-induced transition to a ferromagnetic-like ordered state upon application of magnetic fields stronger than ca. 2T. The superexchange pathway in the metal–oxygen chain suggests that the magnetic moments couple ferromagnetically in the chains, while the antiferromagnetic long-range order, observed at low magnetic fields, is a consequence of the antiparallel alignment of the spins of adjacent chains. The Fe^{II} derivative Fe-MOF-74 (or CPO-27-Fe) was also reported.⁴³ This compound shows a change of the magnetic exchange along the chains upon exposure to 1 bar of different hydrocarbons, which can be related with the strength of the interaction with the framework (Figure 12c). Thus, weakly interacting adsorbates (methane, ethane, and propane) slightly diminish the strength of the ferromagnetic exchange, whereas those that interact more strongly (propylene, ethylene, and acetylene) reverse the nature of the intrachain coupling from ferromagnetic to antiferromagnetic. Computational studies reveal that in this structure the Fe^{II} centers are always in a high-spin state.^{44,45,46,47}

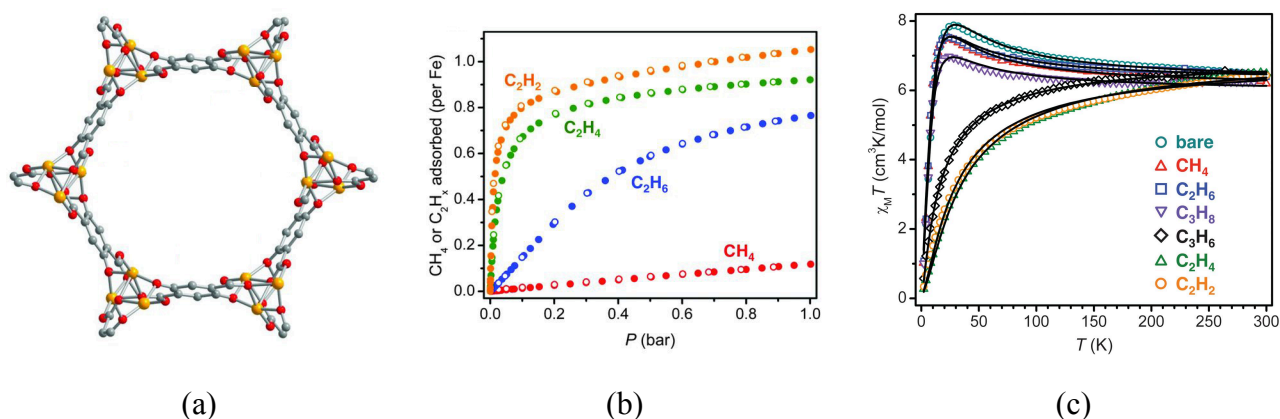


Figure 12. a) Crystal structure of MOF-74; b) Gas adsorption isotherms for methane, ethane, ethylene, and acetylene in Fe-MOF-74 at 318 K; c) Variable-temperature magnetic susceptibility data in an applied field of 1 kOe for samples of Fe-MOF-74 in a vacuum (bare) and under 1 bar of the indicated hydrocarbon (black lines represent magnetic fits). Adapted from reference 43, with permission of the AAAS.

b) Metallo-ligand approach. A different synthetic approach for the preparation of MOFs consists on the use of a “complex-as-ligand” strategy, where a preformed complex acts as a metallo-ligand.⁴⁸ In this approach, a metal complex with vacant additional coordination sites is first prepared and isolated, being used in a second step as a building block towards additional metal ions. By a suitable choice of the metallo-ligand, magnetic communication between the metal nodes can be achieved. This approach has been used extensively in the field of molecular magnetism for the preparation of Prussian blue analogues (via the metallo-ligand $[M^{III}(CN)_6]^{3-}$) and oxalate magnets (via the metallo-ligand $[M^{III}(C_2O_4)_3]^{3-}$), with pores that are filled with countercations.

A successful example of the metallo-ligand approach for the synthesis of magnetic MOFs is the use of oxamato-based oligonuclear complexes, as recently reviewed by Ferrando-Soria and Pardo.⁴⁹ For instance, oxamato-based dinuclear Cu^{II}_2 metallacyclic complexes, with weak ferromagnetic coupling between the Cu^{II} ions, can coordinate Mn^{II} ions through the free carbonyl-oxygen atoms, yielding a 3D MOF of formula $[Na(H_2O)_{3.25}]_4\{Mn_4[Cu_2(Me_3mpba)_2(H_2O)_{3.33}]_3\} \cdot 37H_2O$ [$Me_3mpba^{4-} = N,N'$ -2,4,6-trimethyl-1,3-phenylenebis(oxamate)].⁵⁰ The structure consists of an extended parallel array of anionic, oxamato-bridged Mn_4Cu_6 layers that are further interconnected through the two m-phenylene spacers among the Cu^{II} ions (Figure 13). 3D ferromagnetic ordering is observed, which results from the antiferromagnetic coupling between the high-spin Mn^{II} ($S = 5/2$) and Cu^{II} ($S = 1/2$) ions through the oxamato bridges (2D ferrimagnetic behaviour), and interlayer ferromagnetic interaction across the double 2,4,6-trimethylphenylenebis(amidate) bridges. The magnetic

behaviour depends on the solvent molecules that fill the pores, although gas molecules (CO₂ or CH₄) do not interact with the magnetic framework, maybe due to the amorphization process caused upon activation.

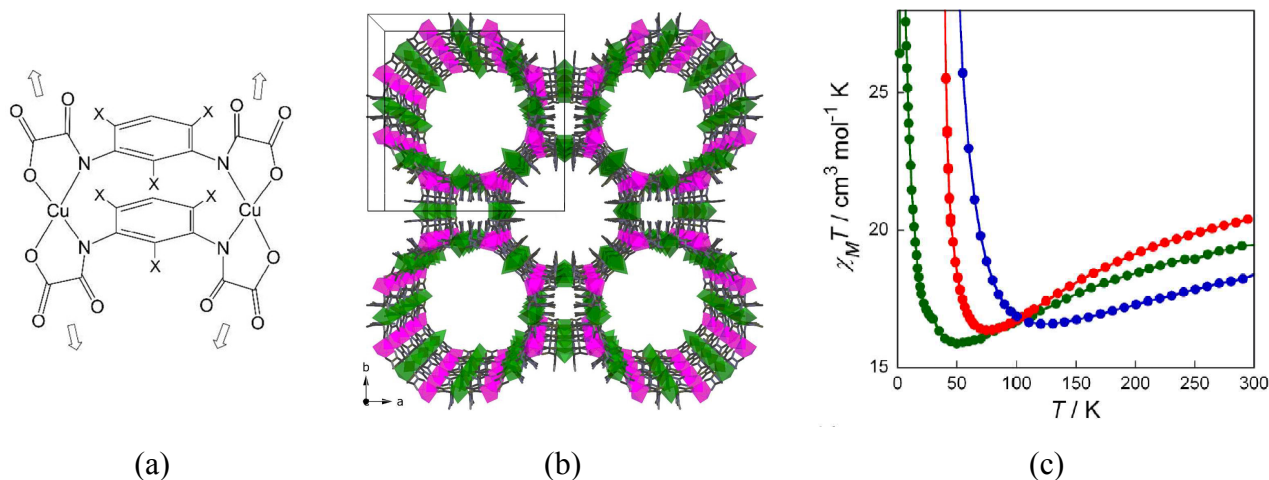


Figure 13. a) Example of an oxamate-based dinuclear metalloligand; b) Crystal structure of [Na(H₂O)_{3.25}]₄{Mn₄[Cu₂(Me₃mpba)₂(H₂O)_{3.33}]₃} · 37H₂O, viewed along the crystallographic c axis showing the pillared square/octagonal layer architecture. Copper and manganese atoms are represented by green and purple octahedra respectively. Free water molecules and Na⁺ counterions have been omitted for clarity; c) Temperature dependence of the product of the direct current (dc) molar magnetic susceptibility by the temperature (χ_MT) the activated MOF (green), with methanol molecules filling the pores (red), and with water molecules filling the pores (blue). Reprinted with permission from reference 50, Copyright 2012 American Chemical Society.

c) Radical-as-ligand approach. An alternative methodology for facilitating the exchange coupling between metal centres of MOFs consists on the incorporation of additional spin carriers in the organic linkers, i.e. the use of radical ligands.⁵¹ This use of non-innocent ligands for the preparation of magnetic MOFs was first shown by Veciana and co-workers, who synthesised a MOF with magnetic sponge-like behaviour using polychlorinated triphenylmethyl tricarboxylic acid radical (ptmtc).⁵² In this work, the open-framework structure {[Cu₃(ptmtc)₂(py)₆(EtOH)₂(H₂O)]}, known as MOROF-1 (MOROF = metal-organic radical open-framework), is a 2D ferrimagnet (with T_c < 2 K). The Cu^{II} centres have a square pyramidal coordination geometry, each of them coordinated to two organic radicals, and each radical coordinated to three metal centres, thus yielding a two-dimensional structure with hexagonal nanopores of dimensions 2.8 x 3.1 nm², as shown in Figure 14. Interestingly, this MOF undergoes a reversible and highly selective solvent-induced ‘shrinking–

breathing' process involving large volume changes (25–35 %) that strongly influences the magnetic properties of the material. Specifically, the desolvation process involving the loss of the coordinated and non-coordinated solvent molecules converts the crystalline ferrimagnet into an amorphous paramagnet. The same ligand has also been combined with lanthanoid centers, but in this case the lanthanoid-radical magnetic exchanges were weakly ferromagnetic.^{53,54}

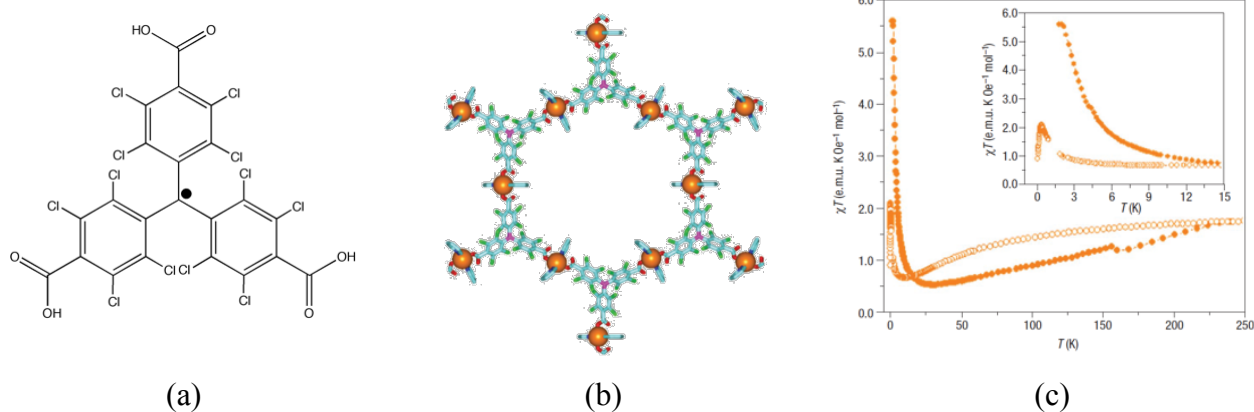


Figure 14. a) Schematic representation of the ptmtc radical ligand; b) Structure of $\{[\text{Cu}_3(\text{ptmtc})_2(\text{py})_6(\text{EtOH})_2(\text{H}_2\text{O})]\}$ showing the open-framework; c) Value of χT as a function of the temperature for MOROF-1 (orange filled circle, MOROF-1; open circle, evacuated MOROF-1). Adapted from reference 52, with permission from the Nature Publishing Group.

A ubiquitous organic radical in the field of functional molecular materials is the radical anion tetracyanoquinodimethane ($\text{TCNQ}^{\cdot-}$), as well as the related tetracyanoethylene ($\text{TCNE}^{\cdot-}$). Through the use of TCNQ and TCNE as building units of MOFs, the functional properties of these non-innocent ligands can be exploited to develop charge transfer frameworks which may exhibit electric conductivity as well as interesting magnetic properties, although the formation of non-porous coordination polymers is rather common. Remarkably, the compound $[\{\text{Ru}_2(\text{O}_2\text{CPh-o-Cl})_4\}_2\text{TCNQ}(\text{MeO})_2] \cdot \text{CH}_2\text{Cl}_2$ ($\text{o-ClPhCO}_2^- = \text{o-chlorobenzoate}$; $\text{TCNQ}(\text{MeO})_2 = 2,5\text{-dimethoxy-7,7,8,8-tetracyanoquinodimethane}$), reported by Miyasaka and co-workers, consists of two-dimensional layers where Ru_2 paddlewheels are linked through the TCNQ ligands, yielding an antiferromagnetic ordering at $T_N = 75 \text{ K}$ (Figure 15). Interstitial CH_2Cl_2 molecules are located in the void spaces between the layers, which can be lost at room temperature to form a dried sample, which orders ferromagnetically at $T_C = 56 \text{ K}$.⁵⁵ This process is reversible upon exposure to CH_2Cl_2 vapors for 72 h. The magnetic change occurs as a result of slight structural modifications caused by the ordering/disordering of ligand orientation upon the extrusion of the CH_2Cl_2 molecules.

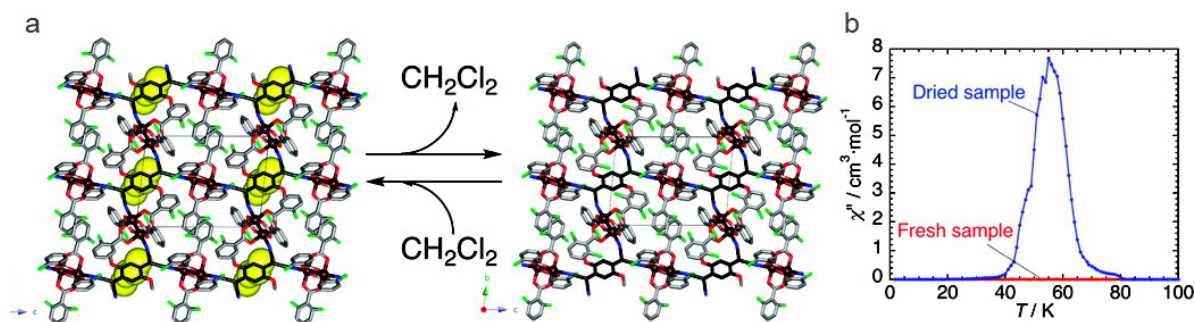


Figure 15. a) Reversible CH_2Cl_2 extrusion/uptake in $[\{\text{Ru}_2(\text{O}_2\text{CPh}-\text{o}-\text{Cl})_4\}_2\text{TCNQ}(\text{MeO})_2]\cdot\text{CH}_2\text{Cl}_2$ provokes subtle changes that affect the pendant ligand (the CH_2Cl_2 molecules are represented by a yellow CPK model); b) effects of the desolvation in the magnetic properties of the Ru coordination polymer: variation of 1 Hz ac susceptibilities χ'' (zero dc field and 3 Oe ac oscillating field) of the solvated and desolvated compounds. Reprinted with permission from reference 55, Copyright 2010 American Chemical Society.

The radical derived from chloranilic acid, 2,5-dichloro-3,6-dihydroxy-1,4-benzoquinone (Cl_2dhbq), has been combined with Fe^{III} yielding a crystalline solid of formula $(\text{Me}_2\text{NH}_2)_2[\text{Fe}_2(\text{Cl}_2\text{dhbq})_3]\cdot 2\text{H}_2\text{O}\cdot 6\text{DMF}$, where the iron centres are bridged by the radical form of the chloranilic acid forming two-dimensional honeycomb-like anionic layers, with Me_2NH_2^+ serving as counteranions (Figure 16).⁵⁶ The one-dimensional hexagonal channels are filled with solvent molecules, but these can be removed upon activation with a slight structural distortion of the framework, yielding a microporous solid with a surface area of $885\text{ m}^2/\text{g}$. Magnetic susceptibility measurements indicate the presence strong magnetic coupling at room temperature, with spontaneous magnetization occurring below $T = 100\text{ K}$, which is reduced to 30 K upon activation of the material. The ordering temperatures of both solvated and unsolvated MOFs have been accurately determined by AC susceptibility, revealing $T_c = 80\text{ K}$ and $T_c = 26\text{ K}$, respectively.

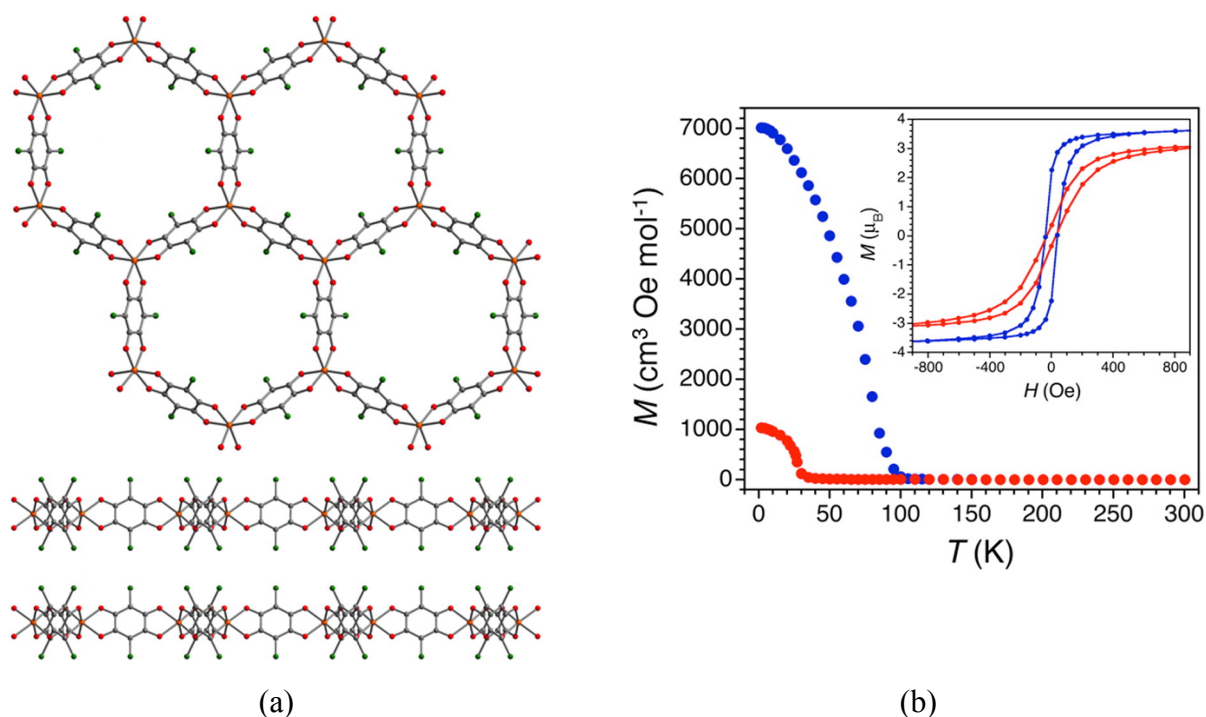


Figure 16. a) X-ray crystal structure of $(\text{Me}_2\text{NH}_2)_2[\text{Fe}_2(\text{Cl}_2\text{dhbq})_3] \cdot 2\text{H}_2\text{O} \cdot 6\text{DMF}$ (cations and solvent molecules omitted for clarity) viewed along the crystallographic c axis (top) and b axis (bottom). Orange = Fe, green = Cl, red = O, and grey = C. b) Thermal dependence of the field-cooled magnetization for as-synthesized $(\text{Me}_2\text{NH}_2)_2[\text{Fe}_2(\text{Cl}_2\text{dhbq})_3] \cdot 2\text{H}_2\text{O} \cdot 6\text{DMF}$ (blue) and activated $(\text{Me}_2\text{NH}_2)_2[\text{Fe}_2(\text{Cl}_2\text{dhbq})_3]$ (red), collected under an applied dc field of 10 Oe. Inset: Field dependence of the magnetization for $(\text{Me}_2\text{NH}_2)_2[\text{Fe}_2(\text{Cl}_2\text{dhbq})_3] \cdot 2\text{H}_2\text{O} \cdot 6\text{DMF}$ at 60 K (blue) and $(\text{Me}_2\text{NH}_2)_2[\text{Fe}_2(\text{Cl}_2\text{dhbq})_3]$ at 10 K (red). Reprinted with permission from reference 56, Copyright 2015 American Chemical Society.

To summarize this section, the different approaches investigated so far for the formation of porous magnets have both advantages and disadvantages. For example, the use of short linkers permits a large magnetic coupling between the metal centres, but limits the possibility of porosity, whereas the combination with other larger units that provide porosity reduces the dimensionality of the framework (from a magnetic point of view) thus resulting in low T_c values. In a different approach, the use of radical ligands seems to be more attractive, as the coupling is favoured even with large distances between the metallic nodes, but the highest limitation resides in their stability. Finally, the use of metallo-ligands seems to be the most convenient approach for the preparation of magnetic MOFs with high T_c , although there is a limited number of metallo-ligands capable of promoting magnetic exchange.

2.2. Spin-crossover MOFs

Spin-crossover (SCO) is a phenomenon in which electronic configurations of a transition metal ion can be switched between high-spin (HS) and low-spin (LS) states in response to external stimuli (temperature, pressure, light irradiation, magnetic field, electric field, guest sorption), producing changes in magnetism, colour and structure.^{57,58} Therefore, due to its molecular origin, no exchange interactions between neighbouring magnetic centres is required, and it is only necessary to design a MOF with first row transition metals in a suitable coordination environment that provides an appropriate ligand field for the transition between the HS and the LS states. Thus, there is no limitation on the length of the ligands, nor the connectivity between the metal centres, which in principle should facilitate the inclusion of this magnetic property in MOFs. However, cooperative effects are still necessary to make this phenomenon useful in order to have an abrupt crossover, and this arises from the elastic forces present in the solid. In these systems, such a cooperativity is favoured by the polymeric nature of the framework, which keeps the spin-crossover centers connected even if they are not very close. Thanks to this cooperativity this type of MOFs does show high sensitivity to the subtle structural changes occurring in metal coordination environments upon inclusion of guest species within the porous framework. Thus, from a multifunctional point of view, one can classify this material as a two-network material in which one network is composed by the framework itself, whereas the second network is provided by the guest molecules. As a consequence, one would expect a weak influence of the molecular network (guests) over the framework. This effect can be strongly enhanced by diminishing the size of the pore, as will be discussed in this section, in which physisorption of gases can even affect the temperature of the spin transition. Moreover, we will focus on unusual MOFs in which the spin-crossover properties is tuned via post-synthetic modification of the framework. The effects of guests and small molecules in SCO-MOFs have been recently reviewed by Ohtani and Hayami,⁵⁹ and therefore will not be analysed here.

a) Physisorption of gases. Although spin-crossover and gas sorption can co-exist in the same material,^{60,61} adsorbed gas molecules do not appreciably interact with the magnetic host network. Thus, in most cases they cause no effects on the spin transition temperature, which remains unaltered upon gas sorption. The first report of the use of gas sorption to modify the transition temperature of a spin-crossover coordination polymer has been reported by our group through the use of discrete compartments that confine the gas molecules and therefore force an enhanced interaction with the framework.^{62,63} Despite the lack of permanent channels, the non-porous coordination polymers $[\text{Fe}(\text{btzx})_3](\text{ClO}_4)_2$ and $[\text{Fe}(\text{btzx})_3](\text{BF}_4)_2$, denoted as **CCP-1** and **CCP-2**

(CCP stands for Compartmentalized Coordination Polymer) are able to allocate circa a single molecule of CO₂, CH₄, C₂H₄ or C₂H₂ in each void of the structures at 298 K and 1 bar, as unequivocally demonstrated by gas sorption isotherms and structural determination after gas loading (Figure 17). These gases affect differently the spin transition depending on the strength of the interaction. Thus, whereas loading of CO₂ gas molecules onto **CCP-1** and **CCP-2** induces an increase of 5 K of the T_{1/2} in both systems, sorption of ethylene causes the opposite response from the framework, i.e. a small reduction in the transition temperature, and sorption of methane, ethane and CO do not affect the transition temperature. This different behavior is related to the gas-framework interaction, which is stronger for the CO₂. Although the effect of the gas sorption on T_{1/2} in this system is rather limited compared to the inclusion of solvent molecules in other SCO MOFs (5 K vs. 50 K), it should be noted that the interaction of gas molecules with the framework is typically so weak that no effect on T_{1/2} had been previously observed.

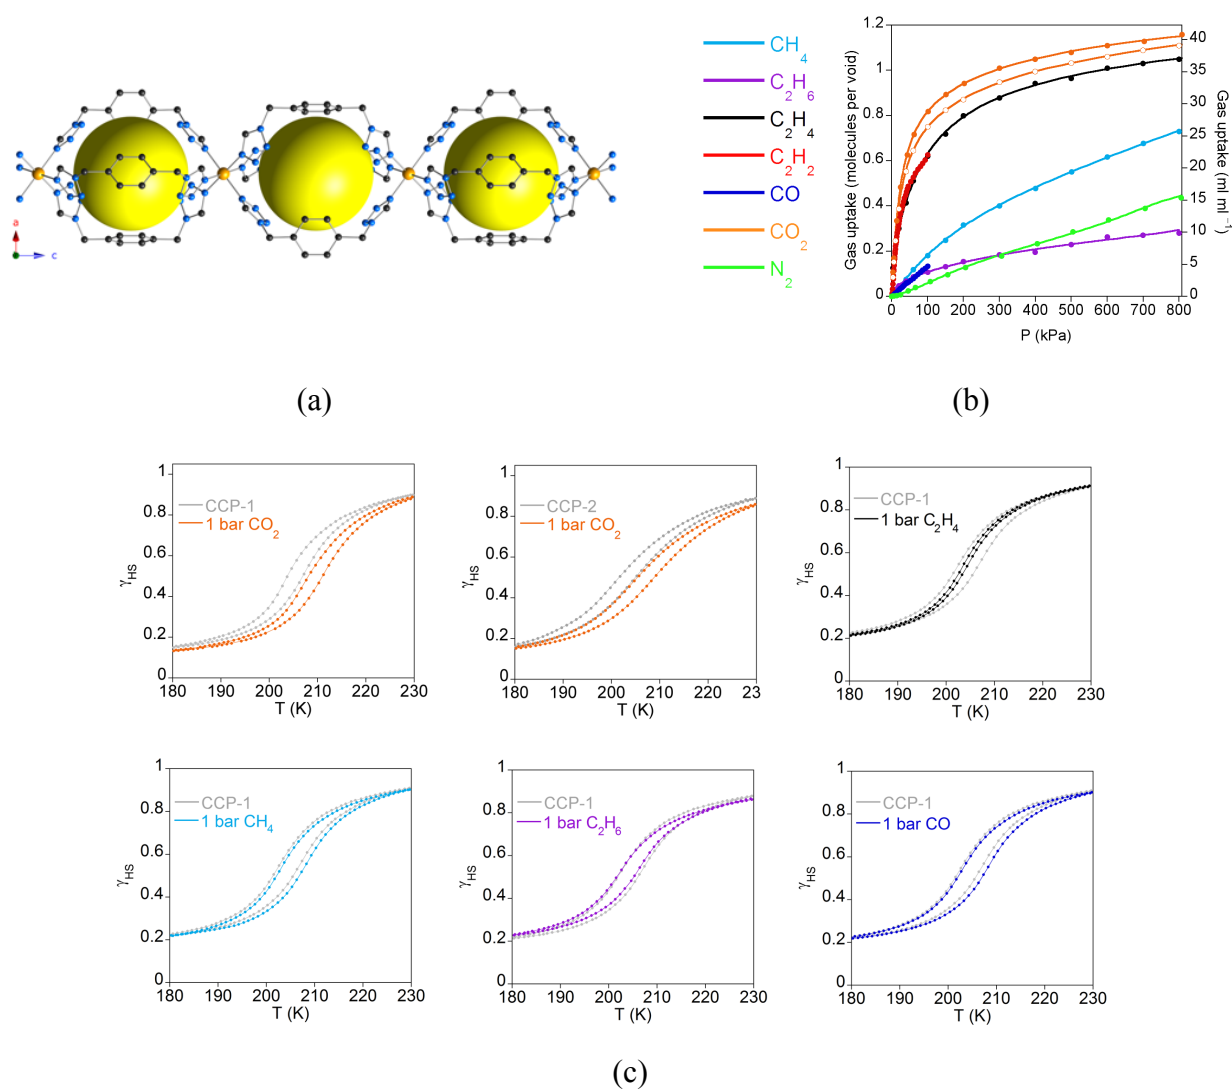


Figure 17. a) Crystal structure of the compartmentalized coordination polymers **CCP-1** and **CCP-2**

emphasizing the internal cavities (as yellow spheres) formed by the connection of Fe^{II} centres to three bistetrazol-*p*-xylene ligands in *syn* conformation. Key: Fe, orange; C, gray; N, blue; H, white; counteranions (ClO₄⁻ and BF₄⁻) omitted for clarity; b) Gas adsorption isotherms at 298 K of **CCP-1** (closed symbols) and **CCP-2** (open symbols) of different gases (lines correspond to the best fits); c) Temperature dependence of the high spin fraction (γ_{HS}) for **CCP-1** and **CCP-2** before (grey) and after inclusion CO₂ (orange), ethylene (black), methane (sky blue), ethane (purple) and CO (dark blue). Adapted from reference 63, with permission from The Royal Society of Chemistry.

The increase of the size of the internal voids has also been examined by extending the length of the flexible organic ligand with the purpose of augmenting the gas sorption capacity (Figure 18).⁶⁴ Through this ligand design, isostructural analogues of these compartmentalized coordination polymers have been prepared, with formula [Fe(btzbp)₃](ClO₄)₂ (**CCP-3**) and [Fe(btzbp)₃](BF₄)₂ (**CCP-4**) (btzbp = 4,4'-bis((1H-tetrazol-1-yl)methyl)-1,1'-biphenyl), which present discrete voids of 257 Å³. Gas sorption measurements show that two molecules of CO₂ can be loaded in each void at 1 bar and 298 K. Both compounds present spin transition centred at 195 and 199 K respectively, similar to the observed in **CCP-1** and **CCP-2**, although different magnetic behaviour has been observed for **CCP-3** and **CCP-4** depending on the number of CO₂ molecules that are physisorbed. Upon inclusion of one molecule of CO₂ in each internal void, a shift of T_{1/2} from 199 K to 206 K has been observed (Figure 19). Thus, physisorption of CO₂ stabilizes the LS state due to the interaction between CO₂ and the cationic framework. However, upon additional CO₂ loading (two molecules in each void), a reduction of T_{1/2} occurs, reaching 202 K. This behaviour could be caused by gas-gas interaction inside the void of the compartmentalized coordination polymer.

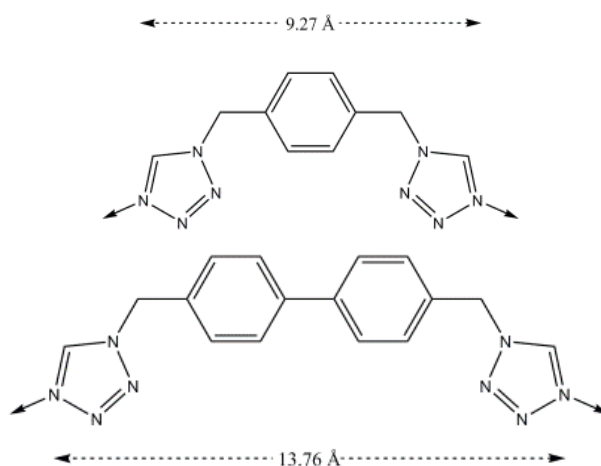


Figure 18. Chemical structures of the ligands btzx (top) and btzbp (bottom). The dashed arrows

represent the distances between the two coordinating nitrogens.

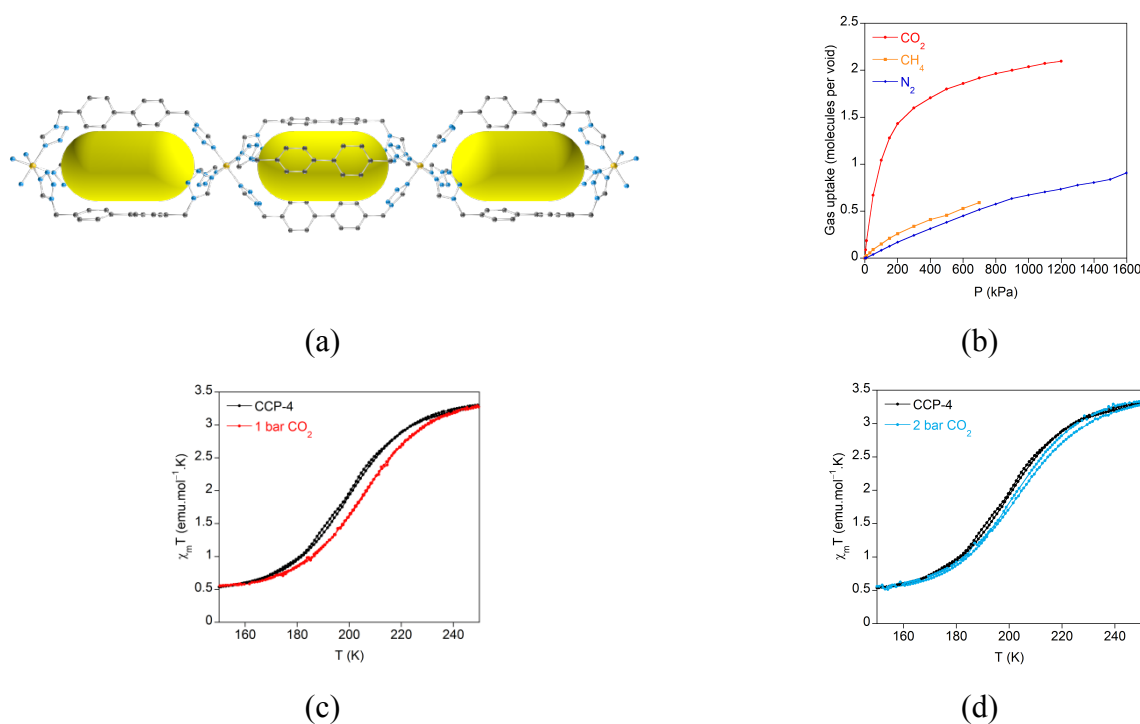


Figure 19. a) Crystal structure of **CCP-4** viewed along the *b*-axis. The BF_4^- anions and hydrogen atoms have been removed for clarity. Key: Fe, orange; C, gray; N, blue. The yellow ellipsoids are placed in the structure to represent the empty space of the internal voids; b) Gas sorption isotherms at 298 K for CO_2 , CH_4 and N_2 for **CCP-4**; c) Temperature dependence product of the magnetic susceptibility times the temperature ($\chi_m T$) for activated **CCP-4** (black) and **CCP-4** loaded with one molecule of CO_2 in each void (red line). d) Temperature dependence product of the magnetic susceptibility times the temperature ($\chi_m T$) for activated **CCP-4** (black) and **CCP-4** loaded with two molecules of CO_2 in each void (blue line). Adapted from reference 64, with permission from The Royal Society of Chemistry.

Another important family of SCO MOFs able to trap molecules is the so-called Hoffmann clathrates. This family has been extensively studied for the co-existence of SCO phenomena and porosity along 1D channels where different guests can be incorporated affecting the transition temperature.⁶⁵ More recently, it has also been demonstrated that adsorption of SO_2 molecules can modify the SCO properties.⁶⁶ Adsorption isotherm at 293 K displays a type I behaviour featuring a sharp SO_2 uptake at low pressures (below 50 mbar) and practically reaches saturation at 0.20 bar, which corresponds to ca. 1.3 equivalents of SO_2 . However, this sorption is not completely

reversible, and after vacuuming for 4 h at 258 K, ca. 0.5 equivalents of SO₂ remain trapped in the pores. The sorbed SO₂ molecules coordinate the Pt^{II} centres through the sulfur atom (Figure 20), stabilizing the low spin state of the Fe^{II} ions and causing an increase of 8 K in the transition temperature.

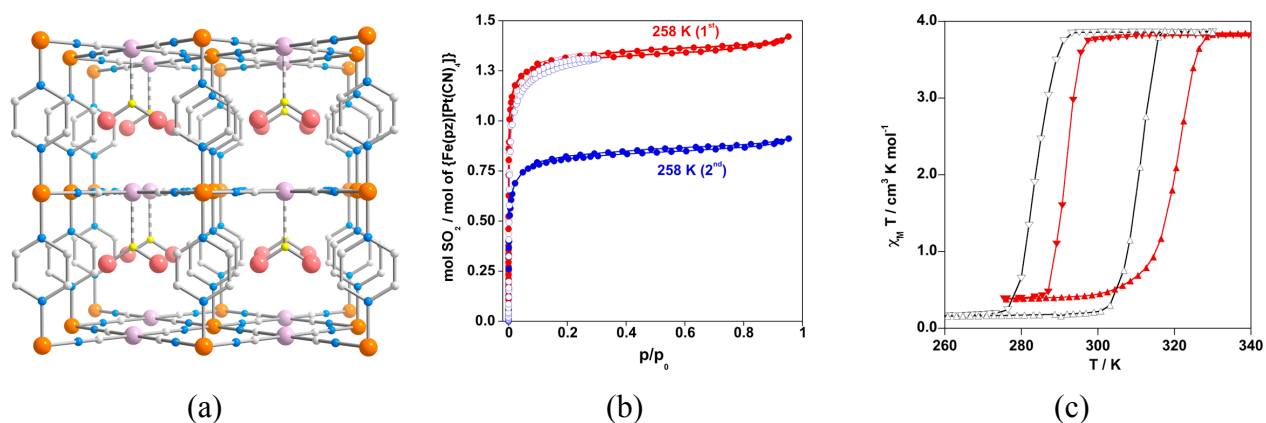


Figure 20. a) Fragment of the structure of {Fe(pz)[Pt^{II}(CN)₄]}·SO₂. Colour code: Fe (orange), Pt (light pink), S (yellow), N (blue), C (grey). b) SO₂ sorption–desorption isotherms for {Fe(pz)[Pt^{II}(CN)₄]} at 293 K (○) and at 258 K (●). Red and blue colour codes refer to the first and second sorption–desorption cycles, respectively. c) Magnetic properties of {Fe(pz)[Pt^{II}(CN)₄]} (black line) and {Fe(pz)[Pt^{II}(CN)₄]}·SO₂ (red line). Reprinted with permission from reference 66, Copyright 2013 American Chemical Society.

b) Chemisorption / post-synthetic modification. An interesting opportunity that arises with the synthesis of Hofmann chltrates with Pt open metal sites is the possibility of tuning the transition temperature by oxidative addition of halogens. Thus, upon exposure of {Fe(pz)[Pt(CN)₄]} to dihalogens, an associative oxidation of Pt^{II} to Pt^{IV} occurs with a reduction of the dihalogen to the corresponding halide resulting in the formation of {Fe(pz)[Pt(CN)₄(X)_p]} [X=Cl⁻ (p=1), Br⁻ (p=1), I⁻ (0<p<1)], shown in Figure 21.^{67,68} This oxidative addition to the Pt centres modifies the σ-donor capability of the nitrogen atom of the Pt–CN group, causing a decrease of T_{1/2} that depends on the electronegativity of X.

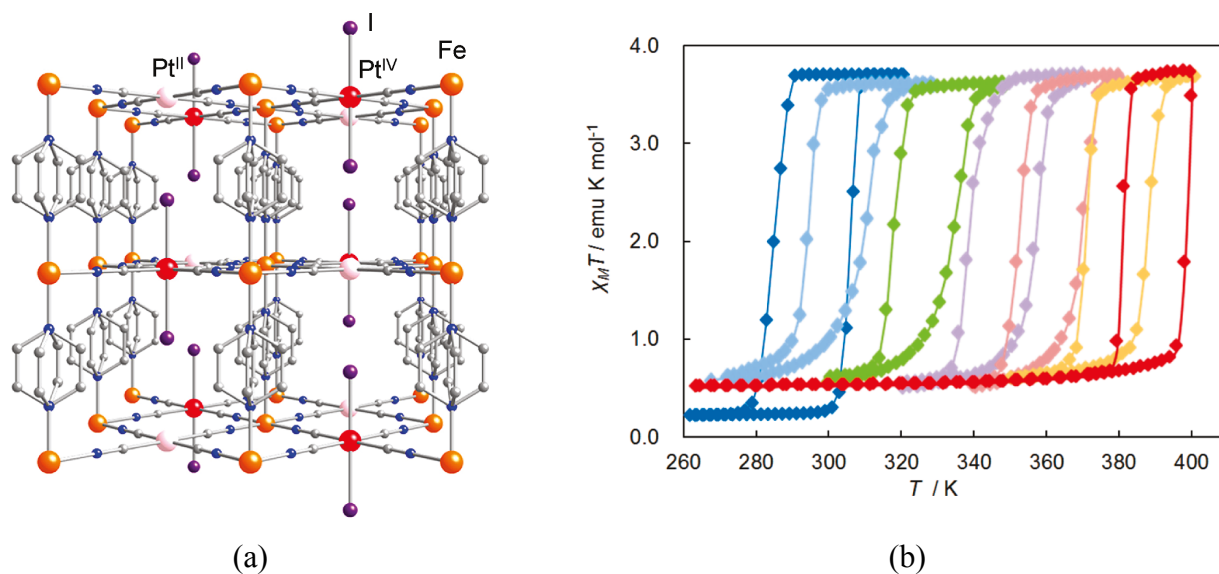


Figure 21. a) Crystal structure of $\{\text{Fe}(\text{pz})[\text{Pt}^{\text{II/IV}}(\text{CN})_4(\text{I})]\}$. Atoms: Fe (orange), Pt^{II} (pink), Pt^{IV} (red), I (purple), C (gray), N (blue). b) Magnetic behavior of $\{\text{Fe}(\text{pz})[\text{Pt}(\text{CN})_4(\text{I})_n]\}$ $n = 0.0$ (blue); 0.1 (sky blue); 0.3 (green); 0.5 (violet); 0.7 (pink); 0.9 (orange); 1.0 (red). Reprinted with permission from reference 68, Copyright 2011 American Chemical Society.

A covalent post-synthetic modification of a SCO MOF has been reported by Kepert and co-workers in a Hoffmann clathrate of formula $[\text{Fe}(\text{bipytz})(\text{Au}(\text{CN})_2)_2]$ through the incorporation of an organic linker, 3,6-bis(4-pyridyl)-1,2,4,5-tetrazine (bipytz), that readily undergoes an inverse-electron-demand Diels–Alder reaction.⁶⁹ The octahedral Fe^{II} centers are bridged equatorially by four linear $[\text{Au}(\text{CN})_2]^-$ linkers forming a 2D layer which is further extended into 3D through bipytz units that serve as pillars (Figure 22). Upon this modification, the SCO behaviour differs from the pristine material in three ways: it is less abrupt; occurs at lower temperature ($T_{1/2} = 178$ K vs. $T_{1/2} = 275$ K); and does not show a thermal hysteretic behaviour.

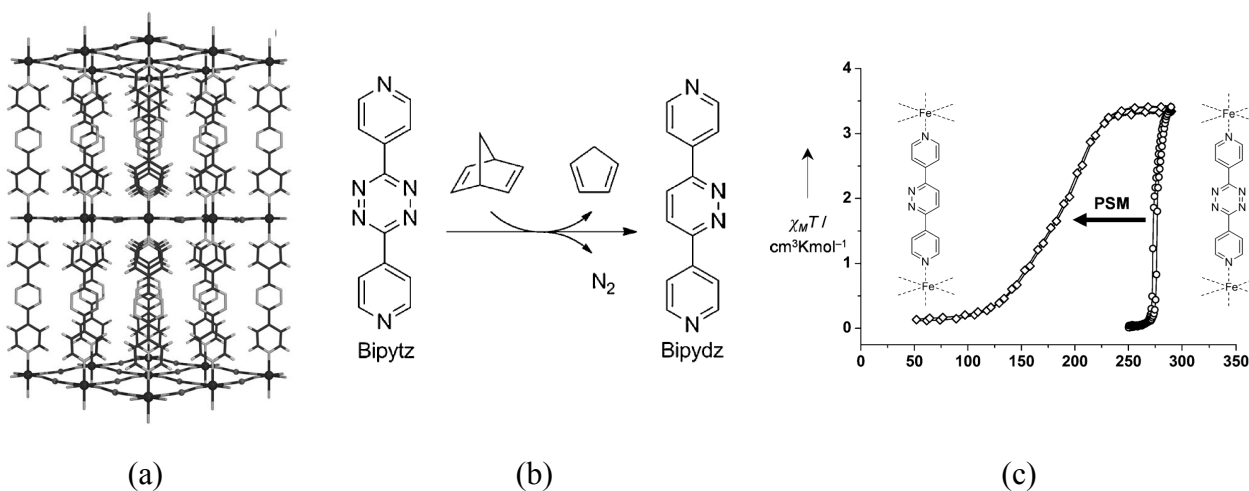


Figure 22. a) Structural representations of $[\text{Fe}(\text{bipytz})(\text{Au}(\text{CN})_2)_2]$ viewed down the b axis with solvent and interpenetration removed for clarity; b) Inverse-electron-demand Diels–Alder reaction of 3,6- bis(4-pyridyl)-1,2,4,5-tetrazine (bipytz) with 2,5-norbornadiene to form 3,6-bis(4-pyridyl)-1,2-diazine (bipydz); c) Magnetic susceptibility data for $[\text{Fe}(\text{bipytz})(\text{Au}(\text{CN})_2)_2]$ and post-synthetically modified $[\text{Fe}(\text{bipydz})(\text{Au}(\text{CN})_2)_2]$. Adapted from reference 69, with permission of John Wiley and Sons.

2.3. MOFs with single-molecule magnets at the inorganic nodes.

Single-Molecule Magnets are magnetic molecules that exhibit slow relaxation of the magnetization at low temperatures. Usually, they are formed by polynuclear magnetic clusters with a large spin value and high magnetic anisotropy. Recently, a second generation of SMMs based on mononuclear metal complexes composed by highly anisotropic magnetic ions has been reported, which are simpler to design from a chemical point of view. This last class of SMM have additional interest in quantum technologies, as they can provide ideal examples of quantum bits (qubits), which are the basic units in quantum computing. Since the ground state of these molecules is a spin doublet, it can be seen as a spin qubit, as far as its quantum coherence is large enough to have time to perform a quantum operation. One important requirement for maximizing the quantum coherence is to minimize the magnetic dipolar interactions between qubits, which can be achieved by separating in the space these magnetic units. In this sense, MOF can be ideal platforms to reach this goal since they provide spatial separation at will.

The linkage of single-molecule magnets based on polynuclear cluster-type metal complexes by bridging organic ligands has been exploited in the past for the isolation of crystalline coordination polymers.⁷⁰ This approach has been useful to investigate the interplay between the single-molecule magnetic behaviour and the new (cooperative) properties that may appear when these molecular nanomagnets are magnetically coupled. Still, this has most commonly resulted in the preparation of systems with lower dimensionality, chains being the most common.⁷¹ The first 3D coordination network of SMMs was prepared by Clérac and co-workers using Mn_4 clusters as nodes.⁷² In these networks, subtle modifications in the synthetic strategies influence enormously and unpredictably the dimensionality of the network,⁷³ and in some other cases the formation of the extended system causes a quenching in the magnet-like properties of the metal clusters.⁷⁴ Although these solids typically lack permanent porosity, Kou and co-workers have recently reported the combination of porosity and SMM behaviour in a MOF based on Mn_6 clusters.⁷⁵

With the recent discovery of the second generation of single-molecule magnets, i.e. the so-called single-ion magnets, or SIMs, new coordination polymers based on these mononuclear

lanthanoid complexes have been isolated. These SIMs are easier to assemble than the cluster-type SMMs and therefore they can allow to circumvent the problems observed for the preparation of SMM-MOFs. The first family of SIM-MOF has been recently reported.⁷⁶ It can be formulated as $\text{Ln}(\text{bipyNO})_4(\text{TfO})_3$ (bipyNO = 4,4'-bipyridyl-N,N'-dioxide, TfO = triflate). Its structure consists of a 3D coordination network containing lanthanoid SIMs in the nodes of a porous cationic framework formed by the long bipyNO as bridging ligand (Figure 23). The pores of this framework are filled by triflate anions. Interestingly, this family shows the capability of exchanging the anions placed in its pores, while maintaining the magnetic behaviour. This feature has been exploited to incorporate in the pores bulky anions such as polyoxometalates (POMs) and other smaller anions such as $[\text{AuCl}_4]^-$ by post-synthetic modification of the magnetic MOF (Figure 24). In these cases, the anion exchange process has occurred in a single-crystal-to-single-crystal manner thus providing structural evidence of the location of the encapsulated species.⁷⁷ The interest of these SIM-MOFs is twofold. On one hand, the controlled organization of the SIMs is an important issue for their possible application in quantum computing since each SIM can behave as a quantum bit. Indeed, the ability to tune the spatial arrangement of more than one non-identical SIM qubit (in the present example three structurally distinguishable SIMs are present) is precisely what is currently needed to advance in the global control paradigm of quantum computing.⁷⁸ On the other hand, the incorporation in the pores of functional molecular species can provide a convenient way for introducing a second property in these hybrid materials. After this first report on the preparation of a SIM-MOF, many other examples have been reported based either on lanthanoids,^{79,80,81} or in transition metals.⁸² A very remarkable result in this context has been recently reported by Freedman and co-workers⁸³ with the demonstration of atomic clock-like transitions in the MOF of formula $[(\text{TCCP})\text{Co}_{0.07}\text{Zn}_{0.93}]_3[\text{Zr}_6\text{O}_4(\text{OH})_4(\text{H}_2\text{O})_6]_2$ (TCCP = 5,10,15,20-tetrakis(carboxyphenyl)porphyrin), where the cobalt(II) porphyrin units, diluted within a diamagnetic network, possess lifetimes of 13.7 μs at 5 K (1.8 μs at 15 K), observed with pulsed EPR spectroscopy, which is a modest improvement over the 8.4 μs obtained in the POM $[\text{Ho}(\text{W}_5\text{O}_{18})_2]^{9-}$.⁸⁴

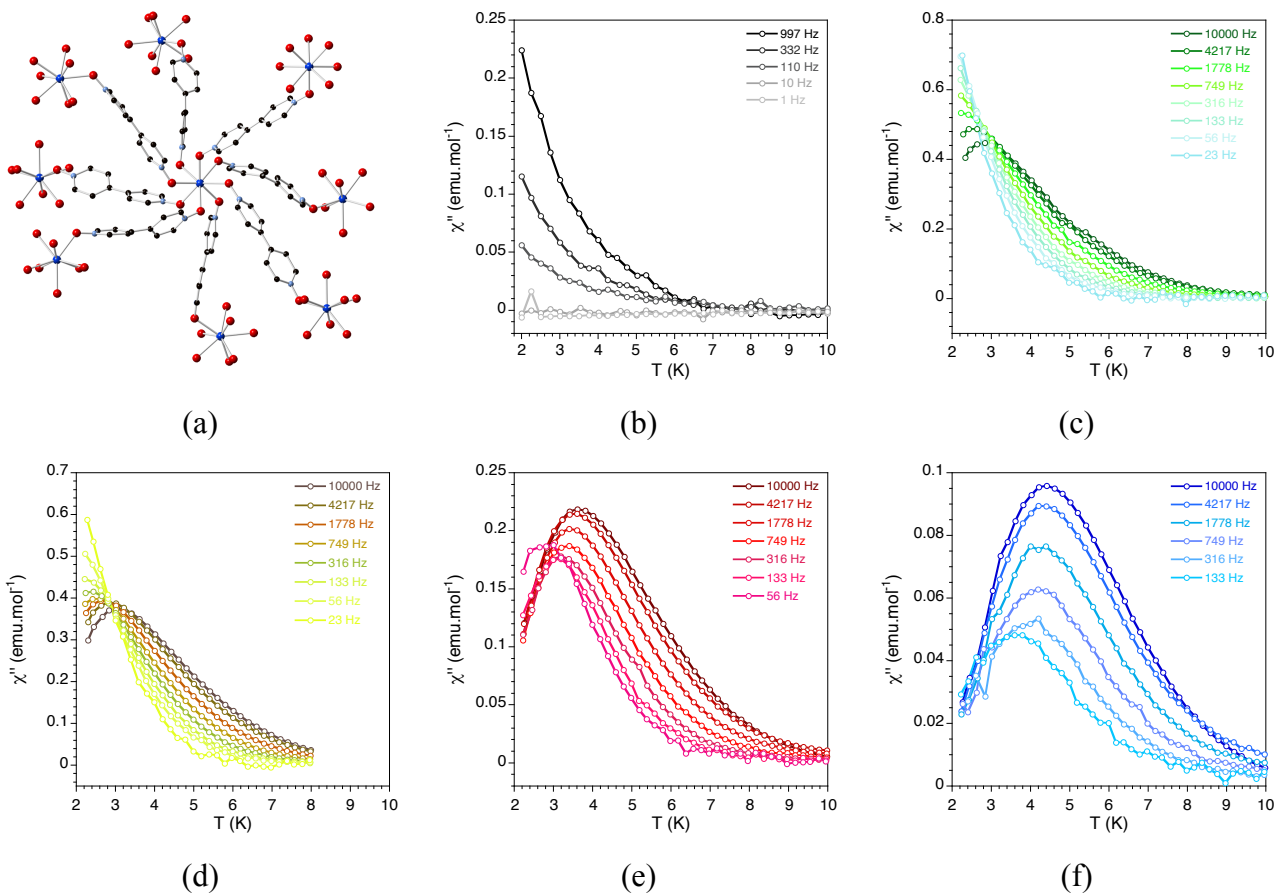
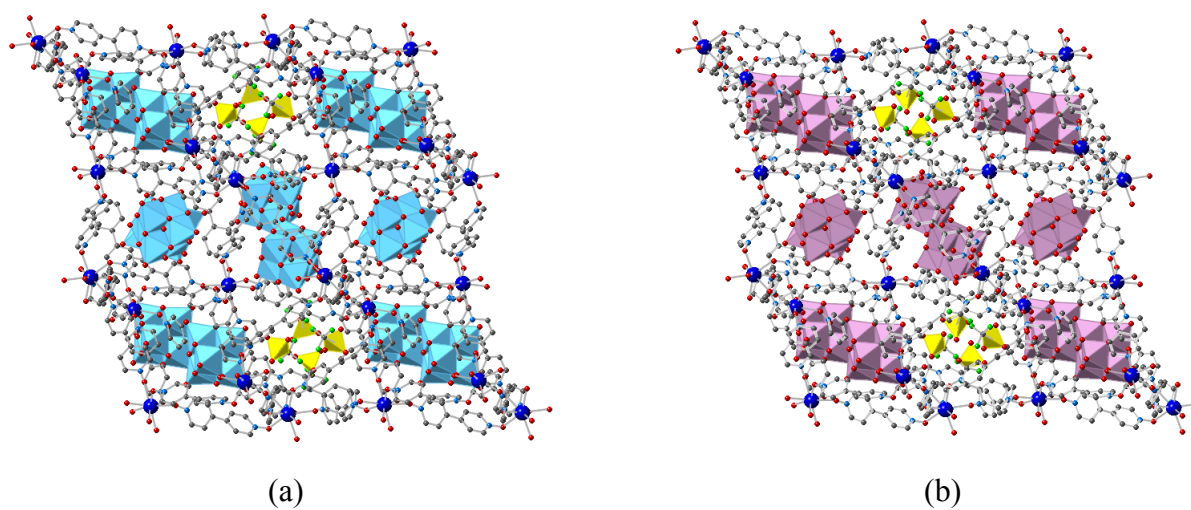


Figure 23. a) Crystal structure of $\text{Ln}(\text{bipyNO})_4(\text{TfO})_3$. Out-of-phase dynamic susceptibility under different external dc magnetic fields: b) 4 G; c) 1000 G; d) 2000 G; e) 5000 G; and f) 10000 G. Solid lines are eye-guides. Adapted from reference 76, with permission of John Wiley and Sons.



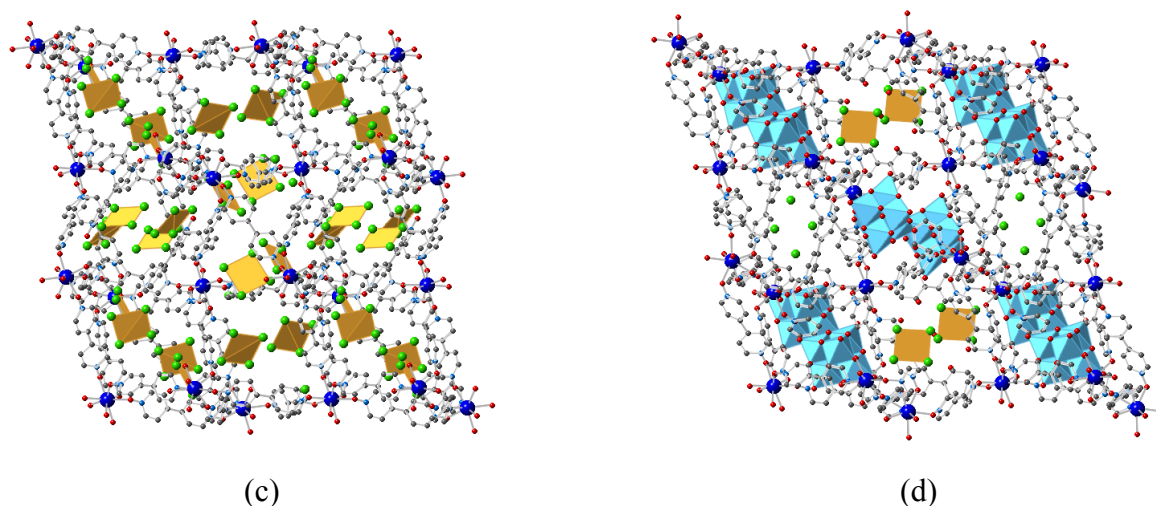


Figure 24. Crystal structures after anion exchange in $\text{Ln}(\text{bipyNO})_4(\text{TfO})_3$ with different anions: a) $[\text{W}_6\text{O}_{19}]^{2-}$; b) $[\text{Mo}_6\text{O}_{19}]^{2-}$; c) $[\text{AuCl}_4]^-$; and d) the mixed system $[\text{W}_6\text{O}_{19}]^{2-}$, and $[\text{AuCl}_4]^-$. $[\text{W}_6\text{O}_{19}]^{2-}$, $[\text{Mo}_6\text{O}_{19}]^{2-}$, $[\text{AuCl}_4]^-$ and Cl^- anions shown in blue, purple, orange and green, respectively.

2.4. MOFs for magnetic refrigeration.

A different magnetic phenomenon that is of high interest for cooling applications is that of magnetic refrigeration (Figure 25), which is based on the magnetocaloric effect (MCE). This effect is the consequence of a change in the magnetic entropy (ΔS_m) and related adiabatic temperature (ΔT_{ad}) in response to a change in the applied magnetic field (ΔB). Although the MCE is intrinsic to any magnetic material, only in a few cases the changes are sufficiently large to make them suitable for applications. In order to maximize the change in the magnetic entropy, the magnetic material should have a large spin ground state S (the maximum magnetic entropy amounts to $R\ln(2S+1)$), high spin degeneracy or low lying spin ground state, negligible magnetic anisotropy, and a high magnetic density. In this sense, gadolinium and manganese based molecular compounds have been largely studied because of their large spin-only magnetic moment ($S_{\text{Gd}} = 7/2$, $S_{\text{Mn}} = 5/2$) and quasi-isotropic character, showing great promise as low temperature magnetic refrigerants based on molecular clusters that can rival traditional materials such as lanthanide alloys and magnetic nanoparticles.



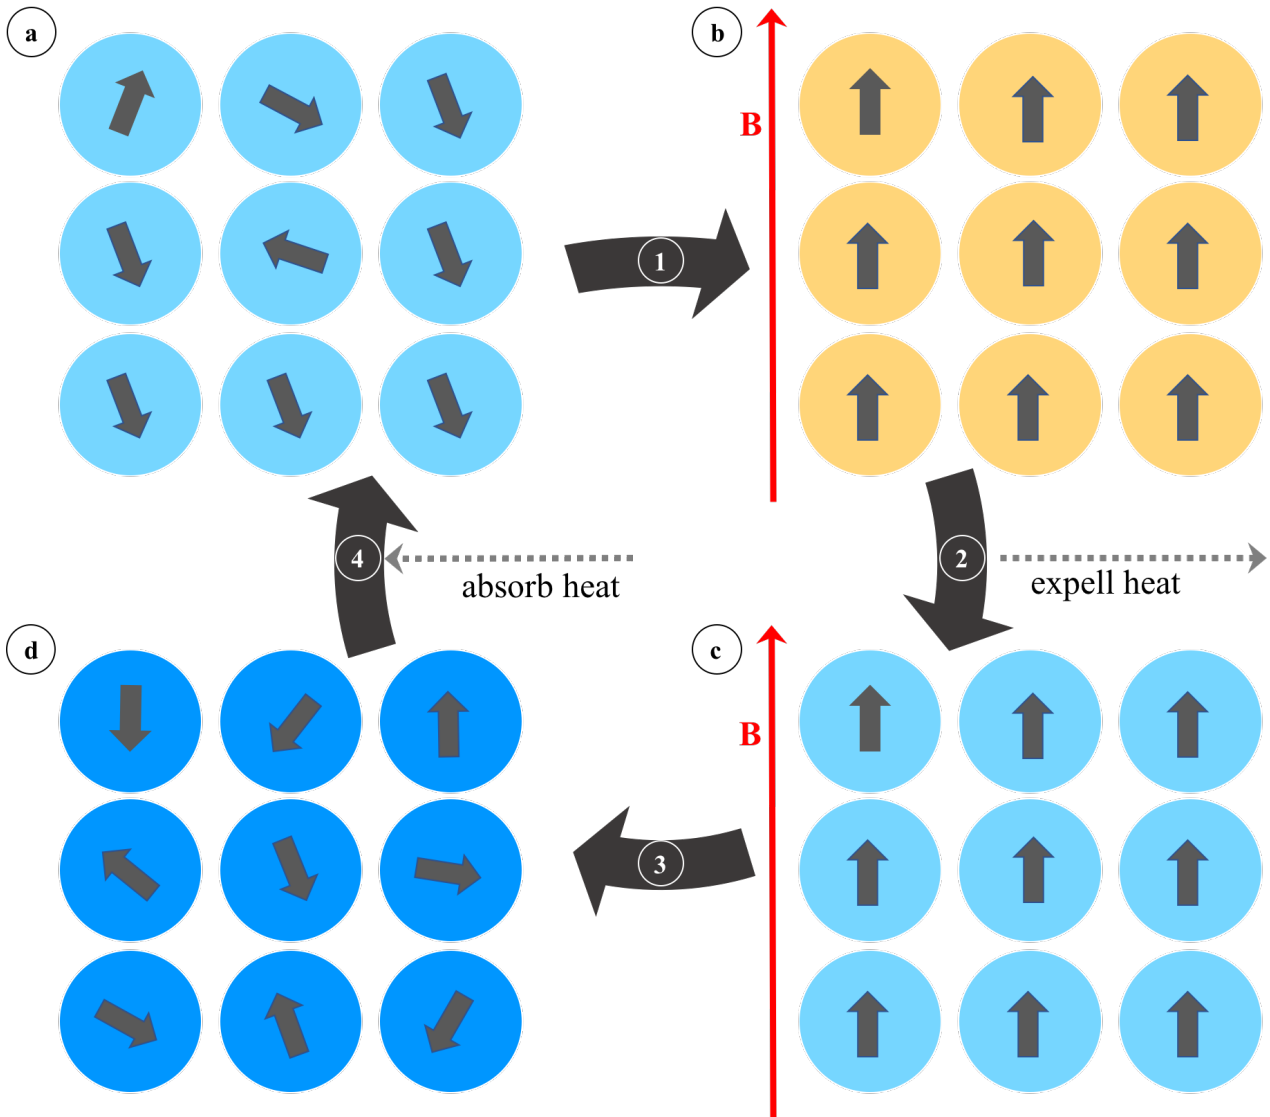


Figure 25. The magnetocaloric cooling cycle consists of four steps: 1) First, the magnetic material (part “a” of the figure) is exposed to a magnetic field, B (represented which a red arrow), resulting in a heating of the material (part “b” of the figure) as consequence of the reduction in the magnetic entropy; 2) The heat excess caused by the alignment of all the spins is expelled to the surroundings, thus yielding to the magnetic material at the same temperature as in the beginning, but with the spins aligned (part “c” of the figure); 3) The removal of the magnetic field causes a cooling of the refrigerant due to the increase of magnetic entropy caused by the spin relaxation (part “d” of the figure); 4) heat can be absorbed from the cooling compartment. The orange colour represents an increase in temperature of the magnetic material, and the dark blue colour represents a decrease in temperature of the magnetic material. The grey arrows represent the large spin of the magnetic material, whose orientation can be modified upon application of a magnetic field (represented as red arrows).

The use of magnetic MOFs is restricted to ultra-low temperature applications, whereas magnetic refrigerators near room temperature is dominated by lanthanoid-based alloys. In this context, the use of magnetic MOFs for magnetic refrigerators is very appealing since they can be designed to consist on isolated paramagnetic centers (i.e. with weak superexchange interactions) that favors a large MCE, combined with higher thermal and solvent stabilities than their discrete molecular cluster analogues. However, there are two important obstacles that should be taken into account: MOFs are typically poor thermal conductors (which is important to dissipate the heat), although their facile deposition on metallic surfaces can overcome this problem; and the density of magnetic centres is very low, which is a consequence of the presence of porosity.

There are numerous examples in the literature of the use of magnetic coordination polymers for MCE since the initial reports on Prussian blue analogues,^{85,86,87,88} which are mainly based on Gd or Mn centres for similar reasons to their interest on molecular clusters mentioned above. Most of these coordination polymers are dense materials, as [Gd(HCOO)(bdc)] (H₂bdc = terephthalic acid),⁸⁹ which present a higher density of magnetic centres. For example, this compound present values of $-\Delta S_m = 47.0 \text{ J}\cdot\text{kg}^{-1}\cdot\text{K}^{-1}$ for $\Delta B=9 \text{ T}$. In other cases, the materials present channels or voids which are filled with solvent molecules, as in Gd₂(fum)₃(H₂O)₄·3H₂O (with MCE values of $\Delta S_m = 20.7 \text{ J}\cdot\text{kg}^{-1}\cdot\text{K}^{-1}$ for $\Delta B=5\text{T}$),⁹⁰ but the sorption of gases has not been demonstrated. However, combination of porosity and MCE is very scarce, and has only been successfully combined in a couple of examples presented below.

The Gd-based MOF of formula [Gd₂(pam)₃(DMF)₂(H₂O)₂]_n·nDMF (H₂pam = pamoic acid) forms a 3D framework with channels of sizes of ca. 17 Å x 15 Å in which the organic ligands adopts different conformations (Figure 26).⁹¹ CO₂ sorption at 195 K shows an uptake of 8.4 wt % (43.5 cm³·g⁻¹). The MCE values are not very high, as expected for a porous system, with calculated values of $-\Delta S_m$, obtained through magnetization data, of $17.25 \text{ J}\cdot\text{kg}^{-1}\cdot\text{K}^{-1}$ at 3 K for $\Delta B = 7 \text{ T}$.

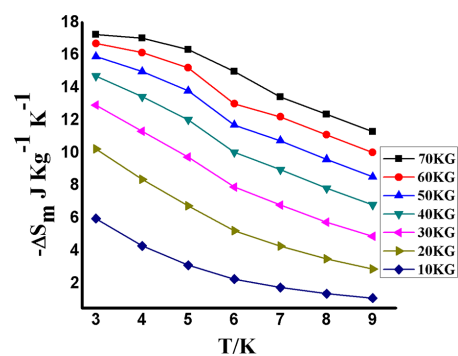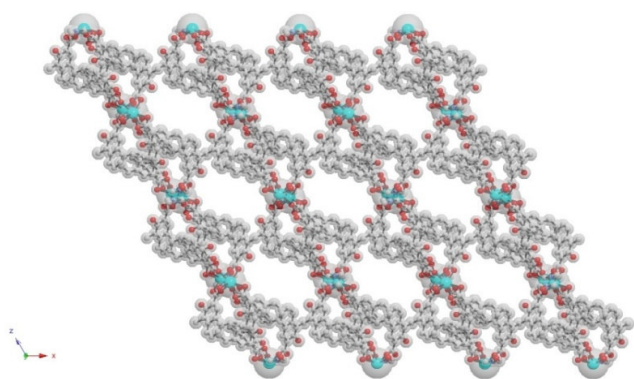

(a)

(b)

Figure 26. (a) Structural view of $[\text{Gd}_2(\text{pam})_3(\text{DMF})_2(\text{H}_2\text{O})_2]_n$; b) ΔS_m calculated by using the magnetization data at different fields and temperatures. Reprinted with permission from reference 91, Copyright 2014 American Chemical Society.

These low values of ΔS_m have been improved, in combination with porosity, by using lanthanoid clusters as nodes of MOFs. Specifically, two MOFs based on Ln_5 clusters, $\{[\text{Ln}_5\text{Zn}(\text{BPDC})_3\text{-H}_2\text{O}]_{10}(\mu_3\text{-OH})_6\}(\text{CO}_3)_{0.5}(\text{NO}_3)_4 \cdot m\text{H}_2\text{O}\}_n$ (BPDC=4,4'-dicarboxylate-2,2'-dipyridine anion; $\text{Ln}=\text{Gd}$, $m=12$; Dy , $m=10$) were investigated.⁹² These compounds are cationic heterometal–organic framework composed by $[\text{Ln}_5\text{Zn}(\text{BPDC})_3(\text{H}_2\text{O})_{10}(\text{OH})_6]^{5+}$ units, which are formed by pentanuclear clusters of formula $[\text{Ln}_5(\text{H}_2\text{O})_{10}(\text{OH})_6]^{9+}$ which are further linked by $[\text{Zn}(\text{BPDC})_3]^{4-}$ units, forming a three-dimensional structure with triangular channels with a diameter of ca. 5.2 Å along the *c* direction (Figure 27). The argon isotherm of the dehydrated Gd derivative shows an uptake of $38.79 \text{ cm}^3 \cdot \text{g}^{-1}$ at approximately 1 bar and 87 K, thus showing the presence of porosity. The MCE present maximum values of $-\Delta S_m$ of $30.7 \text{ J} \cdot \text{kg}^{-1} \cdot \text{K}^{-1}$ and $10.8 \text{ J} \cdot \text{kg}^{-1} \cdot \text{K}^{-1}$ for the Gd (at 3 K) and the Dy (at 4 K) derivatives, respectively (for $\Delta B=7 \text{ T}$), thus showing the successful combination of porosity with MCE effect.

To sum up, although some MOFs presenting MCE have been reported, the values are still far from those of the current state-of-the-art of other molecule-based materials. For example, the dense layered material $\text{Gd}_2(\text{OH})_5\text{Cl}_{1.5}\text{H}_2\text{O}$ has $-\Delta S_m$ of $51.9 \text{ J} \cdot \text{kg}^{-1} \cdot \text{K}^{-1}$ for $\Delta B=7 \text{ T}$.⁹³ The low values found in MOFs is a consequence of the intrinsic characteristics of these materials, in particular their low magnetic density. Thus, despite their high chemical stability, which is the major advantage of using MOFs for magnetic refrigeration, their real use is not very promising.

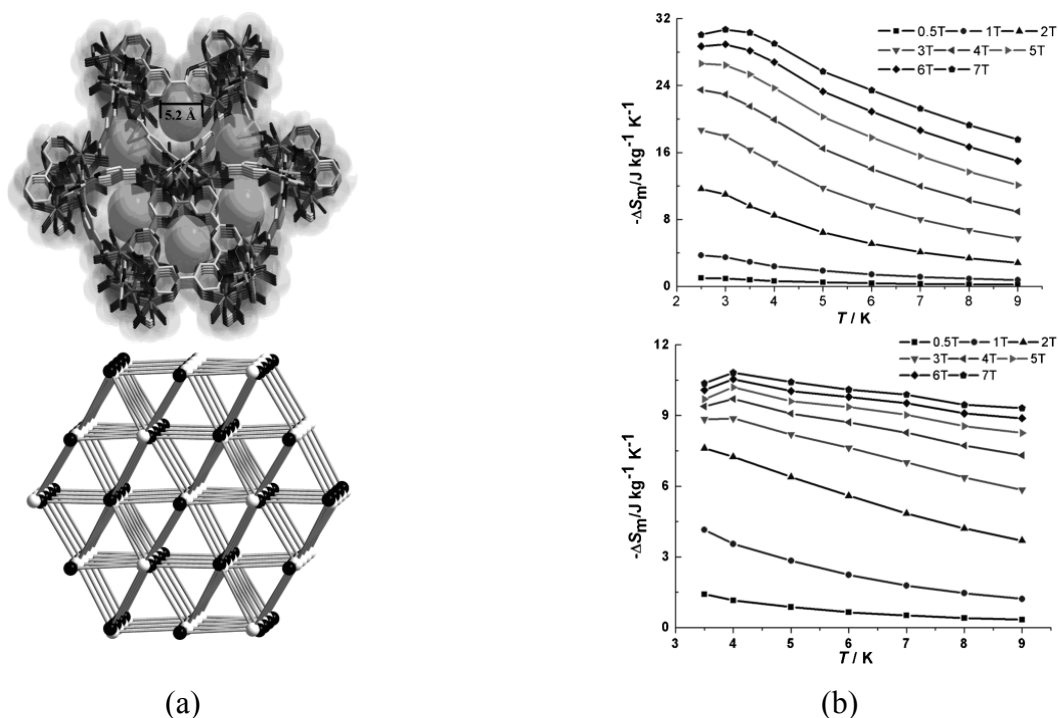


Figure 27. (a) 3D framework and channel along the *c* direction and schematic representation of the topology: black and white represent $[\text{Ln}_5(\text{H}_2\text{O})_{10}(\text{OH})_6]^{9+}$ clusters and $[\text{Zn}(\text{BPDC})_3]^{4-}$ units, respectively; b) Calculated ΔS_m for the pentanuclear-based MOFs (Gd derivative shown in top, Dy derivative shown in bottom) at various fields (1–7 T). Adapted from reference 92, with permission of John Wiley and Sons.

3. Hybrid MOFs incorporating functional molecules in the channels

The presence of a periodic array of empty channels in MOFs can structurally control the positioning of multiple functional guests. In this sense, porous materials capable of absorbing and orienting guest molecules through the use of networked cages have been recently developed as a new strategy for the structural determination of exotic molecules otherwise unachievable.⁹⁴ Furthermore, MOFs have also been exploited for the encapsulation of active species,⁹⁵ which can be as varied as chromophores,^{96,97,98} drugs,⁹⁹ CO releasing molecules,¹⁰⁰ catalysts,^{101,102,103,104,105} or nanoparticles.^{106,107,108} Using this hybrid approach two-network solids can be prepared constructed through the self-assembly of different molecular fragments (organic, inorganic, or organometallic) used as starting building blocks, or using a post-synthetic method in which a molecular guest is inserted into a pre-formed extended network acting as host lattice (Figure 28). As pointed out in the introduction, when the MOF is also functional this hybrid approach can afford the isolation of multifunctional materials (Figure 1c). In this section, we will focus on these multifunctional hybrids, in which each network furnishes the solid with distinct properties. As guest molecules we will show

the insertion of magnetic molecules (spin-crossover complexes and single-molecule magnets) and electro-active molecules (electron donors and acceptors).

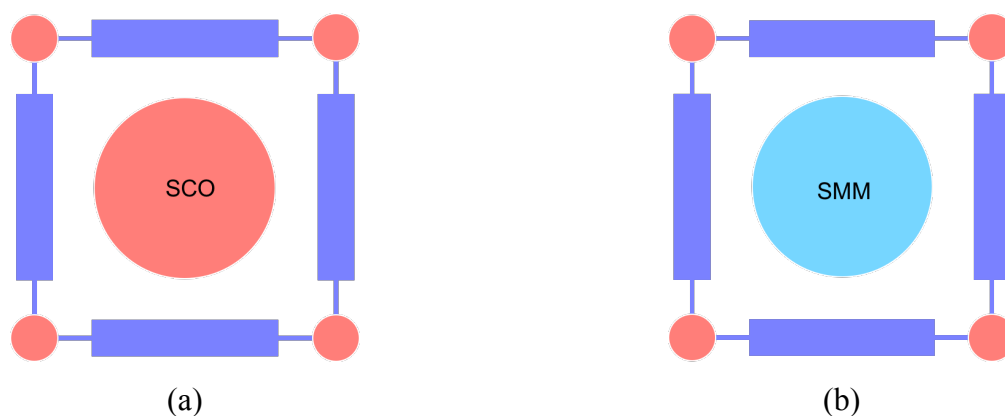


Figure 28. Schematic representation of different functional magnetic guest that can be incorporated in MOFs: (a) spin-crossover complexes, and (b) single-molecule magnets.

3.1. SCO @ MOFs.

Oxalate-based bimetallic coordination polymers of general formula $[M^{II}M^{III}(\text{ox})_3]^-$ are archetypical examples of 2D and 3D magnetic networks, which can host a wide variety of functional cations to give rise to hybrid materials exhibiting multifunctional properties. Our group has extensively exploited this feature to combine cooperative magnetism with other properties such as electrical conductivity, paramagnetism, single-molecule magnetism and spin crossover.¹⁰⁹ The synthetic approach to obtain these hybrid materials involves a self-assembly method that consists in growing the extended network from its molecular precursors, $[M^{III}(\text{ox})_3]^{3-}$ and $M^{2+}(\text{aq})$, in presence of the functional cations, which act as templates to stabilize the dimensionality of the network (2D or 3D). Using this method many examples of hybrid materials with coexistence of magnetic ordering and spin-crossover have been successfully prepared,¹¹⁰ as well as using diamagnetic frameworks.¹¹¹ The most interesting properties have been observed in the 2D compounds $[\text{Fe}^{III}(\text{sal}_2\text{-trien})][\text{Mn}^{II}\text{Cr}^{III}(\text{ox})_3]\cdot X$ ($X = \text{CHBr}_3, \text{CHCl}_3, \text{CH}_2\text{Br}_2$ and CH_2Cl_2) which, apart of ferromagnetism and spin-crossover, also exhibit a photo-induced spin transition (i.e., a light-induced excited spin trapping (LIEEST) effect).^{112,113}

Another approach that has also been successfully used to incorporate spin-crossover complexes within a magnetic MOF involves the so-called post-synthetic method (already pointed out in section 2.3). The first example has been obtained through a solid-state incorporation of the $[\text{Fe}^{III}(\text{sal}_2\text{-trien})]^+$ complex into the large pores (ca. 2.2 nm) of a $\text{Mn}^{II}\text{Cu}^{II}$ 3D MOF of formula $\text{Na}_4\{\text{Mn}_4[\text{Cu}_2(\text{Me}_3\text{pba})_2]_3\cdot 60\text{H}_2\text{O}$ (Figure 29).¹¹⁴ Interestingly, the magnetic properties of the

$\text{Mn}^{\text{II}}\text{Cu}^{\text{II}}$ MOF change upon insertion of the spin-crossover complex (the critical temperature increases from 14 to 19 K) as a consequence of the strengthening of the antiferromagnetic coupling $\text{Mn}^{\text{II}}\text{Cu}^{\text{II}}$, which is likely associated to the changes induced in the crystal lattice by the exchange of Na^+ cations with the $[\text{Fe}^{\text{III}}(\text{sal}_2\text{-trien})]^+$ complex.

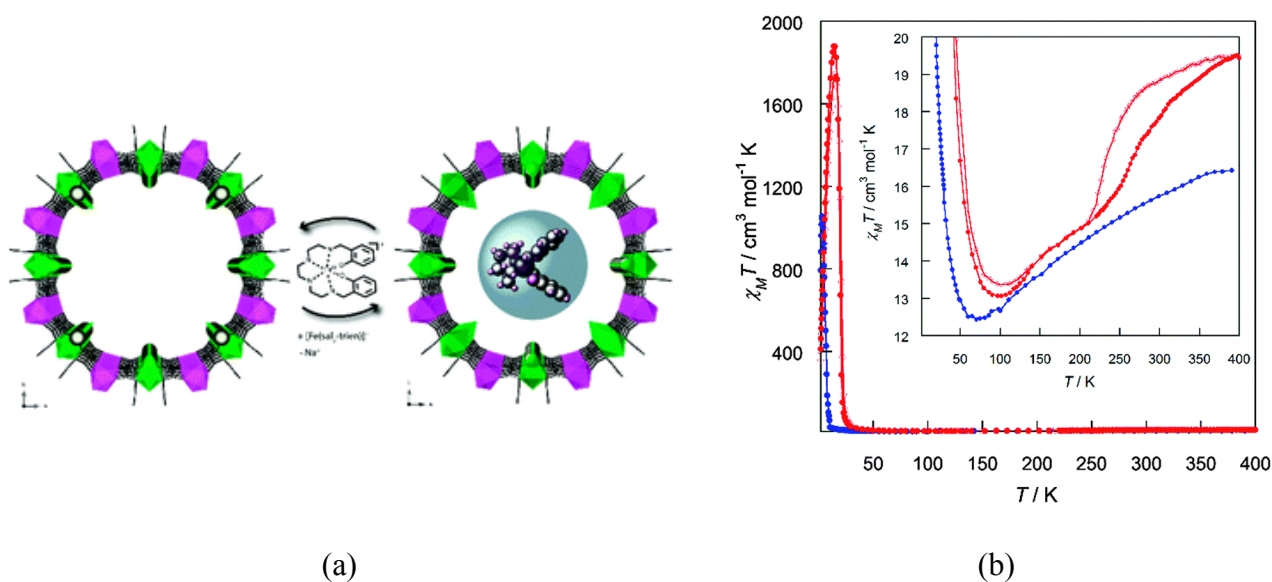


Figure 29. a) Schematic representation of the SC to SC cation exchange process leading to the hybrid $\text{Fe}(\text{sal}_2\text{-trien})@\text{Mn}^{\text{II}}\text{Cu}^{\text{II}}$ MOF. b) $\chi_M T$ versus T plot for $\text{Mn}^{\text{II}}\text{Cu}^{\text{II}}$ MOF (blue) and $\text{Fe}(\text{sal}_2\text{-trien})@\text{Mn}^{\text{II}}\text{Cu}^{\text{II}}$ MOF (red). The inset shows the minima and the high temperature region in detail, emphasising the thermal hysteresis loop. The full and empty circles represent the $\text{Fe}(\text{sal}_2\text{-trien})@\text{Mn}^{\text{II}}\text{Cu}^{\text{II}}$ MOF data recorded in the heating and cooling modes respectively. Adapted from reference 114, with permission from The Royal Society of Chemistry.

3.2. SMM @ MOFs.

Similar to spin-crossover complexes, metal complexes exhibiting SMM behaviour have been inserted in magnetic coordination polymers. Magnetic bimetallic oxalates have also been used to reach this goal. An appealing example of this kind is provided by the hybrid compound $[\text{Mn}^{\text{III}}(\text{salen})(\text{H}_2\text{O})]_2[\text{Mn}^{\text{II}}\text{Cr}^{\text{III}}(\text{ox})_3]_2 \cdot (\text{MeOH}) \cdot (\text{CH}_3\text{CN})_2$, which is formed by the SMM $[\text{Mn}^{\text{III}}(\text{salen})(\text{H}_2\text{O})]_2^{2+}$ ($\text{salen}^{2-} = \text{N,N}'\text{-ethylenebis}(\text{salicylideneimine})$) inserted into a ferromagnetic 3D oxalate network $[\text{Mn}^{\text{II}}\text{Cr}^{\text{III}}(\text{ox})_3]^-$.¹¹⁵ Notice that in the two-network compounds containing a magnetic oxalate network the electronic coupling between the two sublattices is usually very small and therefore a lack of interplay between the two properties has always been observed. Interestingly, this compound is an exception to this rule. Thus, the magnetic coupling

between the two spin sublattices leads to an antiparallel arrangement between the magnetization of the oxalate lattice and that of the inserted SMM. This coupling affects the magnetic relaxation of the SMM, but more interestingly it also affects the magnetic behavior of the ferromagnetic lattice. In fact, in contrast to the rest of hybrid materials containing the MnCr oxalate lattice, which behave as soft magnets, the coupling of this soft magnetic lattice with the highly anisotropic SMM leads to a drastic enhancement of the coercive field of the hybrid (from 10 to ca. 800 G), which behaves as a permanent magnet below 5 K (Figure 30). Although limited to low temperatures, this situation resembles that found in alloys of 3d metals and lanthanide ions that, like NdFe₁₄B, are among the best permanent magnets known to date, but has the advantage of using SMMs based on d-transition metal complexes instead of lanthanide ions as a source of magnetic anisotropy.

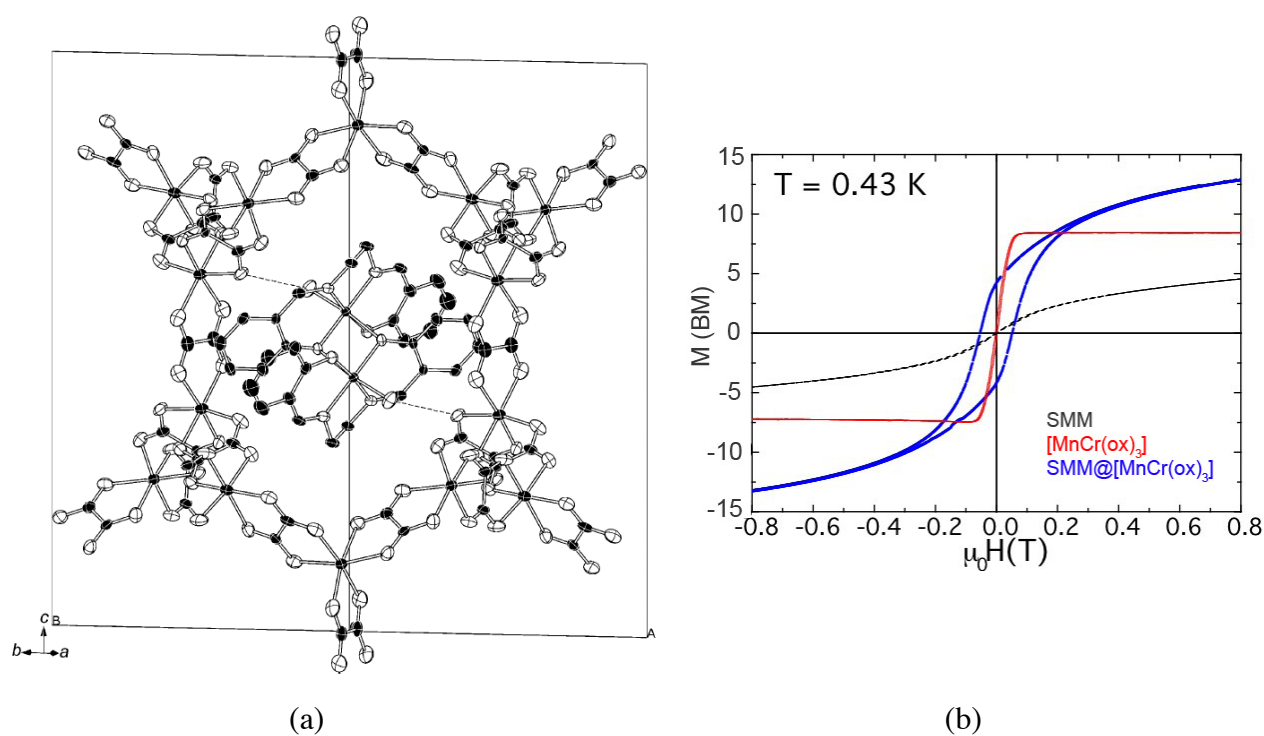


Figure 30. a) Crystal structure of $[\text{Mn}^{\text{III}}(\text{salen})(\text{H}_2\text{O})]_2[\text{Mn}^{\text{II}}\text{Cr}^{\text{III}}(\text{ox})_3]_2 \cdot (\text{MeOH})_3 \cdot (\text{CH}_3\text{CN})$. Hydrogen atoms and disordered solvent molecules have been omitted for clarity. b) Magnetization hysteresis loops of the hybrid **SMM@MnCr** (blue), the **SMM** in a diamagnetic network (black) and **MnCr** (red) measured at $T = 0.43$ K. The sweeping field rate was 6 mTs^{-1} . Adapted from reference 115, with permission of John Wiley and Sons.

The above example uses a self-assembly method to form the hybrid material. As pointed out above, the porosity and stability of some MOFs can be useful for loading molecules into their pores using post-synthetic procedures. These methods have also been used to incorporate SMMs within

both magnetic and non-magnetic MOFs. In the former case, the presence of a Mn^{III} porphyrin, which is a magnetic molecule behaving as a SIM, into a Mn^{II}Cu^{II} 3D magnetic MOF leads to an interplay of the magnetic properties.¹¹⁶ Thus, the internal magnetic field created by the long-range magnetic ordering of the MOF seems to have an influence on the slow magnetic relaxation of the SIM leading to an attenuation of the quantum tunneling of the magnetization in the mononuclear complex. Non-magnetic MOFs have also been used to accommodate the magnetic molecules with the aim of creating isolated nanostructures of these nanomagnets. An example has been the incorporation of Mn₁₂ acetate in the mesoporous aluminium-based MOF [Al(OH)(SDC)]_n (H₂SDC = 4,4'-stilbenedicarboxylic acid).¹¹⁷ The chemically robust magnetic polyoxometalate [(FeW₉O₃₄)₂Fe₄(H₂O)₂]¹⁰⁻ has been inserted in both diamagnetic and antiferromagnetic MOFs (UiO-67 and MIL-101(Cr), respectively).¹¹⁸ In the diamagnetic matrix the SMM behavior is retained because the magnetic anisotropy of the POMs is not altered by their interaction with the host. Differently, in the antiferromagnetic matrix the SMM character is clearly reduced because the magnetic interactions lead to faster relaxation of the magnetization.

To conclude this part we can say that magnetic molecules exhibiting a SMM behavior can be incorporated into the pores of a MOF using both self-assembly and post-synthetic methods. By using a diamagnetic MOF this approach has allowed to keep the SMMs isolated, leading to controlled nanostructures that retain the SMM behavior of the pure compound. In contrast, when the MOF matrix is magnetic, some changes in the SMM behavior are observed due to the weak interactions established between the two networks. However, with one exception, these interactions are too weak to affect the properties of the magnetic MOF.

3.3 Electroactive molecules @ MOFs

A class of molecular anions that have been incorporated into MOFs are the polyoxometalates (POMs). These metal-oxide clusters are robust species with unique electronic properties owing to their ability to act as electron reservoirs or to accommodate magnetic centers. In previous sections we have already shown some examples that illustrate these possibilities.^{67,68,97} In view of the ability of POMs to act as heterogeneous catalysts, their insertion and dispersion into the pores of a MOF can be beneficial in order to increase the active surface area of the POM and consequently its catalytic properties, while enhancing also the stability of the resulting POM-MOF material thanks to the host-guest interactions established between the two sublattices. In this context MOFs have shown to be more suitable to disperse POMs than other host matrices such as silica, activated carbon, ion-exchange resin and mesoporous molecular sieves, which often lead to low POM loading, POM leaching, agglomeration of POM particles and ill-defined solids. Some

examples that illustrate this concept are the following: i) the immobilization of the protonated Keggin POMs $[H_nXM_{12}O_{40}]^{m-}$ ($X = Si, Ge, P, As; M = Mo, W$) into the MOF Cu-BTC (BTC = benzenetricarboxylate) for the hydrolysis of esters;¹¹⁹ ii) the incorporation of the Keggin POM $[PW_{12}O_{40}]^{3-}$, used as template, in a sodalite-type MOF. This POM-MOF has displayed its potential application in the removal and decomposition of the nerve gas dimethyl methylphosphonate;¹²⁰ iii) the incorporation of $[CuPW_{11}O_{39}]^{5-}$ into the pores of HKUST-1 for air-based oxidations;¹²¹ iv) the incorporation of POMs $K_4[PW_{11}VO_{40}]$, $H_3[PW_{12}VO_{40}]$ and $K_4[SiW_{12}VO_{40}]$ in the MOF MIL-101 for selective adsorption of cationic dyes;¹²² v) the encapsulation of POMs within the large pores of the Zr(IV) biphenyldicarboxylate UiO-67 MOF.¹²³ These examples illustrate the use of electronically-innocent MOFs for dispersing electroactive molecules in their pores (Figure 1b). In this case, the MOFs play exclusively a structural role.

Other electroactive molecule that has been incorporated in the MOFs is the TCNQ, which is a well-known organic acceptor able to form low dimensional chain structures showing conductive properties. This molecule has been incorporated in the channels of the HKUST-1 MOF to give rise to a hybrid material showing an enhanced electrical conductivity from 10^{-6} S/m of the as-synthesised material to 7 S/m of the TCNQ loaded MOF.¹²⁴

4. Concluding remarks

In this review we have discussed the new opportunities that can appear in the crossroad between Molecular Magnetism and MOFs. Thus, the different types of multifunctional materials that can be encountered when combining magnetism with porosity have been discussed. In the first part, we have shown with three different classes of magnetic MOFs that the incorporation of magnetic centers in the coordination framework can result in the appearance of new properties in the crystalline MOF. In particular, this concept has provided a new generation of stimuli-responsive materials in which the magnetism can be tuned by the presence of molecular species in the pores (see the first and second class of MOFs, *vide infra*), or the possibility of keeping the magnetic centers well insulated in a crystalline framework (see the third class of MOFs, *vide infra*).

The first class of magnetic MOFs shows cooperative magnetic properties below a given critical temperature, T_c . The challenge with these materials is to shift T_c at temperatures as high as possible, a goal which is difficult to achieve since porosity and cooperative magnetism are two inimical properties that require opposite structural features (large porosity requires the use of long linkers between the metal centres, while strong exchange interactions require the use of short ones). In fact, this “magnetic exchange” approach is seriously hindered by the relatively low temperatures at which the cooperative magnetism appears (typically much below 100 K).

To overcome this limitation, a second class of magnetic MOFs based on “spin-crossover complexes” has been proposed as the spin transition typically occurs near room temperature. In that case, cooperativity is controlled by elastic forces in the lattice, which can be maintained at long metal-metal distances thanks to the polymeric nature of the MOF lattice. In fact, it has been shown that the structural changes occurring upon uptake/release of a guest molecule can be detected in these spin-crossover MOFs, while the cooperativity of this phenomenon is maintained for small pore sizes (typically in the nanometer range). Notice that this molecular confinement has shown to be beneficial to enhance the interaction between adsorbed gas molecules and the framework. This feature has resulted in a shift on the spin transition temperature upon gas sorption, which, in some cases, can be accompanied with a selectivity in the gas sorption.

A third class of magnetic MOFs that has been reported contains magnetic centres at the nodes of the framework. In that case, the interest is to generate magnetic nanostructures which are well organized and well insulated in the space thanks to the structural features of the MOF. Since these magnetic centres may behave as single-molecule magnets, their controlled organization in the space could find an application in quantum computing since each magnetic centre behaves as a quantum bit. In addition, the well magnetic insulation provided by the MOF has shown to be useful to obtain isotropic paramagnetic materials which can be of interest as magnetic coolers.

All the examples reported in this part have exploited the possibility of incorporating the magnetism at the nodes of the framework. Still, the porosity offered by these coordination polymers can also allow us to fill the pores with functional molecules. This possibility is discussed in the second part of the review where hybrid functional MOFs combining an extended lattice with a molecular lattice are presented. These hybrids have been used as an ideal platform to create new multifunctional materials covering from the simple co-existence of different properties, provided by the framework and the functional guest, to a synergy between these functionalities as a result of the coupling between the two components. Thus, in this part different types of functional molecules have been introduced in the channels, including magnetic molecules (spin-crossover and single-molecule magnets) as well as electro-active molecules (electron donors and acceptors, for example). The result of such a combination has given rise in some cases to an improvement in the properties of the hybrid MOFs, making them of interest in magnetism (lanthanide-free hard magnets), heterogeneous catalysis (catalysts with enhanced surface areas) or electronics (MOFs with semiconducting properties).

5. Perspectives

To finish we should mention some of the current challenges and perspectives in the field of magnetic MOFs. The incorporation of magnetic functionality in a MOF is quite recent, so that at this step most of the studies in this area have been focused on the synthesis of materials in bulk, with analysis of the crystal structures and properties. The field has to move on to the processing of these materials towards applications, including, among others, their use as sensors, in electronic applications, in magnetic refrigeration, or in quantum computing. For example, the study of the quantum coherence in SMM-MOFs is at the very early stages, and the integration of these qubits in superconducting circuits would be the next stage in order to manipulate the spin state. For some of these applications it is crucial to process the materials, and not only using single crystals, or polycrystalline materials, which are currently the goal of chemists in order to get unequivocal information regarding the structural aspects of the new materials. Thus, magnetic MOFs should be processed as films, nanoparticles, or nanostructures, while keeping the properties.

The initial steps on this matter have already been done in films of coordination polymers based on spin-crossover, where thick films have been prepared.^{125,126} Despite their roughness, these films can be used as sensors, but their application is unfeasible in nano- and micro-electronics (including spintronics) as these applications require films of higher quality. In this context, a current trend in this area is that of integrating these MOFs as ultrathin films on solid surfaces (SURMOFs). The first generation of SURMOFs has given rise to the emergence of new MOF-based devices of interest as separation membranes, catalytic coatings, or sensors that exploit the porosity as active function.¹²⁷ In the context of MOFs with electronic functionalities, an appealing issue is that of exploiting not only their porosity but also these electronic functionalities in order to use these films as active interfaces in electronic molecular-based devices. Most properties of these devices are crucially determined by these interfaces so that an active manipulation of these interfaces is key to improve the device performance. This second generation of SURMOFs is chemically much more demanding than the first one because it requires the organization of continuous, high-quality and oriented ultrathin films (below 10-20 nm) of these materials on surfaces. Furthermore, it is also very demanding from the electronic point of view since it requires to tailor the degree of interaction between the SURMOF and the inorganic surface as that generally impacts the electronic properties of the hybrid interface and the functioning of the entire device. Still, the accomplishment of these challenging goals can open new perspectives in the use of MOFs in molecular electronics and spintronics. Here, the transport of charge carriers as well as the spin injection across the MOF interface could be manipulated by loading of molecular guests in the porous scaffold. In addition, the open structures of these crystalline materials display higher surface areas for direct contact with the molecules than those offered by a normal 2D surface, thus improving the interactions between

these molecules and the inorganic surface. These complex hybrid interfaces, integrated by an open framework and molecular guests, are linked to a new idea of assembled 3D interfaces with addressable functionality, which may generate conceptually new hybrid devices. In this line, the possibility of incorporating molecules with different functionalities (magnetism, bistability, luminescence, etc.) inside the MOF, or increasing the intrinsic conductivity of the framework could enlarge the versatility of these complex interfaces.

A recent result that exemplifies the fabrication of these electronically-active MOF interfaces has been recently reported.¹²⁸ The approach involves a sequential layer-by-layer transfer of 2D preassembled MOF nanosheets, organized by using a Langmuir-Blodgett method, to SAM-functionalized substrates. As model system, a layered MOF built from the sequential stacking of 2D networks of Co(II) tetracarboxylate porphyrin units interconnected by Cu(II) ions (NAFS-1) has been used (Figure 31). In contrast with previous methodologies, SAM-assisted transfer enables the fabrication of homogeneous, highly oriented, ultrathin films across millimeter-scale areas, regardless of the substrate. This approach has allowed to transfer NAFS-1 onto a nonconventional, ferromagnetic substrate such as permalloy. Owing to the high quality and low-thickness (<10 nm) of these SURMOFs, it has been possible to investigate their electrical properties and evaluate the effect of the thickness of the MOF over the conductance using Hg drop micrometric electrode junctions. This result illustrates that this liquid-phase layer-by-layer method can be a useful approach to fabricate electronic interfaces based on magnetic SURMOFs. This kind of approach has also shown to be useful for preparing thin films of good optical quality based on Hofmann chelates exhibiting spin crossover.^{124,125,129}

A different approach that can be foreseen to improve the quality of these ultrathin films is based on the deposition of two-dimensional (2D) crystals on electronic/magnetic surfaces which can provide very clean interfaces of direct application in electronics / spintronics, as has already been shown with graphene and graphene-like 2D materials.¹³⁰ This goal can be achieved either by using chemical vapour deposition (CVD) methods, or by direct micromechanical exfoliation of the bulk materials and subsequent transfer of the 2D layer onto the substrate. The first approach (CVD method), although very promising, has been exploited only very recently in MOF chemistry for the preparation of ZIF-8.¹³¹ This archetypical MOF has served to demonstrate the feasibility of CVD but its electronic properties are rather limited. The second approach (micromechanical exfoliation method) has not been still reported in MOF chemistry. The only examples are limited to the use of liquid exfoliation methods,^{132,133} which lack the high quality requirements for electronic applications.


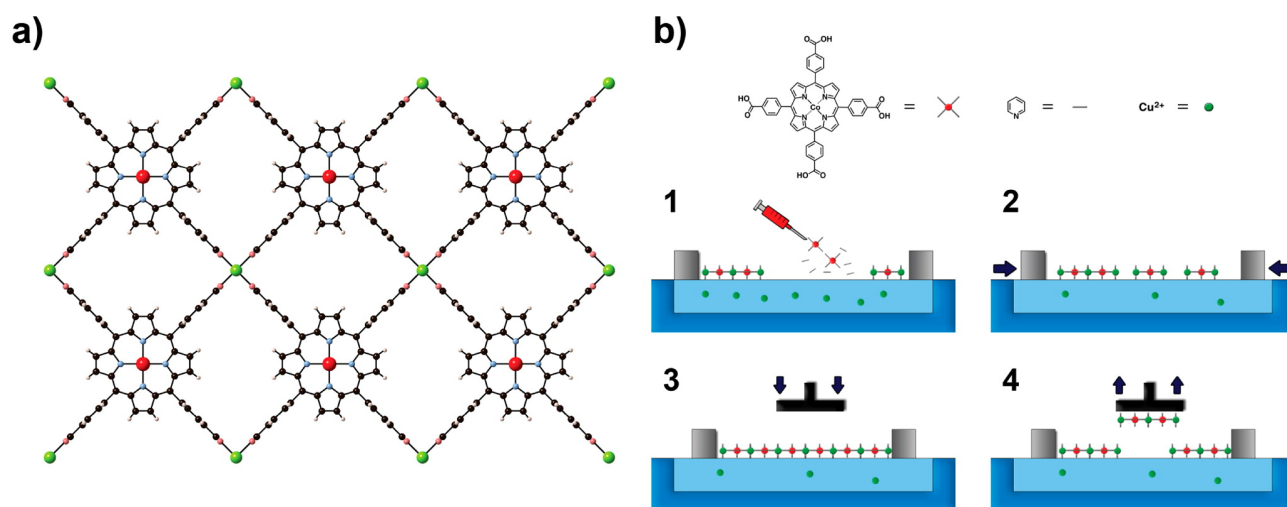


Figure 31. NAFS-1 structure (a) and Langmuir–Blodgett (LB) transfer process (b). Reprinted with permission from reference 128, Copyright 2016 American Chemical Society.

Acknowledgements

Financial support from the Spanish MINECO (Unit of Excellence María de Maeztu MDM-2015-0538, CTQ2014-59209-P and MAT2014-56143-R), the Generalitat Valenciana (Prometeo programme), the EU (ERC-2016-CoG 724681-S-CAGE) and the VLC/Campus Program is gratefully acknowledged. G.M.E. acknowledges Ramón y Cajal Programme.

Table of contents

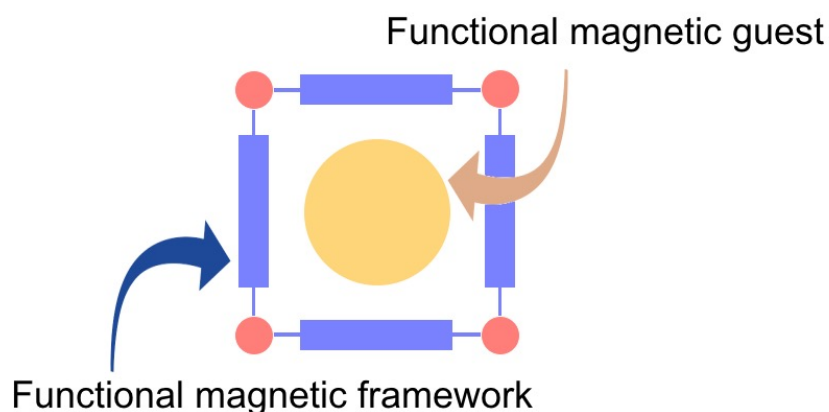

This review covers the incorporation of different magnetic phenomena in MOFs, either in the framework or through the encapsulation of functional species in the pores.

References

- ¹ C. Wang, D. Liu, W. Lin, *J. Am. Chem. Soc.* 2013, **135**, 13222–13234.
- ² P. Z. Moghadam, A. Li, S. B. Wiggin, A. Tao, A. G. P. Maloney, P. A. Wood, S. C. Ward, D. Fairen-Jimenez, *Chem. Mater.* 2017, **29**, 2618–2625.
- ³ S. S. Park, E. R. Hontz, L. Sun, C. H. Hendon, A. Walsh, T. Van Voorhis, M. Dinca, *J. Am. Chem. Soc.* 2015, **137**, 1774–1777.
- ⁴ L. Sun, M. G. Campbell, M. Dinca, *Angew. Chem. Int. Ed.* 2016, **55**, 3566–3579.
- ⁵ Z. Hu, B. J. Deibert, J. Li, *Chem. Soc. Rev.* 2014, **43**, 5815–5840.
- ⁶ L.-J. Xu, G.-T. Xu, Z.-N. Chen, *Coord. Chem. Rev.* 2014, **273–274**, 47–62.
- ⁷ Y. Cui, B. Chen, G. Qian, *Coord. Chem. Rev.* 2014, **273–274**, 76–86.
- ⁸ a) J. M. Manriquez, G. T. Yee, R. S. McLean, A. J. Epstein, J. S. Miller, *Science* 1991, **252**, 1415–1417; b) T. Mallah, S. Thiébaud, M. Verdaguer, P. Veillet, *Science* 1993, **262**, 1554–1557; c) S. Ferlay, T. Mallah, R. Ouahès, P. Veillet, M. Verdaguer, *Nature* 1995, **378**, 701–703
- ⁹ M. Clemente-León, E. Coronado, C. Martí-Gastaldo, F. M. Romero, *Chem. Soc. Rev.*, 2011, **40**, 473–497.
- ¹⁰ E. Coronado, J. R. Galán-Mascarós, C. J. Gómez-García, V. Laukhin, *Nature*, 2000, **408**, 447–449.
- ¹¹ E. Coronado, P. Day, *Chem. Rev.* 2004, **104**, 5419–5448.
- ¹² P. Guetlich, A. B. Gaspar, Y. Garcia, *Beilstein J. Org. Chem.* 2013, **9**, 342–391.
- ¹³ S. Ohkoshi, H. Tokoro, *Acc. Chem. Res.* 2012, **45**, 1749–1758.
- ¹⁴ T. Nuida, T. Matsuda, H. Tokoro, S. Sakurai, K. Hashimoto, S. Ohkoshi, *J. Am. Chem. Soc.* 2005, **127**, 11604–11605.
- ¹⁵ E. Coronado, G. Mínguez Espallargas, *Chem. Soc. Rev.* 2013, **42**, 1525–1539.
- ¹⁶ E. Coronado, M. Giménez-Marqués, G. Mínguez Espallargas, L. Brammer, *Nature Commun.* 2012, **3**, 828.
- ¹⁷ P. Jain, V. Ramachandran, R. J. Clark, H. D. Zhou, B. H. Toby, N. S. Dalal, H. W. Kroto, A. K. Cheetham, *J. Am. Chem. Soc.* 2009, **131**, 13625.
- ¹⁸ G.-C. Xu, W. Zhang, X.-M. Ma, Y.-H. Chen, L. Zhang, H.-L. Cai, Z.-M. Wang, R.-G. Xiong, S. Gao, *J. Am. Chem. Soc.* 2011, **133**, 14948–14951.
- ¹⁹ B. Saparov and D. B. Mitzi, *Chem. Rev.* 2016, **116**, 4558–4596.
- ²⁰ Z. M. Wang, B. Zhang, H. Fujiwara, H. Kobayashi, M. Kurmoo, *Chem. Commun.* 2004, 416.
- ²¹ B. Zhang, Z.-M. Wang, M. Kurmoo, S. Gao, K. Inoue and H. Kobayashi, *Adv. Funct. Mater.*, 2007, **17**, 577–584.

-
- ²² Z.-M. Wang, B. Zhang, M. Kurmoo, M. A. Green, H. Fujiwara, T. Otsuka and H. Kobayashi, *Inorg. Chem.*, 2005, **44**, 1230–1237.
- ²³ M. Viertelhaus, P. Adler, R. Clérac, C. E. Anson and A. K. Powell, *Eur. J. Inorg. Chem.*, 2005, 692–703.
- ²⁴ D. N. Dybtsev, H. Chun, S. H. Yoon, D. Kim and K. Kim, *J. Am. Chem. Soc.*, 2004, **126**, 32–33.
- ²⁵ Z. Wang, Y. Zhang, T. Liu, M. Kurmoo and S. Gao, *Adv. Funct. Mater.*, 2007, **17**, 1523–1536.
- ²⁶ Z. Wang, K. Hu, S. Gao, H. Kobayashi, *Adv. Mater.*, 2010, **22**, 1526–1533.
- ²⁷ M. Verdaguer, G. S. Girolami, “Magnetic Prussian Blue Analogs” in “Magnetism: Molecules to Materials V” ed. J. S. Miller, M. Drillon, Wiley-VCH, p. 283.
- ²⁸ M. Shatruk, S. Gómez-Coca, K. R. Dunbar, “Molecular Magnetism”, in “Molecular Magnetic Materials: Concepts and Applications”, Eds. B. Sieklucka and D. Pinkowicz, Wiley-VCH 2016
- ²⁹ L. G. Beauvais, J. R. Long, *J. Am. Chem. Soc.* 2002, **124**, 12096–12097.
- ³⁰ S. S. Kaye, H. J. Choi, J. R. Long, *J. Am. Chem. Soc.* 2008, **130**, 16921–16925.
- ³¹ J.-P. Zhang, Y.-B. Zhang, J.-B. Lin, and X.-M. Chen, *Chem. Rev.* 2012, **112**, 1001–1033.
- ³² C. Pettinari, A. Tabacaru, S. Galli, *Coord. Chem. Rev.* 2016, **307**, 1–31.
- ³³ A. Phan, C. J. Doonan, F. J. Uribe-Romo, C. B. Knobler, M. O’Keeffe, O. M. Yaghi, *Acc. Chem. Res.* 2010, **43**, 58–67.
- ³⁴ K. S. Park, Z. Ni, A. P. Côté, J. Y. Choi, R. Huang, F. J. Uribe-Romo, H. K. Chae, M. O’Keeffe, O. M. Yaghi, *Proc. Natl. Acad. Sci. U.S.A.* 2006, **103**, 10186–10191.
- ³⁵ Y.-Q. Tian, C.-X. Cai, Y. Ji, X.-Z. You, S.-M. Peng, G.-H. Lee, *Angew. Chem. Int. Ed.* 2002, **41**, 1384–1386.
- ³⁶ Y.-Q. Tian, C.-X. Cai, X.-M. Ren, C.-Y. Duan, Y. Xu, S. Gao, X.-Z. You, *Chem. Eur. J.* 2003, **9**, 5673–5685.
- ³⁷ Y.-Q. Tian, Z.-X. Chen, L.-H. Weng, H.-B. Guo, S. Gao, D. Y. Zhao, *Inorg. Chem.* 2004, **43**, 4631–4635.
- ³⁸ S. S. Mondal, A. Bhunia, S. Demeshko, A. Kelling, U. Schilde, C. Janiak, H.-J. Holdt, *CrystEngComm*, 2014, **16**, 39–42.
- ³⁹ M. Wriedt, A. A. Yakovenko, G. J. Halder, A. V. Prosvirin, K. R. Dunbar, H.-C. Zhou, *J. Am. Chem. Soc.* 2013, **135**, 4040–4050.
- ⁴⁰ J.A. R. Navarro, E. Barea, A. Rodríguez-Diéguez, J. M. Salas, C. O. Ania, J. B. Parra, N. Masciocchi, S. Galli, A. Sironi, *J. Am. Chem. Soc.* 2008, **130**, 3978–3984.
- ⁴¹ M.-H. Zeng, Z. Yin, Y.-X. Tan, W.-X. Zhang, Y.-P. He, M. Kurmoo, *J. Am. Chem. Soc.* 2014, **136**, 4680–4688.

-
- ⁴² P. D. C. Dietzel, Y. Morita, R. Blom, H. Fjellvåg, *Angew. Chem. Int. Ed.* 2005, **44**, 6354–6358.
- ⁴³ E. D. Bloch, W. L. Queen, R. Krishna, J. M. Zadrozny, C. M. Brown, J. R. Long, *Science* 2012, **335**, 1606.
- ⁴⁴ J. Park, H. Kim, Y. Jung, *J. Phys. Chem. Lett.* 2013, **4**, 2530–2534.
- ⁴⁵ Q. Zhang, B. Li, L. Chen, *Inorg. Chem.* 2013, **52**, 9356.
- ⁴⁶ H. Wu, J. M. Simmons, G. Srinivas, W. Zhou, T. Yildirim, *J. Phys. Chem. Lett.*, 2010, **1**, 1946–1951.
- ⁴⁷ D. Yu, A. O. Yazaydin, J. R. Lane, P. D. C. Dietzel, R. Q. Snurr, *Chem. Sci.*, 2013, **4**, 3544–3556
- ⁴⁸ M. C. Das, S. Xiang, Z. Zhang, B. Chen *Angew. Chem. Int. Ed.* 2011, **50**, 10510–10520.
- ⁴⁹ T. Grancha, J. Ferrando-Soria, M. Castellano, M. Julve, J. Pasán, D. Armentano, E. Pardo, *Chem. Commun.*, 2014, **50**, 7569–7585.
- ⁵⁰ J. Ferrando-Soria, P. Serra-Crespo, M. de Lange, J. Gascon, F. Kapteijn, M. Julve, J. Cano, F. Lloret, J. Pasán, C. Ruiz-Pérez, Y. Journaux, E. Pardo, *J. Am. Chem. Soc.* 2012, **134**, 15301–15304
- ⁵¹ T. B. Faust, D. M. D'Alessandro, *RSC Adv.*, 2014, **4**, 17498–17512.
- ⁵² D. MasPOCH, D. Ruiz-Molina, K. WurSt, N. Domingo, M. Cavallini, F. Biscarini, J. Tejada, C. Rovira, J. Veciana, *Nat. Mater.*, 2003, **2**, 190–195.
- ⁵³ N. Roques, D. MasPOCH, I. Imaz, A. Datcu, J.-P. Sutter, C. Rovira, J. Veciana, *Chem. Commun.* 2008, 3160–3162.
- ⁵⁴ A. Datcu, N. Roques, V. Jubera, D. MasPOCH, X. Fontrodona, K. WurSt, I. Imaz, G. Mouchaham, J.-P. Sutter, C. Rovira, J. Veciana, *Chem. Eur. J.* 2012, **18**, 152–162.
- ⁵⁵ N. Motokawa, S. Matsunaga, S. Takaishi, H. Miyasaka, M. Yamashita, K. R. Dunbar, *J. Am. Chem. Soc.*, 2010, **132**, 11943–11951.
- ⁵⁶ I.-R. Jeon, B. Negru, R. P. Van Duyne, T. D. Harris, *J. Am. Chem. Soc.* 2015, **137**, 15699–15702
- ⁵⁷ Halcrow M. (eds.) *Spin-crossover materials properties and applications*. Wiley (2013).
- ⁵⁸ A. Bousseksou, G. Molnár, L. Salmon, W. Nicolazzi, *Chem. Soc. Rev.*, 2011, **40**, 3313–3335.
- ⁵⁹ R. Ohtani and S. Hayami, *Chem. Eur. J.* 2017, **23**, 2236–2248.
- ⁶⁰ P. D. Southon, L. Liu, E. A. Fellows, D. J. Price, G. J. Halder, K. W. Chapman, B. Moubaraki, K. S. Murray, J.-F. Létard, C. J. Kepert, *J. Am. Chem. Soc.* 2009, **131**, 10998–11009.
- ⁶¹ M. Ohba, K. Yoneda, G. Agustí, M. C. Muñoz, A. B. Gaspar, J. A. Real, M. Yamasaki, H. Ando, Y. Nakao, S. Sakaki, S. Kitagawa, *Angew. Chem. Int. Ed.* 2009, **48**, 4767–4771.
- ⁶² E. Coronado, M. Giménez-Marqués, G. Mínguez Espallargas, F. Rey, I. J. Vitórica-Yrezábal, *J. Am. Chem. Soc.* 2013, **135**, 15986–15989.

-
- ⁶³ M. Giménez-Marqués, N. Calvo Galve, M. Palomino, S. Valencia, F. Rey, G. Sastre, I. J. Vitorica-Yrezábal, M. Jiménez-Ruiz, J. A. Rodríguez-Velamazán, M. A. González, J. L. Jordá, E. Coronado, G. Mínguez Espallargas, *Chem. Sci.* 2017, **8**, 3109–3120.
- ⁶⁴ N. Calvo Galve, M. Giménez-Marqués, M. Palomino, S. Valencia, F. Rey, G. Mínguez Espallargas, E. Coronado, *Inorg. Chem. Front.* 2016, **3**, 808–813.
- ⁶⁵ M. C. Muñoz, J. A. Real, *Coord. Chem. Rev.* 2011, **255**, 2068–2093.
- ⁶⁶ Z. Arcís-Castillo, F. J. Muñoz-Lara, M. C. Muñoz, D. Aravena, A.B. Gaspar, J. F. Sánchez-Royo, E. Ruiz, M. Ohba, R. Matsuda, S. Kitagawa, J. A. Real, *Inorg. Chem.* 2013, **52**, 12777–12783.
- ⁶⁷ G. Agustí, R. Ohtani, K. Yoneda, A. B. Gaspar, M. Ohba, J. F. Sánchez-Royo, M. C. Muñoz, S. Kitagawa and J. A. Real, *Angew. Chem. Int. Ed.* 2009, **48**, 8944–8947.
- ⁶⁸ R. Ohtani, K. Yoneda, S. Furukawa, N. Horike, S. Kitagawa, A. B. Gaspar, M. C. Muñoz, J. A. Real and M. Ohba, *J. Am. Chem. Soc.* 2011, **133**, 8600–8605.
- ⁶⁹ J. E. Clements, J. R. Price, S. M. Neville, C. J. Kepert, *Angew. Chem. Int. Ed.* 2014, **53**, 10164–10168.
- ⁷⁰ A. D. Katsenis, E. K. Brechin, G. S. Papaefstathiou, *Metal-Organic Framework Materials - Encyclopedia of Inorganic and Bioinorganic Chemistry*, Chapter: Metal-Organic Frameworks from Single-Molecule Magnets, **2014**, pp.245-258.
- ⁷¹ I.-R. Jeon, R. Clerac, *Dalton Trans.* 2012, **41**, 9569.
- ⁷² H. Miyasaka, K. Nakata, K.-i. Sugiura, M. Yamashita, R. Clérac, *Angew. Chem. Int. Ed.* 2004, **43**, 707.
- ⁷³ H. Miyasaka, K. Nakata, L. Lecren, C. Coulon, Y. Nakazawa, T. Fijisaki, K.-i. Sugiura, M. Yamashita, R. Clérac, *J. Am. Chem. Soc.* 2006, **128**, 3770.
- ⁷⁴ M. Murrie, S. J. Teat, H. Stoeckli-Evans, H. Güdel, *Angew. Chem. Int. Ed.* 2003, **42**, 4653
- ⁷⁵ X. Jiang, C.-M. Liu, H.-Z. Kou, *Inorg. Chem.* 2016, **55**, 5880–5885.
- ⁷⁶ J. J. Baldoví, E. Coronado, A. Gaita-Ariño, C. Gamer, M. Giménez-Marqués, G. Mínguez Espallargas, *Chem. Eur. J.* 2014, **20**, 10695–10702.
- ⁷⁷ J. López-Cabrelles, G. Mínguez Espallargas, E. Coronado, *Polymers* 2016, **8**, 171.
- ⁷⁸ J. M. Clemente-Juan, E. Coronado, A. Gaita Ariño in "Lanthanides and Actinides in Molecular Magnetism", pp. 27–60, Eds R. Layfield, M. Murugesu (2015).
- ⁷⁹ I. Oyarzabal, B. Fernández, J. Cepeda, S. Gómez-Ruiz, A. J. Calahorra, J. M. Seco, A. Rodríguez-Diéguez, *CrystEngComm* 2016, **18**, 3055–3063.
- ⁸⁰ Q. Chen, J. Li, Y.-S. Meng, H.-L. Sun, Y.-Q. Zhang, J.-L. Sun, S. Gao, *Inorg. Chem.* 2016, **55**, 7980–7987.

-
- ⁸¹ K. Liu, H. Li, X. Zhang, W. Shi, P. Cheng, *Inorg. Chem.* 2015, **54**, 10224–10231.
- ⁸² J. Vallejo, F. R. Fortea-Pérez, E. Pardo, S. Benmansour, I. Castro, J. Krzystek, D. Armentano, J. Cano, *Chem. Sci.* 2016, **7**, 2286–2293.
- ⁸³ J. M. Zadrozny, A. T. Gallagher, T. D. Harris, D. E. Freedman, *J. Am. Chem. Soc.*, 2017, **139**, 7089–7094.
- ⁸⁴ M. Shiddiq, D. Komijani, Y. Duan, A. Gaita-Ariño, E. Coronado, S. Hill, *Nature* 2016, **531**, 348–351.
- ⁸⁵ M. Evangelisti, E. Manuel, M. Affronte, M. Okubo, C. Train, M. Verdaguer, *J. Magn. Magn. Mater.* 2007, **316**, e569–e571.
- ⁸⁶ E. Manuel, M. Evangelisti, M. Affronte, M. Okubo, C. Train, M. Verdaguer, *Phys. Rev. B* 2006, **73**, 172406.
- ⁸⁷ N. Sharma, S. M. Yusuf, A. Kumar, J. V. Yakhmi, *AIP Conf. Proc.* 2008, **1003**, 8.
- ⁸⁸ S. M. Yusuf, A. Kumar, J. V. Yakhmi, *Appl. Phys. Lett.* 2009, **95**, 182506.
- ⁸⁹ R. Sibille, T. Mazet, B. Malaman, M. François, *Chem. Eur. J.* 2012, **18**, 12970–12973.
- ⁹⁰ L. Sedláková, J. Hanko, A. Orendáčová, M. Orendác, C.-L. Zhou, W.-H. Zhu, B.-W. Wang, Z.-M. Wang, S. Gao, *J. Alloys Compd.* 2009, **487**, 425–429.
- ⁹¹ S. Biswas, H. S. Jena, S. Goswami, S. Sanda, S. Konar, *Cryst. Growth Des.* 2014, **14**, 1287–1295.
- ⁹² P.-F. Shi, Y.-Z. Zheng, X.-Q. Zhao, G. Xiong, B. Zhao, F.-F. Wan, P. Cheng, *Chem. Eur. J.* 2012, **18**, 15086–15091.
- ⁹³ G. Abellán, G. Mínguez Espallargas, G. Lorusso, M. Evangelisti, E. Coronado, *Chem. Commun.*, 2015, **51**, 14207–14210.
- ⁹⁴ Y. Inokuma, S. Yoshioka, J. Ariyoshi, T. Arai, Y. Hitora, K. Takada, S. Matsunaga, K. Rissanen and M. Fujita, *Nature*, 2013, **495**, 461.
- ⁹⁵ J. Juan-Alcañiz, J. Gascon, F. Kapteijn, *J. Mater. Chem.*, 2012, **22**, 10102–10118.
- ⁹⁶ Y.-Q. Lan, H.-L. Jiang, S.-L. Li, Q. Xu, *Inorg. Chem.* 2012, **51**, 7484–7491.
- ⁹⁷ P. Mahato, N. Yanai, M. Sindoro, S. Granick, N. Kimizuka, *J. Am. Chem. Soc.* 2016, **138**, 6541–6549.
- ⁹⁸ C.-Y. Sun, W.-P. To, X.-L. Wang, K.-T. Chan, Z.-M. Su, C.-M. Che, *Chem. Sci.* 2015, **6**, 7105–7111.
- ⁹⁹ M. Giménez-Marqués, T. Hidalgo, C. Serre, P. Horcajada, *Coord. Chem. Rev.* 2016, **307**, 342–360.
- ¹⁰⁰ F. J. Carmona, S. Rojas, P. Sánchez, H. Jeremias, A. R. Marques, C. C. Romão, D. Choquesillo-Lazarte, J. A. R. Navarro, C. R. Maldonado, E. Barea, *Inorg. Chem.* 2016, **55**, 6525–6531.

-
- ¹⁰¹ R. C. Klet, S. Tussupbayev, J. Borycz, J. R. Gallagher, M. M. Stalzer, J. T. Miller, L. Gagliardi, J. T. Hupp, T. J. Marks, C. J. Cramer, M. Delferro, O. K. Farha, *J. Am. Chem. Soc.*, 2015, **137**, 15680–15683.
- ¹⁰² A. Grigoropoulos, G. F. S. Whitehead, N. Perret, A. P. Katsoulidis, F. M. Chadwick, R. P. Davies, A. Haynes, L. Brammer, A. S. Weller, J. Xiao, M. J. Rosseinsky, *Chem. Sci.*, 2016, **7**, 2037–2050.
- ¹⁰³ D. Yang, S. O. Odoh, T. C. Wang, O. K. Farha, J. T. Hupp, C. J. Cramer, L. Gagliardi, B. C. Gates, *J. Am. Chem. Soc.* 2015, **137**, 7391–7396.
- ¹⁰⁴ T. Kajiwara, M. Fujii, M. Tsujimoto, K. Kobayashi, M. Higuchi, K. Tanaka, S. Kitagawa, *Angew. Chem. Int. Ed.* 2016, **55**, 2697–2700.
- ¹⁰⁵ A. Chołuj, A. Zieliński, K. Grela, M. J. Chmielewski, *ACS Catalysis* 2016, **6**, 6343–6349.
- ¹⁰⁶ C. R. Kim, T. Uemura, S. Kitagawa, *Chem. Soc. Rev.* 2016, **45**, 3828–3845.
- ¹⁰⁷ C. Rösler, R. A. Fischer, *CrystEngComm* 2015, **17**, 199–217.
- ¹⁰⁸ P. Falcaro, R. Ricco, A. Yazdi, I. Imaz, S. Furukawa, D. Maspoeh, R. Ameloot, J. D. Evans, C. J. Doonan, *Coord. Chem. Rev.* 2016, **307**, 237–254.
- ¹⁰⁹ M. Clemente-León, E. Coronado, C. Martí-Gastaldo, F. M. Romero, *Chem. Soc. Rev.*, 2011, **40**, 473–497.
- ¹¹⁰ M. López-Jordà, M. Giménez-Marqués, C. Desplanches, G. Mínguez Espallargas, M. Clemente-León, E. Coronado, *Eur. J. Inorg. Chem.* 2016, 2187–2192 and references therein.
- ¹¹¹ T. Zhao, I. Boldog, V. Spasojevic, A. Rotaru, Y. Garcia, C. Janiak, *J. Mater. Chem. C*, 2016, **4**, 6588–6601.
- ¹¹² M. Clemente-León, E. Coronado, M. López-Jordà, C. Desplanches, S. Asthana, H. Wang, J.-F. Létard, *Chem. Sci.*, 2011, **2**, 1121–1127.
- ¹¹³ M. Clemente-León, E. Coronado, M. López-Jordà, J. C. Waerenborgh, C. Desplanches, H. Wang, J.-F. Létard, A. Hauser, A. Tissot, *J. Am. Chem. Soc.* 2013, **135**, 8655–8667.
- ¹¹⁴ A. Abhervé, T. Grancha, J. Ferrando-Soria, M. Clemente-León, E. Coronado, J. C. Waerenborgh, F. Lloret, E. Pardo, *Chem. Commun.*, 2016, **52**, 7360–7363.
- ¹¹⁵ M. Clemente-León, E. Coronado, C. J. Gómez-García, M. López-Jordà, A. Camón, A. Repollés, F. Luis, *Chem. Eur. J.* 2014, **20**, 1669–1676.
- ¹¹⁶ M. Mon, A. Pascual-Álvarez, T. Grancha, J. Cano, J. Ferrando-Soria, F. Lloret, J. Gascon, J. Pasán, D. Armentano, E. Pardo, *Chem. Eur. J.*, 2016, **22**, 539–545.
- ¹¹⁷ D. Aulakh, J. B. Pyser, X. Zhang, A. A. Yakovenko, K. R. Dunbar, M. Wriedt, *J. Am. Chem. Soc.* 2015, **137**, 9254–9257.

-
- ¹¹⁸ W. Salomon, Y. Lan, E. Rivière, S. Yang, C. Roch-Marchal, A. Dolbecq, C. Simonnet-Jégat, N. Steunou, N. Leclerc-Laronze, L. Ruhlmann, T. Mallah, W. Wernsdorfer, P. Mialane, *Chem. Eur. J.* 2016, **22**, 6564–6574.
- ¹¹⁹ C.-Y. Sun, S.-X. Liu, D.-D. Liang, K.-Z. Shao, Y.-H. Ren, Z.-M. Su, *J. Am. Chem. Soc.*, 2009, **131**, 1883–1888.
- ¹²⁰ F.-J. Ma, S.-X. Liu, C.-Y. Sun, D.-D. Liang, G.-J. Ren, F. Wei, Y.-G. Chen, Z.-M. Su, *J. Am. Chem. Soc.*, 2011, **133**, 4178–4181.
- ¹²¹ J. Song, Z. Luo, D. K. Britt, H. Furukawa, O. M. Yaghi, K. I. Hardcastle, C. L. Hill, *J. Am. Chem. Soc.* 2011, **133**, 16839–16846.
- ¹²² A.-X. Yan, S. Yao, Y.-G. Li, Z.-M. Zhang, Y. Lu, W.-L. Chen, E.-B. Wang, *Chem. Eur. J.* 2014, **20**, 6927–6933.
- ¹²³ W. Salomon, C. Roch-Marchal, P. Mialane, P. Rouschmeyer, C. Serre, M. Haouas, F. Taulelle, S. Yang, L. Ruhlmann, A. Dolbecq, *Chem. Commun.* 2015, **51**, 2972–2975.
- ¹²⁴ A. A. Talin, A. Centrone, A. C. Ford, M. E. Foster, V. Stavila, P. Haney, R. A. Kinney, V. Szalai, F. El Gabaly, H. P. Yoon, F. Léonard, M. D. Allendorf, *Science* 2014, **343**, 66–69.
- ¹²⁵ S. Cobo, G. Molnár, J. A. Real, A. Bousseksou, *Angew. Chem. Int. Ed.* 2006, **45**, 5786–5789.
- ¹²⁶ C. Bartual-Murgui, L. Salmon, A. Akou, C. Thibault, G. Molnár, T. Mahfoud, Z. Sekkat, J. A. Real, A. Bousseksou, *New J. Chem.*, 2011, **35**, 2089–2094.
- ¹²⁷ B. Liu, *J. Mater. Chem.* 2012, **22**, 10094–10101.
- ¹²⁸ V. Rubio-Giménez, S. Tatay, F. Volatron, F. J. Martínez-Casado, C. Martí-Gastaldo, E. Coronado, *J. Am. Chem. Soc.* 2016, **138**, 2576–2584.
- ¹²⁹ S. Sakaida, K. Otsubo, O. Sakata, C. Song, A. Fujiwara, M. Takata, H. Kitagawa, *Nature Chem.*, 2016, **8**, 377–383.
- ¹³⁰ D. Jariwala, T. Marks, M. C. Hersam, *Nature Mater* **2017**, *16*, 170–181.
- ¹³¹ I. Stassen, M. Styles, G. Greci, H. Van Gorp, W. Vanderlinden, S. De Feyter, P. Falcaro, D. De Vos, P. Vereecken, R. Ameloot, *Nat. Mat.* 2016, **5**, 304–310.
- ¹³² Y. Peng, Y. Li, Y. Ban, H. Jin, W. Jiao, X. Liu, W. Yang, *Science* 2014, **346**, 1356–1359.
- ¹³³ J. A. Foster, S. Henke, A. Schneemann, R. A. Fischer, A. K. Cheetham, *Chem. Commun.* 2016, **52**, 10474–10477.