

Breathing-Dependent Redox Activity in a Tetrathiafulvalene-based Metal-Organic Framework

Manuel Souto,[†] Jorge Romero,[†] Joaquín Calbo,[#] Iñigo J. Vitórica-Yrezábal,[§] José L. Zafra,[‡] Juan Casado,[‡] Enrique Ortí,[†] Aron Walsh,^{#,∇} Guillermo Mínguez Espallargas^{*,†}

[†] Instituto de Ciencia Molecular (ICMol), Universidad de Valencia, c/Catedrático José Beltrán, 2, 46980 Paterna, Spain

[#] Department of Materials, Imperial College London, London SW7 2AZ, United Kingdom

[∇] Department of Materials Science and Engineering, Yonsei University, Seoul 03722, Korea

[§] School of Chemistry, University of Manchester, Oxford Road, Manchester M13 9PL, United Kingdom

[‡] Departamento de Química Física, Universidad de Málaga, 29071 Málaga, Spain

KEYWORDS. *Metal-Organic Framework, breathing behavior, tetrathiafulvalene, redox activity.*

ABSTRACT: “Breathing” metal-organic frameworks (MOFs) which involve changes in their structural and physical properties upon an external stimulus are an interesting class of crystalline materials due to their range of potential applications including chemical sensors. The addition of redox activity opens up a new pathway for multi-functional “breathing” frameworks. Herein we report the continuous breathing behavior of a tetrathiafulvalene(TTF)-based MOF, namely **MUV-2**, showing a reversible swelling (up to *ca.* 40% of the volume cell) upon solvent adsorption. Importantly, the planarity of the TTF linkers is influenced by the breathing behavior, directly impacting on their electrochemical properties, thus opening the way for the development of new electrochemical sensors. Quantum chemical calculations and Raman spectroscopy have been used to provide insights into the tunability of the oxidation potential.

1. Introduction

Metal-organic frameworks (MOFs) are crystalline porous materials formed by inorganic building units and organic linkers that find several applications such as gas storage and separation, sensing or catalysis.¹ Although chemical and robustness of MOFs have been key features in terms of possible industrial applications, during the past years there has been a growing interest in the design of flexible MOFs which undergo structural changes upon exposure to physical or chemical stimuli.^{2–4} However, among the about 70 000 reported MOFs, only around 100 exhibit flexible or “breathing” behavior in response to an external stimulus.^{3,5,6} Typically, the reversible transitions in flexible MOFs occur through well-defined phase transitions between wide-pore and narrow-pore forms which can be exemplified by the case of MIL-53.^{7,8} On the contrary, MOFs exhibiting large flexibility without exhibition of well-defined transitions are extremely rare.⁵ This behavior is known as continuous breathing or “swelling” and the prototypical example of such behavior is the family of MIL-88.^{9,10} In both MIL-53 and MIL-88, the breathing behavior is driven by the rotation of the linkers with respect to the inorganic SBUs based on a ‘kneecap’ mechanism. However, there are not many examples in which the breathing is based on the flexibility of the ligand.^{11,11}

Breathing MOFs are even more interesting if they are able to tune the physical properties upon structural changes since they

could be exploited for sensing or chemical-reporting applications. Recently, Farha and coworkers presented a Zr-based breathing MOF with flexible pyrene ligands where the linker conformational modifications are reflected in changes in its optical properties.¹²

On the other hand, redox-active MOFs¹³ have attracted a big deal of attention due to their potential application in electrocatalysis,¹⁴ electrochromic devices,¹⁵ conductors¹⁶ and switches.¹⁷ In particular, tetrathiafulvalene(TTF)-based MOFs are promising systems for the development of multifunctional materials due to the intrinsically redox, electron-donor and conducting properties of the TTF ligand.^{18–21} In this line, Zhou and coworkers have demonstrated the reversible modulation of the breathing behavior of a TTF-based MOF upon oxidation and reduction of the TTF modifying the flexibility of the linker.²²

Very recently, we have reported a highly stable and TTF-based MOF, namely **MUV-2** (MUV: Materials of University of Valencia), which shows a hierarchical crystal structure with mesoporous one-dimensional channels and orthogonal microporous channels.²³ This hierarchical MOF, based on 6-connected [Fe₃O(μ₃O)(COO)₆] secondary building units (SBUs) and tetra-topic tetrathiafulvalene tetrabenzoic (TTFB⁺) ligands, shows high thermal and chemical stability and has proven to be an efficient catalyst for the aerobic oxidation of dibenzothiophenes.

Herein we report on the continuous breathing behavior of **MUV-2** upon solvent adsorption by exploiting the flexibility of the boat-shaped TTFTB ligand (Figure 1). The reversible swelling of *ca.* 40% was studied in terms of cell dimensions between four different crystal structures of **MUV-2(X)**, where $X = 29, 31, 33$ and 35 , which were determined by single-crystal X-ray diffraction as well as by the effect of different solvents on the framework by powder X-ray diffraction. Interestingly, the cell volume of the crystal structures is directly related to the degree of bending or planarity of the TTFTB ligands. Otherwise, the dihedral angles of TTFTB linkers have a direct influence on the ionization energy of the molecules and, therefore, on the oxidation potential of **MUV-2** as confirmed by quantum chemical calculations of the energy associated with electron removal. The tunability of the electrochemical properties of **MUV-2** based on the breathing behavior has been demonstrated to have potential application as electrochemical sensor. This is the first example of how the breathing behavior promoted by guest inclusion and based on a flexible ligand can modulate the redox properties of a MOF.

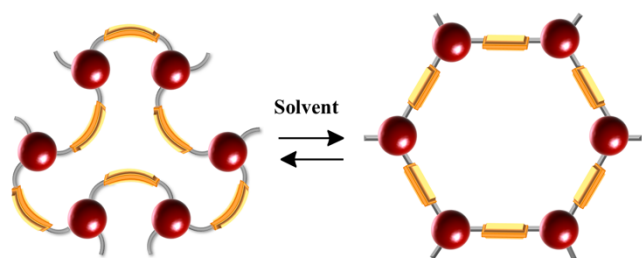


Figure 1. Schematic representation of the breathing behavior of **MUV-2** upon solvent adsorption.

2. Results and discussion

2.1. X-ray diffraction analysis

MUV-2 was synthesized, washed and characterized as previously described.²³ Single-crystal X-ray diffraction data were collected at the I19 beamline facilities at Diamond Light Source (UK) that were used to determine four different isolated phases of **MUV-2** during the breathing behavior (see Supporting Information). As it has been previously reported,²³ **MUV-2** crystal structure is hexagonal (space group $P-62m$), and based on the connection of six $\text{Fe}_3\text{O}(\text{COO})_6$ SBUs and tetrapotic TTFTB ligands it can be simplified as a 3,6-connected network with ttp topology.²⁴ This non-interpenetrated structure shows hexagonal mesoporous channels of *ca.* 3 nm in diameter along the c -axis direction formed by 6 TTFTB linkers and 6 SBUs (Figure 2). On the other hand, microporous channels of *ca.* 1 nm formed by 2 TTFTB ligands and 2 SBUs are disposed orthogonal to the mesoporous ones.

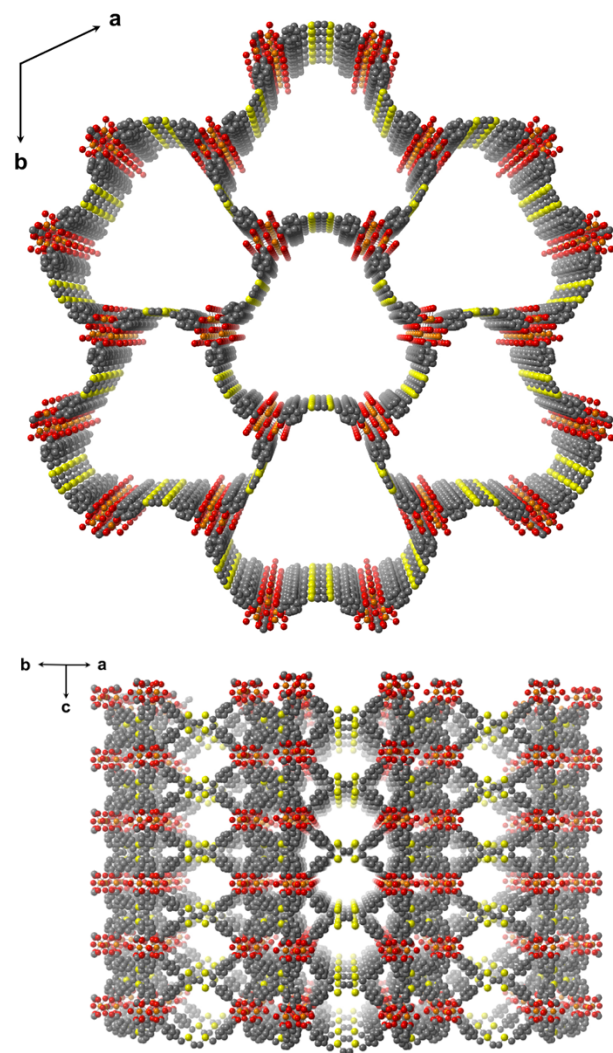


Figure 2. Overview of the crystal structure of **MUV-2** showing the hexagonal mesoporous channels along the c -axis (top) and microporous channels orthogonal to the mesoporous ones (bottom). The grey, yellow, red and orange balls represent the C, S, O and Fe atoms, respectively. For simplicity, hydrogens are omitted.

The breathing behavior of **MUV-2** was studied in terms of four isolated crystal structures determined by single-crystal X-ray diffraction using synchrotron radiation, denoted as **MUV-2(29, 31, 33 and 35)** in accordance with the a and b unit cell parameters (Figure 3). The crystal structure of **MUV-2** is contracted and expanded through the ab plane whereas the c cell parameter remains almost unaltered, retaining in all four structures the same symmetry (hexagonal) and space group ($P-62m$). The as-synthesized structure, **MUV-2(33)** (Figure 3c), shows a significant contraction upon drying treatment providing the narrowest form, namely **MUV-2(29)** (Figure 3a). Upon adsorption of different solvents, the unit cell gradually increases, obtaining intermediate crystal structures such as **MUV-2(31)** (Figure 3b). The largest unit cell is observed using pyridine as guest, producing **MUV-2(35)** (Figure 3d), in which 3 pyridines molecules are coordinated to the $\text{Fe}_3\text{O}(\text{COO})_6$ SBU replacing the 3 H_2O molecules. The reversible

continuous breathing behavior through the *ab* plane is based on the flexibility of the TTFTB ligands, becoming much more planar upon solvent adsorption, and also on the partial rotation of the $\text{Fe}_3\text{O}(\text{COO})_6$ SBUs. The shape of the pore changes from a triangle in **MUV-2(29)** to a hexagon in **MUV-2(35)**, with a significant change of the distance between the calculated centroid of the C=C central bond of adjacent TTFs (16.7 Å vs. 29.5 Å, respectively) (Figure 3) and a total expansion of *ca.* 40% in the crystal structure volume (9427 Å³ vs. 13163 Å³).

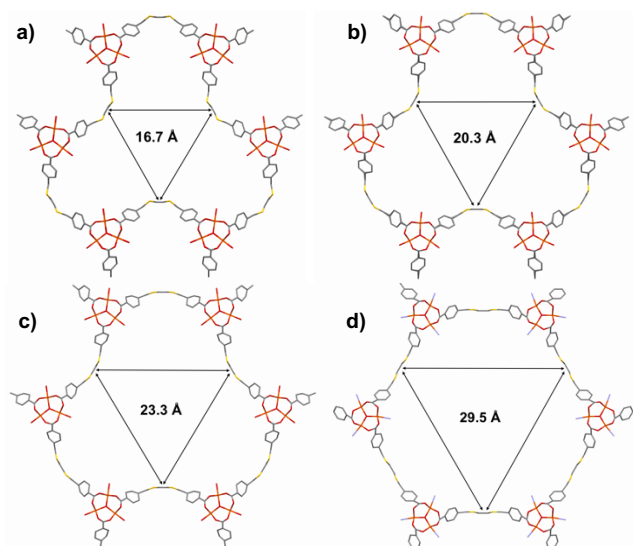


Figure 3. Crystal view of the pore opening evolution of a) **MUV-2(29)** ($a = b = 29.4$ Å; $c = 12.5$ Å), b) **MUV-2(31)** ($a = b = 31.9$; $c = 12.5$ Å), c) **MUV-2(33)** ($a = b = 33.3$; $c = 12.4$ Å), and d) **MUV-2(35)** ($a = b = 35.4$ Å; $c = 12.1$ Å) forms. The grey, yellow, red, orange and blue ellipsoids represent the C, S, O, Fe and N atoms, respectively. For simplicity, hydrogens are omitted.

According to the single crystal structures, the reversible expansion and contraction of $\sim 40\%$ between **MUV-2(29)** and **MUV-2(35)** occurs primarily through the *ab* plane. This reversible expansion and contraction can also be observed using an optical microscope by exposing few desolvated single crystals of **MUV-2(29)** to pyridine solvent (Figure S2). The exposure of the single crystals to pyridine produces a reversible expansion between 20-30% of the width of the crystal, in agreement with the crystal indexing which reveals that mesoporous channels are oriented along the length of the crystal (Figure S3). After evaporation of the pyridine solvent, the crystals recover the initial dimensions.

The evolution of the planarity of the TTFTB linker with the breathing behavior was analyzed by means of the dihedral angle (θ) formed by the two dithiole rings (planes S1-C1-C2-S2 and S3-C5-C6-S4) in the different crystal structures. The angles were found to be 69°, 54°, 41° and 9° for **MUV-2(29)**, **MUV-2(31)**, **MUV-2(33)** and **MUV-2(35)**, respectively (Figures 4 and S4). Moreover, the torsion angles of S2-C3-S1-C1, which are also related to the degree of planarity of the TTF;²⁵ also decreased when increasing the volume cell obtaining values of 32°, 26°, 17° and 14°, respectively.

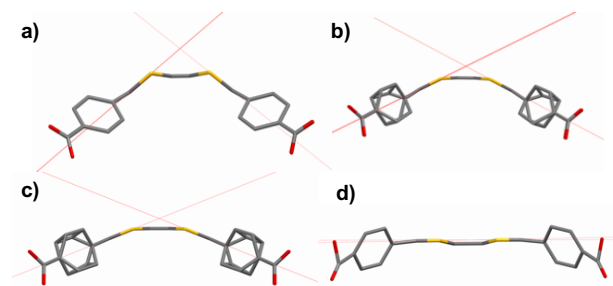


Figure 4. Partial views of the TTFTB ligand for the crystal structures of a) **MUV-2(29)**; b) **MUV-2(31)**; c) **MUV-2(33)** and d) **MUV-2(35)** highlighting the dihedral angles between the planes formed by the two dithiole rings ($\theta = 69^\circ$, 54° , 41° and 9° , respectively).

2.2. Breathing behavior upon solvent adsorption

Powder X-ray diffraction (PXRD) pattern of activated material shows that (100) peak appears at $2\text{-theta} = 3.45^\circ$ after solvent removal, in agreement with the contracted **MUV-2(29)** crystal structure. This peak shifts towards lower degrees after soaking **MUV-2(29)** with different solvents during 24h (Figure 5). As also observed in MIL-88,^{9,10} the breathing behavior is very selective and the pore opening depends on the nature of the solvent. Strongly polar solvents such as pyridine, which is coordinated to the $\text{Fe}_3\text{O}(\text{COO})_6$ SBU replacing the water molecules, generate the largest pore opening with a PXRD pattern similar to the one simulated from the crystal structure of **MUV-2(35)**. Otherwise, exposure to ethanol, water, toluene and acetonitrile yields intermediate cell variations with PXRD patterns similar to the ones simulated from **MUV-2(33)** and **MUV-2(31)** crystal structures, thus showing a continuous breathing behavior. Interestingly, PXRD patterns with ethanol, water and toluene show the presence of two principal peaks which can be related to a decrease of symmetry. The different breathing behavior of the solvents can be explained by the coordination of the polar organic solvent molecules with the inorganic $\text{Fe}_3\text{O}(\text{COO})_6$ SBUs (as observed in the case of pyridine) or by weak interactions with the organic linkers, a behavior which is similar to those of MIL-88 family.^{9,10} Moreover, the reversible swelling of **MUV-2(35)** was confirmed by heating the soaked material with pyridine obtaining the initial desolvated PXRD pattern (Figure S5). It is important to note that the EPR spectra of **MUV-2** in the different solvents do not show the presence of any signal related to TTFTB⁺ radical indicating that the TTFTB moieties remain in the neutral state (Figure S6). Moreover, thermogravimetric analysis (TGA) of **MUV-2** in different solvents was performed to determine the amounts of solvent molecules included in the pores in each case (Figure S7).

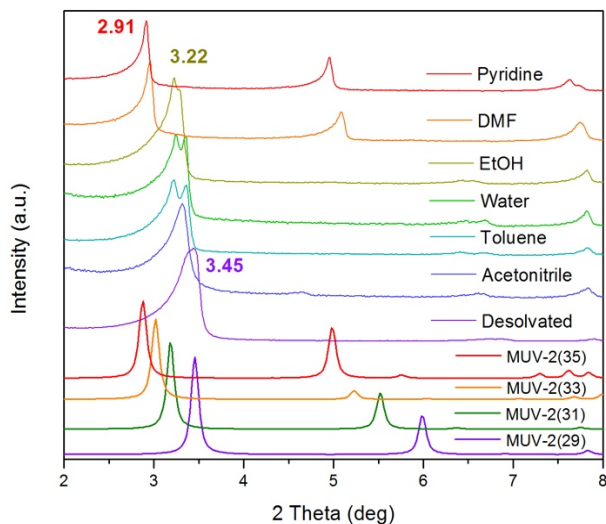


Figure 5. Evolution of PXRD patterns for **MUV-2** after soaking with various solvents at room temperature. Simulated diffraction patterns of **MUV-2(29)**, **MUV-2(31)**, **MUV-2(33)** and **MUV-2(35)**.

2.3. Quantum chemical calculations

Based on the significant conformational changes of the TTF moiety observed in the different crystal structures, we aimed to analyze the impact of the TTF curvature on the electronic structure and redox properties of **MUV-2**. First, the minimum-energy structure of **MUV-2** was obtained upon full ion and lattice relaxation under the density functional theory (DFT) framework. The range-separated hybrid exchange-correlation HSE06 functional was employed along with the “Tier 1” numerical basis set using the FHI-AIMS package^{26–28} (see the SI for full Computational Details). A high-spin configuration for the Fe atoms was adopted in line with the experimental evidences.²³ The optimized structure of **MUV-2** (Figure S8) compares well with the X-ray structure of **MUV-2(33)**, and provides optimized lattice parameters of $a = 34.03 \text{ \AA}$, $b = 34.06 \text{ \AA}$, $c = 12.15 \text{ \AA}$, $\alpha = 90.4^\circ$, $\beta = 89.5^\circ$, $\gamma = 120.2^\circ$, a TTF boat dihedral angle of $\theta = 46.24^\circ$, and a pore opening (distance between centroid of the C=C central bond of adjacent TTFs) of 23.95 \AA . Note that substitution of the two coordinating water molecules by acetonitrile or pyridine barely affect the TTF tilting, with a boat dihedral angle θ of 44.82 and 45.53° , respectively (Figure S9). The breathing behaviour of **MUV-2** must therefore be originated from long-range electrostatic effects (solvent polarity) and/or medium-range electron correlation effects (noncovalent interactions).¹⁰

Analysis of the electronic density of states (DoS) indicates a small bandgap of 0.86 eV originated in the beta-spin manifold (Figure 6a). Projected DoS (PDoS) allows unequivocal assignment of the frontier crystal orbitals (FCOs): the highest-occupied crystal orbital (HOCO) belongs to the organic TTF ligand, whereas the lowest unoccupied crystal orbital (LUCO) is localized in the inorganic cluster (Figure 6a and S10). Visualization of the electronic

eigenstate densities confirmed the nature of the FCOs with a HOCO (Figure 6b) analogous to the highest-occupied molecular orbital of TTF (Figure S11), and a d -orbital HUCO centered on the Fe atoms (Figure 6c). These results suggest that reduction of the MOF must occur in the inorganic cluster, whereas oxidation processes will be centered in the TTF-based ligand. The spin density of the **MUV-2** oxidized by one-electron per TTF ligand (unit cell with three positive charges) confirmed the electron density extraction from the TTF moiety upon oxidation (Figure S12).

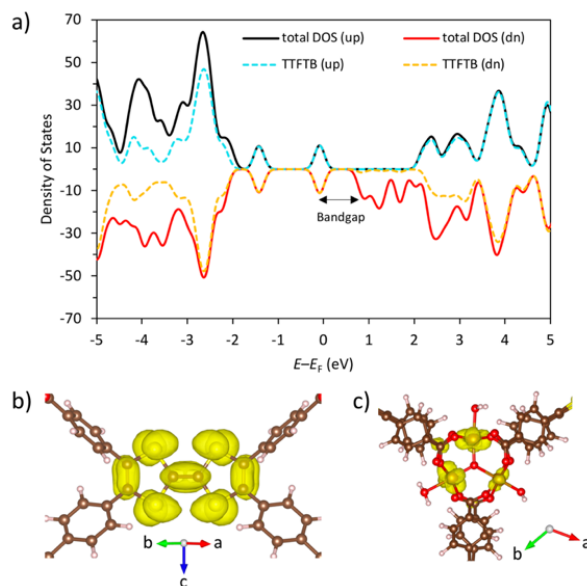


Figure 6. a) Electronic density of states (DoS) calculated at the DFT-HSE06 level of theory for the optimized geometry of **MUV-2**. The highest occupied state (E_F) is set to 0 eV . Spin-up (up) and spin-down (dn) are differentiated with opposite signs. The contribution of the ligand atoms to the DoS is included. b) and c) Eigenstate densities (isovalue = 0.001) for the HOCO and LUCO, respectively, of the beta-spin channel.

In order to analyze the impact of the breathing motion into the electrochemical properties of **MUV-2**, experimental X-ray crystal structures were further employed to achieve geometries with variable TTF curvature (see the SI). The schematic representation of the FCOs versus the characteristic TTF boat dihedral angle θ shows a significant stabilization of 0.41 eV for the TTF-centered HOCO going from $\theta = 30.87^\circ$ to 66.11° (Figure 7). This stabilization has already been reported in molecular systems containing the TTF unit, and is ascribed to an inefficient 6π -electron delocalization that disrupts its donor ability upon deviation from planarity.^{29–31} Otherwise, the Fe-centered LUCO remains practically unaffected upon TTF bending, with an energy range of $[-4.30, -4.40] \text{ eV}$. As a result, an increase of $> 0.3 \text{ eV}$ in the electronic bandgap is predicted going from MOF structures with a planar TTF to those with a highly curved ligand (Figure 7).

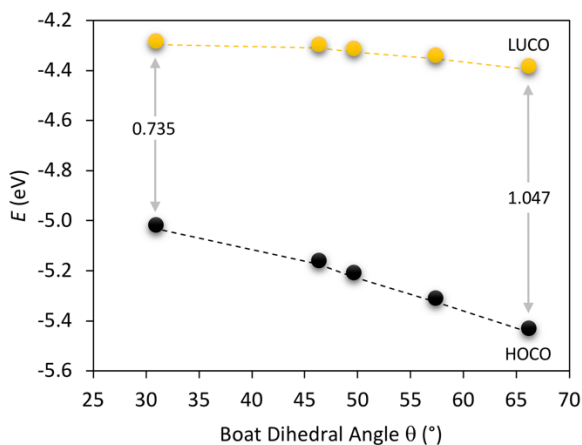


Figure 7. One-electron energy diagram of the frontier crystal orbitals of **MUV-2** with different values for the TTF boat dihedral angle θ as defined in Figure 4. The electronic bandgap (in eV) for the extreme cases is indicated. Dashed lines are included to guide the eye.

We took advantage of the localized nature of the HOCO into the π -conjugated TTF core to analyze the electrochemical properties of **MUV-2** upon ligand bending by performing high-level molecular calculations. The minimum-energy structure of the TTFTB moiety in its neutral (fully-protonated) form was obtained at the DFT-PBE0/cc-pVDZ level of theory in gas phase (Figure S11). Starting from this geometry, a relaxed scan was performed at the same level by varying the characteristic TTF boat dihedral angle. Theoretical calculations predict a small energy penalty upon boat bending, with a large conformational space $0^\circ < \theta < 80^\circ$ accessible within 5 kcal/mol (Figure S17). Initial analysis of the molecular orbitals indicates a significant stabilization of the TTF-centered highest-occupied molecular orbital (HOMO) upon bending (from -4.93 eV at $\theta = 4.84^\circ$ to -5.69 eV at $\theta = 87.34^\circ$; Table S4), in good accord with the solid-state calculations (Figure 7).

The first ionization potential (IP) of the TTFTB ligand was then calculated along the relaxed scan to estimate the effect of the breathing motion into the oxidation potential of **MUV-2** (see the SI). As shown in Figure 8, the IP of TTFTB monotonically decreases upon planarization (6.60 eV at $\theta = 87.34^\circ$ vs. 6.08 eV at $\theta = 37.61^\circ$). It is well known that the TTF unit planarizes upon one-electron oxidation.^{32,33} However, the effect in IP due to the strained rigidity of the ligand in **MUV-2** is calculated to be only of 0.10 eV at the minimum-energy boat dihedral angle $\theta = 35.72^\circ$ (adiabatic IP = 5.97 eV). Further planarization of the ligand leads to a small decrease of IP, with the lowest value of 5.95 eV at $\theta = 4.84^\circ$. Theoretical calculations therefore predict a significant change in the electrochemical properties of **MUV-2** upon swelling, with a systematically increasing ease for oxidation upon planarization of the TTFTB ligand.

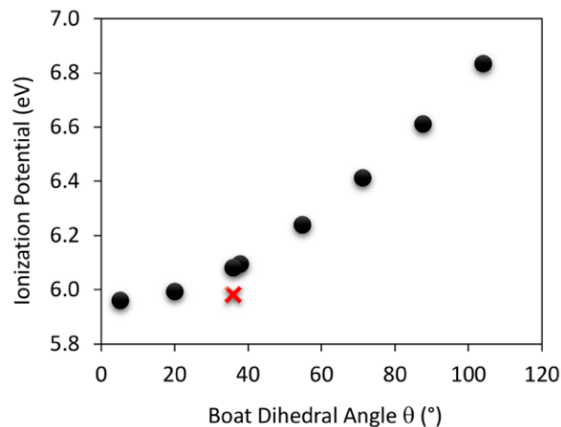


Figure 8. Ionization potential (IP) calculated for the TTFTB ligand molecule from total energy differences at the DFT-PBE0/cc-pVDZ level of theory as a function of the characteristic TTF boat dihedral angle θ . The adiabatic IP calculated for TTFTB as shown as a red cross.

2.4. Electrochemical properties

Encouraged by the theoretical results demonstrating the influence of the breathing motion on the electrochemical properties of **MUV-2**, solid-state Cyclic Voltammetry (CV) and Differential Pulse Voltammetry (DPV) of **MUV-2** were performed in different solvents (Figure 9). We have previously reported the CV of **MUV-2** in CH_3CN up to 1.6 V (vs. Ag/AgCl), which showed a reversible redox peak attributed to the reduction process of $\text{Fe}^{3+}/\text{Fe}^{2+}$ around -0.9 V but no peak related to the oxidation of the TTFTB linkers was observed.²³ Upon increasing the potential up to 3 V, the CV of **MUV-2** shows an irreversible redox peak at 2.2 V, which can be attributed to the oxidation process of the TTFTB units (Figures 9 and S20). In order to investigate the relationship between the Fe and TTFTB moieties, the Randles-Sevcik equation³⁴ was used to determine the Fe/TTFTB molar ratio, that was found to have a value of 1.8 . This value is close to the formula of **MUV-2** ($2 \text{ Fe}_3\text{O SBU}$ s per 3 TTFTB linker).

The solid-state CV of **MUV-2** in pyridine shows that the formal redox potential assigned to the oxidation of TTFTB significantly decreases and two irreversible redox waves were observed at 1.02 V and 1.16 V attributed to the two oxidation processes of TTFTB to TTFTB^+ and TTFTB^{2+} , respectively (Figures 9 and S20). This oxidation potentials are closer to those reported for other TTF-based MOFs.¹⁹ The decrease of the oxidation potential of **MUV-2** when using pyridine as solvent can be explained by the increased planarity of the TTFTB linkers, which significantly decreased the ionization potential as it has been previously showed in the theoretical calculations. Interestingly, when using a solvent such as DMF, which produces an intermediate degree of swelling and planarity of the TTFTB ligands, the formal oxidation potential is slightly higher than that in pyridine (1.40 V) (Figures 9 and S21). Hence, the

electrochemical properties of **MUV-2** can be modulated by the solvent-induced breathing behavior.

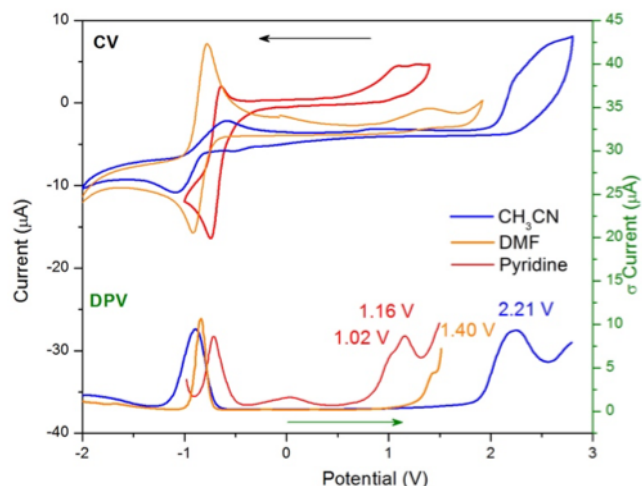


Figure 9. Solid-state Cyclic Voltammetry (CV) and Differential Pulse Voltammetry (DPV) of **MUV-2** in CH_3CN (blue line), DMF (orange line) and pyridine (red line) using TBAPF_6 0.1 M as electrolyte and 0.1 V/s scan rate. Platinum wire was used as the counter electrode and silver wire as the pseudoreference electrode. Ferrocene was added as internal standard. All potentials are reported versus Ag/AgCl .

Based on the idea that the electrochemical properties can be tuned by the effect of the different solvents on the breathing behavior, DPV measurements of **MUV-2** in CH_3CN were performed in the range of 0–2.4 V after adding consecutive aliquots of pyridine in order to study the modification of the oxidation potential of the TTFTB linker (Figure 10). The oxidation peak which initially appears at 2.2 V gradually shifts towards lower potentials when adding pyridine in agreement with the lower ionization potential of **MUV-2** when is soaked with pyridine and the TTFTB linker becomes planar. After adding 100 μl (1% v/v) and 300 μl (3% v/v) of pyridine the oxidation potential moves to 2.0 V and 1.8 V, respectively. Moreover, we also observe the appearance of new peaks in the range of 1.0–1.5 V, which are close to the oxidation peak of **MUV-2**, using exclusively pyridine as solvent. (Figure 10). The presence of numerous peaks indicates different degrees of breathing behavior probably due to diffusion effects. In addition, CV measurements performing the same procedure (Figure S23) also show a gradual shift of the oxidation peak towards lower potential. Thus, consecutive addition of pyridine induces the expansion towards **MUV-2(35)** form and the consequent planarization of TTFTB linkers producing significant changes in its electrochemical response.

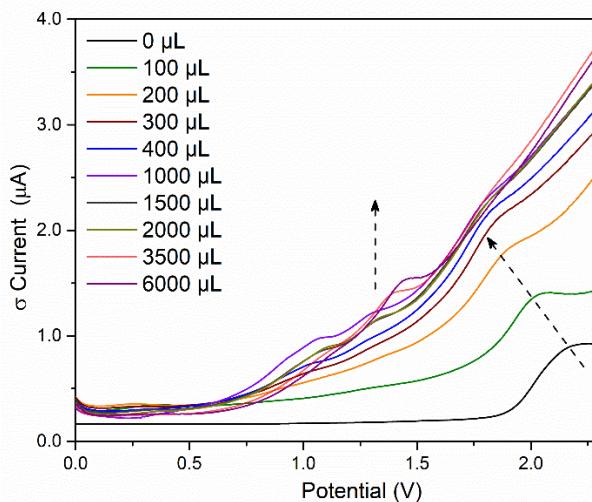


Figure 10. Differential Pulse Voltammetry (DPV) of **MUV-2** in CH_3CN after consecutive addition of aliquots of pyridine using TBAPF_6 0.1 M as electrolyte. Platinum wire was used as the counter electrode and silver wire as the pseudoreference electrode.

Motivated by the idea of isolating the oxidized MOF (**ox-MUV-2**) to study the pore opening of the system, we oxidized **MUV-2** deposited on the electrode applying a constant potential (1.8 V using DMF as solvent, or 1.1 V using pyridine as solvent). EPR spectra demonstrates that the TTFTB linkers were oxidized to TTFTB^+ in agreement with the presence of the typical signal for the radical cation species centered at $g = 2.006$ (Figure S25). However, the PXRD pattern shows that crystallinity is decreased (Figure S26), and IR spectra suggest that some of TTFTB linkers are uncoordinated to the metal due to the presence of bands at 1691 cm^{-1} assigned to free $\text{C}=\text{O}$ groups (Figure S27). This suggests that an irreversible decarboxylation upon oxidation is produced related to the Kolbe reaction, as it has been observed for other TTF bearing carboxylic moieties.^{35,36} Some electrochemical studies performed on different TTF bearing carboxylic acids suggests that a decarboxylation process occurs only during the second oxidation step (the formation of the dication species), which is irreversible.³⁷ In the case of **MUV-2**, it has been not possible to control the oxidation up to the radical cation state since the two oxidation peaks are very close.

2.5. Raman spectroscopy

The vibrational fingerprint of **MUV-2** can provide structural information of the dynamics and of the structural changes in the interior of the pores under a variety of conditions.^{38,39} Hence, a complete study of the vibrational Raman properties of desolvated **MUV-2**, upon solvation with pyridine, acetonitrile and DMF (**py-MUV-2**, **ACN-MUV-2** and **DMF-MUV-2**) and electrochemically oxidized (**ox-MUV-2**) has been carried out with two different Raman laser excitation lines (633 and 785 nm, shown in Figure 11 and Figure S28, respectively).

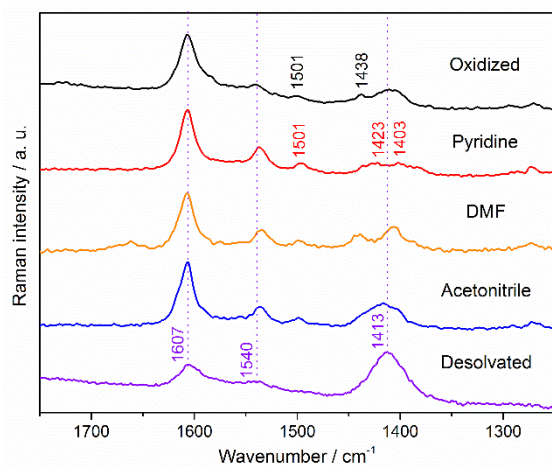


Figure 11. 633 nm Raman spectra of desolvated **MUV-2** (purple line), and solvated with acetonitrile (blue line), DMF (orange line), and pyridine (red line), and electrochemically oxidized **ox-MUV-2** (black line) at 298 K in solid state. See Figure S29 for a larger spectral range.

The 785 and 633 nm Raman spectra of the desolvated sample are dominated by the presence of three main bands in the 1650-1400 cm^{-1} interval: the band at 1607 cm^{-1} (i.e., due to the C=C stretching vibration of the benzene moieties), the band at 1540 cm^{-1} (i.e., assigned to the C=C stretching mode of the TTF moiety) and the broad band at 1413 cm^{-1} (i.e., arising from the stretching modes of the carboxylate groups). See Figures S18-S19 for the simulated Raman spectra. Importantly, the relative Raman intensity pattern of these bands consists of the strongest band at 1413 cm^{-1} followed by the 1607 cm^{-1} with medium intensity. In the case of the electrochemically oxidized **ox-MUV-2**, the spectral intensity pattern in the 1650-1400 cm^{-1} interval is reversed compared with the unoxidized material, with the strongest feature now at 1607 cm^{-1} and those at 1440-1400 cm^{-1} as medium bands. In addition, two new weak bands appear at 1501 and 1438 cm^{-1} , which are assigned to those Raman modes in the oxidized TTF moiety that result from the frequency softening of the C=C stretching modes upon oxidation of the TTF unit.

Solvation causes structural changes that make their Raman spectra to resemble that of the oxidized material. This is inferred by the relative intensity pattern of the bands at 1607 (strongest) and 1440-1400 cm^{-1} (medium), and by the appearance of new bands at 1501 and 1440-1410 cm^{-1} in the solvated samples in analogy with the Raman spectrum for **ox-MUV-2**. Based on the fact that oxidation of TTF produces its backbone planarization, the spectral similitude with the solvated materials indicates that solvation also produces the planarization of the TTF unit of **MUV-2**. Looking more in detail to the 1440-1400 cm^{-1} region of the solvated samples, significant differences are found between the spectra. Whereas four peaks are observed for **py-MUV-2**, a main band with two shoulders is resolved in **ACN-MUV-2** (for **DMF-MUV-2** the solvent bands prevent further comparisons). It seems that the

spectral changes in this region are less marked for **ACN-MUV-2** than for **py-MUV-2** (1 peak in the former and 4 peaks in the latter), revealing that adsorption of acetonitrile induces smaller changes in the Raman spectra. This is in perfect agreement with the structural features obtained by X-ray diffraction.

3. Conclusions

In summary, we have reported the continuous breathing behavior of a TTF-based MOF, namely **MUV-2**, which shows up to 40% of a reversible expansion upon solvent adsorption. Interestingly, the planarity of the TTF linkers is influenced by the breathing behavior as demonstrated by single-crystal X-ray diffraction and Raman spectroscopy. Theoretical calculations show that the degree of planarity of the TTF ligands has a direct influence on the electrochemical properties and the tunability of the oxidation potential of **MUV-2** upon adsorption of solvents. These results open the way to develop new electrochemical sensor based on the breathing behavior and new materials in which it could be possible to control the pore opening upon application of electrochemical potential.

ASSOCIATED CONTENT

Supporting Information. General methods and materials, crystallographic data, theoretical calculations, electrochemical measurements, characterization of oxidized **MUV-2**, Raman spectroscopy. This material is available free of charge via the Internet.

AUTHOR INFORMATION

Corresponding Author

* guillermo.minguez@uv.es

Author Contributions

The manuscript was written through contributions of all authors. All authors have given approval to the final version of the manuscript.

Funding Sources

Any funds used to support the research of the manuscript should be placed here (per journal style).

ACKNOWLEDGMENT

The work has been supported by the European Union (ERC- 2016-CoG 724681-S-CAGE) and the Spanish MINECO (CTQ2014-59209-P and CTQ2017-89528-P) and (CTQ2015-69391-P). We also thank the Spanish government for the provision of a María de Maeztu project (MDM-2015-0538). G. M. E. and M. S. thank MINECO for a Ramón y Cajal and a Juan de la Cierva-Formación fellowships, respectively. We thank the Diamond Light Source (UK) for the synchrotron beamtime. The work at ICL has been supported by the Leverhulme Trust and the Royal Society. Via our membership of the UK's HEC Materials Chemistry Consortium, which is funded by EPSRC (EP/L000202), this work used the ARCHER supercomputing service.

ABBREVIATIONS

TTFTB, tetrathiafulvalene tetrabenzoic; MUV, Materials of University of Valencia; MOF, Metal-Organic Framework; CV, Cyclic Voltammetry.

REFERENCES

- (1) Maurin, G.; Serre, C.; Cooper, A.; Férey, G. *Chem. Soc. Rev.* **2017**, *46*, 3104.
- (2) Férey, G.; Serre, C. *Chem. Soc. Rev.* **2009**, *38*, 1380.
- (3) Schneemann, A.; Bon, V.; Schwedler, I.; Senkovska, I.; Kaskel, S.; Fischer, R. A. *Chem. Soc. Rev.* **2014**, *43*, 6062.
- (4) Morris, R. E.; Brammer, L. *Chem. Soc. Rev.* **2017**, *46*, 5444.
- (5) Carrington, E. J.; McAnally, C. A.; Fletcher, A. J.; Thompson, S. P.; Warren, M.; Brammer, L. *Nat. Chem.* **2017**, *9*, 882.
- (6) Moghadam, P. Z.; Li, A.; Wiggin, S. B.; Tao, A.; Maloney, A. G. P.; Wood, P. A.; Ward, S. C.; Fairen-Jimenez, D. *Chem. Mater.* **2017**, *29*, 2618.
- (7) Serre, C.; Millange, F.; Thouvenot, C.; Noguès, M.; Marsolier, G.; Louër, D.; Férey, G. *J. Am. Chem. Soc.* **2002**, *124*, 13519.
- (8) Horcajada, P.; Serre, C.; Maurin, G.; Ramsahye, N. a.; Balas, F.; Sebban, M.; Taulelle, F.; Vallet-Regi, M.; Férey, G. *J. Am. Chem. Soc.* **2008**, *130*, 6774.
- (9) Mellot-Draznieks, C.; Serre, C.; Surblé, S.; Audebrand, N.; Férey, G. *J. Am. Chem. Soc.* **2005**, *127*, 16273.
- (10) Serre, C.; Mellot-Draznieks, C.; Surblé, S.; Audebrand, N.; Filinchuk, Y.; Férey, G. *Science* **2007**, *315*, 1828.
- (11) Lin, Z.-J.; Lü, J.; Hong, M.; Cao, R. *Chem. Soc. Rev.* **2014**, *43*, 5867.
- (12) Deria, P.; Gómez-Gualdrón, D. A.; Bury, W.; Schaefer, H. T.; Wang, T. C.; Thallapally, P. K.; Sarjeant, A. A.; Snurr, R. Q.; Hupp, J. T.; Farha, O. K. *J. Am. Chem. Soc.* **2015**, *137*, 13183.
- (13) D'Alessandro, D. M. *Chem. Commun.* **2016**, *52*, 8957.
- (14) Ahrenholtz, S. R.; Epley, C. C.; Morris, A. J. *J. Am. Chem. Soc.* **2014**, *136*, 2464.
- (15) Kung, C. W.; Wang, T. C.; Mondloch, J. E.; Fairen-Jimenez, D.; Gardner, D. M.; Bury, W.; Klingsporn, J. M.; Barnes, J. C.; Van Duyne, R.; Stoddart, J. F.; Wasielewski, M. R.; Farha, O. K.; Hupp, J. T. *Chem. Mater.* **2013**, *25*, 5012.
- (16) Darago, L. E.; Aubrey, M. L.; Yu, C. J.; Gonzalez, M. I.; Long, J. R. *J. Am. Chem. Soc.* **2015**, *137*, 15703.
- (17) Gui, B.; Meng, X.; Chen, Y.; Tian, J.; Liu, G.; Shen, C.; Zeller, M.; Yuan, D.; Wang, C. *Chem. Mater.* **2015**, *27*, 6426.
- (18) Wang, H.-Y.; Cui, L.; Xie, J.-Z.; Leong, C. F.; D'Alessandro, D. M.; Zuo, J.-L. *Coord. Chem. Rev.* **2017**, *345*, 342.
- (19) Wang, H.-Y.; Ge, J.-Y.; Hua, C.; Jiao, C.-Q.; Wu, Y.; Leong, C. F.; D'Alessandro, D. M.; Liu, T.; Zuo, J.-L. *Angew. Chem. Int. Ed.* **2017**, *56*, 5465.
- (20) Narayan, T. C.; Miyakai, T.; Seki, S.; Dincă, M. *J. Am. Chem. Soc.* **2012**, *134*, 12932.
- (21) Park, S. S.; Hontz, E. R.; Sun, L.; Hendon, C. H.; Walsh, A.; Van Voorhis, T.; Dincă, M. *J. Am. Chem. Soc.* **2015**, *137*, 1774.
- (22) Su, J.; Yuan, S.; Wang, H.-Y.; Huang, L.; Ge, J.-Y.; Joseph, E.; Qin, J.; Cagin, T.; Zuo, J.-L.; Zhou, H.-C. *Nat. Commun.* **2017**, *8*, 2008.
- (23) Souto, M.; Santiago-Portillo, A.; Palomino, M.; Vitorica-Yrzebal, I.; Vieira, B. J. C.; Waerenborgh, J. C. C.; Valencia, S.; Navalon, S.; Rey, F.; Garcia, H.; Minguez Espallargas, G. *Chem. Sci.* **2018**, *9*, 2413.
- (24) Although the topology of MUV-2 has been previously described as a binoidal (4,6)-c net,²³ the correct topology is a binoidal (3,6)-c net since the linker should be abstracted as a two three-coordinated nodes.
- (25) Mukherjee, V.; Singh, N. P. *Spectrochim Acta A Mol Biomol Spectrosc* **2014**, *117*, 315.
- (26) Blum, V.; Gehrke, R.; Hanke, F.; Havu, P.; Havu, V.; Ren, X.; Reuter, K.; Scheffler, M. *Comput. Phys. Commun.* **2009**, *180*, 2175.
- (27) Havu, V.; Blum, V.; Havu, P.; Scheffler, M. *J. Comput. Phys.* **2009**, *228*, 8367.
- (28) Ren, X.; Rinke, P.; Blum, V.; Wieferink, J.; Tkatchenko, A.; Sanfilippo, A.; Reuter, K.; Scheffler, M. *New J. Phys.* **2012**, *14*, 53020.
- (29) Hansen, T. K.; Joergensen, T.; Jensen, F.; Thygesen, P. H.; Christiansen, K.; Hursthouse, M. B.; Harman, M. E.; Malik, M. A.; Girmay, B. *J. Org. Chem.* **1993**, *58*, 1359.
- (30) Wang, C. S.; Bryce, M. R.; Batsanov, A. S.; Howard, J. A. K. *Chem. Eur. J.* **1997**, *3*, 1679.
- (31) Berridge, R.; Serebryakov, I. M.; Skabara, P. J.; Ortí, E.; Viruela, R.; Pou-Américo, R.; Coles, S. J.; Hursthouse, M. B. *J. Mater. Chem.* **2004**, *14*, 2822.
- (32) Adamo, C.; Arnaud, R.; Scalmani, G.; Müller, H.; Sahli, F.; Barone, V. *J. Phys. Chem. B* **1999**, *103*, 6863.
- (33) Yakushi, K.; Nishimura, S.; Sugano, T.; Kuroda, H.; Ikemoto, I. *Acta Crystallogr. Sect. B Struct. Crystallogr. Cryst. Chem.* **1980**, *36*, 358.
- (34) Zhang, T.; Hu, Y. Q.; Han, T.; Zhai, Y. Q.; Zheng, Y. Z. *ACS Appl. Mater. Interfaces* **2018**, *10*, 15786.
- (35) Nguyen, T. L. A.; Demir-Cakan, R.; Devic, T.; Morcrette, M.; Ahnfeldt, T.; Auban-Senzier, P.; Stock, N.; Goncalves, A. M.; Filinchuk, Y.; Tarascon, J. M.; Férey, G. *Inorg. Chem.* **2010**, *49*, 7135.
- (36) Nguyen, T. L. A.; Devic, T.; Mialane, P.; Rivière, E.; Sonnauer, A.; Stock, N.; Demir-Cakan, R.; Morcrette, M.; Livage, C.; Marrot, J.; Tarascon, J. M.; Férey, G. *Inorg. Chem.* **2010**, *49*, 10710.
- (37) Idriss, K. A.; Chambers, J. Q. *J. Electroanal. Chem.* **1980**, *109*, 340.
- (38) Krylov, A.; Vtyurin, A.; Petkov, P.; Senkovska, I.; Maliuta, M.; Bon, V.; Heine, T.; Kaskel, S.; Slyusareva, E. *Phys. Chem. Chem. Phys.* **2017**, *19*, 32099.
- (39) Hoffman, A. E. J.; Vanduyfhuys, L.; Nevjestić, I.; Wieme, J.; Rogge, S. M. J.; Depauw, H.; Van Der Voort, P.; Vrielinck, H.; Van Speybroeck, V. *J. Phys. Chem. C* **2018**, *122*, 2734.

Table of Contents (TOC)

